

10-27-2003

Spin blockade in ferromagnetic nanocontacts

M. Ye Zhuralev

University of Nebraska - Lincoln

Evgeny Y. Tsymbal

University of Nebraska-Lincoln, tsymbal@unl.edu

Sitaram Jaswal

University of Nebraska, sjaswal1@unl.edu

A.V. Vedyayev

CEA/Grenoble, Departement de Recherche Fondamentale sur la Matiere Condensee, SPINTEC

B. Dieny

CEA/Grenoble, Departement de Recherche Fondamentale sur la Matiere Condensee, SPINTEC

Follow this and additional works at: <http://digitalcommons.unl.edu/mrsecfacpubs>



Part of the [Materials Science and Engineering Commons](#)

Zhuralev, M. Ye; Tsymbal, Evgeny Y.; Jaswal, Sitaram; Vedyayev, A.V.; and Dieny, B., "Spin blockade in ferromagnetic nanocontacts" (2003). *Faculty Publications: Materials Research Science and Engineering Center*. 33.

<http://digitalcommons.unl.edu/mrsecfacpubs/33>

This Article is brought to you for free and open access by the Materials Research Science and Engineering Center at DigitalCommons@University of Nebraska - Lincoln. It has been accepted for inclusion in Faculty Publications: Materials Research Science and Engineering Center by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.

Spin blockade in ferromagnetic nanocontacts

M. Ye. Zhuravlev,^{a)} E. Y. Tsymbal, and S. S. Jaswal

*Department of Physics and Astronomy and Center for Materials Research and Analysis,
University of Nebraska, Lincoln, Nebraska 68588*

A. V. Vedyayev^{b)} and B. Dieny

*CEA/Grenoble, Département de Recherche Fondamentale sur la Matière Condensée, SPINTEC,
38054 Grenoble, France*

(Received 10 July 2003; accepted 5 September 2003)

Using a free-electron model and a linear response theory we investigate spin-dependent electronic transport in magnetic nanocontacts in the ballistic regime of conduction. We emphasize the fact that in atomic-size ferromagnetic contacts it is possible to achieve the conductance value of e^2/h , which implies a fully spin-polarized electric current. We explore some consequences of this phenomenon. In particular, we show that the presence of a nonmagnetic region in the nanocontact separating two ferromagnetic electrodes can lead to a spin blockade resulting in very large values of magnetoresistance. © 2003 American Institute of Physics. [DOI: 10.1063/1.1622986]

The electrical conductance through a narrow constriction is quantized when the constriction width is comparable to the electron Fermi wavelength. This phenomenon was discovered in two-dimensional electron gas semiconductor structures, in which the constriction width can be controlled by the gate voltage.¹ The quantized conductance was also observed in metallic nanowires, where an atomic-size constriction is created by pulling off two electrodes in contact.²⁻⁴ The conductance quantization can be explained within the Landauer formula⁵ and the adiabatic principle,⁶ according to which the conductance is given by $\Gamma = Ne^2/h$, where N is the number of open conducting channels, i.e., the number of transverse modes at the Fermi energy. When the constriction width changes the number of conducting channels and consequently the conductance vary in discrete steps. For diamagnetic nanowires the conductance is quantized in units of $2e^2/h$, where the factor 2 stands for spin degeneracy. If the constriction is made of a ferromagnetic metal, such as Ni, the exchange energy lifts the spin degeneracy and the conductance is quantized in units of e^2/h . Such a phenomenon was observed in Ni break junctions,⁷ Ni nanowires electrodeposited into pores of membranes,⁸ Ni atomic-size contacts made by a scanning tunneling microscope,⁹ and electrodeposited Ni nanocontacts grown by filling an opening in focused-ion-beam-milled nanowires.¹⁰

An interesting observation that follows from these studies is the possibility to achieve the conductance value of e^2/h , which implies that one spin channel is open, whereas the other spin channel is closed. In this regime the ferromagnetic atomic-size constrictions resemble half-metallic bulk ferromagnets, materials for which only one spin band is occupied at the Fermi level, resulting in a perfect 100% spin polarization.¹¹ We see, therefore, that by making a sufficiently narrow nanoconstriction from an ordinary ferromagnet it is possible to achieve a fully spin-polarized electric current.

In this letter, using a free-electron model and quantum-mechanical description of electronic transport in the ballistic regime we explore some consequences of this phenomenon. In particular, we show that the presence of a nonmagnetic region in the nanocontact separating two ferromagnetic electrodes can lead to a spin blockade resulting in very large values of magnetoresistance.

We model nanoconstrictions by considering a segmented cylindrical nanowire of a variable radius as shown in Fig. 1(a). The electronic structure of the nanowire is described by free electrons moving in a constant potential V_j within each

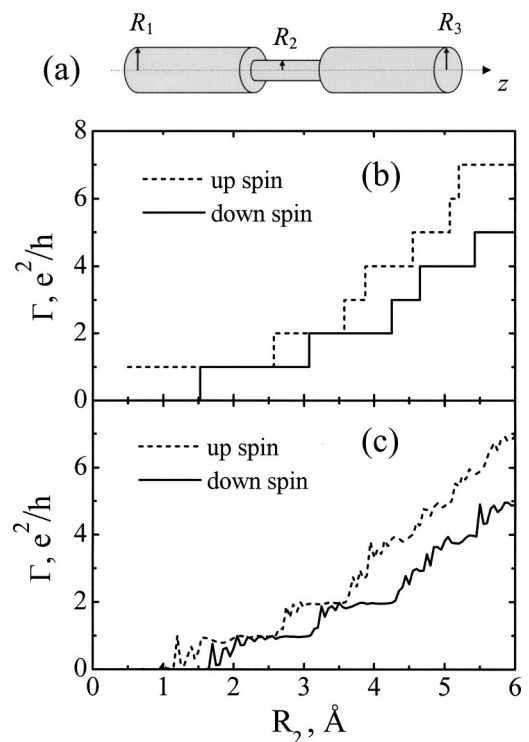


FIG. 1. (a) Segmented nanowire representing a nanoconstriction; (b) conductance for up- and down-spin electrons in a nanowire of constant radius $R = R_1 = R_2 = R_3$ as a function of R ; (c) conductance for up- and down-spin electrons in a segmented nanowire of $R_1 = R_3 = 15 \text{ \AA}$ and the length of the middle segment $L_2 = 20 \text{ \AA}$ as a function of R_2 .

^{a)}Electronic mail: zhur@unlserve.unl.edu

^{b)}Permanent address: Department of Physics, M. V. Lomonosov Moscow State University, 119899 Moscow, Russia.

segment, where index j denotes the segment number. The exchange splitting of the bands in a ferromagnet is introduced using the Stoner model via an effective exchange field, h_{ex} , so that the spin-dependent potential within segment j is $V_{\sigma j} = V_j + \sigma h_{ex}$, where σ is the spin index. For an infinite wire of potential $V_{\sigma j}$ the Fermi wave vector, $k_F^{\sigma j} = \sqrt{2m(E_F - V_{\sigma j})/\hbar^2}$, depends on the radius of the nanowire, R_j , through the Fermi energy E_F which is determined by the number of valence electrons in a metal. In segmented nanowires we fix the Fermi energy throughout the structure and renormalize potentials $V_{\sigma j}$ (and consequently the Fermi momenta) to provide charge neutrality on average within each segment. We assume that there is no variation in the exchange energy with the radius of the nanowire.

We analyze the electrical conductance using a linear response theory. The central quantity to be calculated within this approach is the one-electron Green's function. Following the method developed in Ref. 12, we obtain the Green's function $G(r, r', z, z', \theta, \theta')$ by taking into account cylindrical symmetry of the problem. For a given segment j the solution can be expanded in terms of radial and angular eigenfunctions:

$$G(r, r', z, z', \theta, \theta') = \sum_{lmn} \frac{e^{i(\theta - \theta')}}{2\pi} \left\{ \frac{\phi_{lm}(r) \phi_{lm}(r') e^{ik_{lm}^{\sigma j} |z - z'|}}{2ik_{lm}^{\sigma j}} \times \delta_{mn} + A_{lmn} \phi_{lm}(r) \phi_{lm}(r') e^{-ik_{lm}^{\sigma j} z} e^{-ik_{lm}^{\sigma j} z'} \right\}, \quad (1)$$

where $k_{lm}^{\sigma j} = \sqrt{(k_F^{\sigma j})^2 - (\nu_{lm}/R_j)^2}$ is the longitudinal component of the wave vector at the Fermi energy. Radial functions $\phi_{lm}(r)$ are given by

$$\phi_{lm}(r) = \sqrt{2} J_l \left(\frac{\nu_{lm}}{R_j} r \right) / R_j J_{l+1}(\nu_{lm}), \quad (2)$$

where ν_{lm} is the m th node of the Bessel function $J_l(x)$. The coefficients A_{lmn} are calculated from the continuity condition of the Green's function and its derivatives at the interfaces. Mathematically the problem is reduced to the inversion of infinite rank matrices which can be performed using an appropriate truncation procedure.¹³ A similar problem was encountered when considering the conductance of 2D and 3D nanowires of variable radius using the scattering matrix formalism.¹⁴

Using the Green's function (1) we calculate spin conductance Γ_σ at zero temperature from the Kubo formula. The result can be represented as follows:

$$\Gamma_\sigma = -\frac{2e^2}{h} \sum_{lmn} \left[\text{Im}(k_{lm}^{\sigma j}) \left(|A_{lmn}|^2 - \frac{\delta_{mn}}{4|k_{lm}^{\sigma j}|^2} \right) + \text{Re}(k_{lm}^{\sigma j}) \text{Im} \left(\frac{A_{lmn}}{(k_{lm}^{\sigma j})^*} \right) \right] \text{Im}(k_{lm}^{\sigma j}). \quad (3)$$

Note that due to the current continuity condition Γ_σ does not depend on the choice of segment j in which it is calculated.

Figure 1(b) shows the calculated spin-dependent conductance of a uniformly magnetized wire of constant radius $R = R_1 = R_2 = R_3$. In the calculations we used the commonly accepted values of the material parameters typical for Ni and

Co: $E_F = 3.5$ eV, $h_{ex} = 1$ eV.¹⁵ As is seen from Fig. 1(b), the conductance is different for up- and down-spin electrons and changes in discrete steps of e^2/h with the increasing radius of the nanowire. At small values of R the down-spin channel is closed, and the conductance is equal to the spin conductance quantum e^2/h . The closure of the spin channel occurs at the critical radius R_0 given by the following expression:

$$R_0^2 = \frac{2\sqrt{mh_{ex}}}{\pi^2 \hbar n}, \quad (4)$$

where n is the total number of valence electrons per unit volume. In our case $R_0 \approx 1.5$ Å, so that the diameter of the nanowire is of the order of the lattice parameter in the bulk ferromagnet. The up-spin channel is never closed due to the charge neutrality condition imposed on the system.

In the case of a segmented nanowire with radius $R_2 < R_1 = R_3$ [Fig. 1(a)], the conductance displays irregular oscillations with increasing R_2 [see Fig. 1(c)]. These oscillations are the consequence of scattering at the interfaces between the segments. Abrupt changes in the radius of the segmented wire violate the adiabatic principle⁶ smearing out the conductance steps. These fluctuations do not, however, prevent the closure of the down-spin channel at $R_2 = R_0$, similar to the case of a wire of constant radius. At $R_2 < R_0$ only the up-spin channel is open, and the electric current in the nanowire is 100% spin-polarized. We note that the vanishing up-spin conductance seen in Fig. 1(c) at small values of R_2 is the result of the potential well created within the constriction region. The charge neutrality condition requires the depth of the potential well being inversely proportional to R_2^2 which leads to a strong reflection of incident electronic waves at small R_2 .

The possibility to achieve a fully spin-polarized conductance in the regime when only one spin-channel is open leads to another phenomenon that might occur in atomic-size contacts. If there is a nonmagnetic region within the constriction that separates two ferromagnetic electrodes, as is shown in Fig. 2(a), electronic conduction can be blocked by the spin conservation rule. Indeed, if magnetizations of the two ferromagnets are antiparallel the spin channel that is open in the one ferromagnet is closed in the other ferromagnet and vice versa. This *spin blockade* effect makes the conductance between the antiparallel-aligned electrodes equal to zero. This is opposite to the case of the parallel-aligned electrodes for which a conduction channel is open for up-spin electrons and the conductance is not equal to zero. We see that the magnetoresistance of such an atomic-size constriction can be infinite.

We model this effect by considering a segmented nanowire in which ferromagnetic electrodes are separated by a thin nonmagnetic spacer layer which is placed within the constriction region and has the same radius as the radius of the inner part of the nanowire, i.e., R_2 [Fig. 2(a)]. The only role of the spacer is to decouple magnetic moments of the electrodes which allows one to magnetize the ferromagnets in opposite directions. In our calculations we assume that the spacer is metallic, although the spin blockade effect survives in the case of an insulating barrier as well.

Figure 2(b) shows the conductance for parallel and antiparallel magnetization of the ferromagnets in a nanowire of

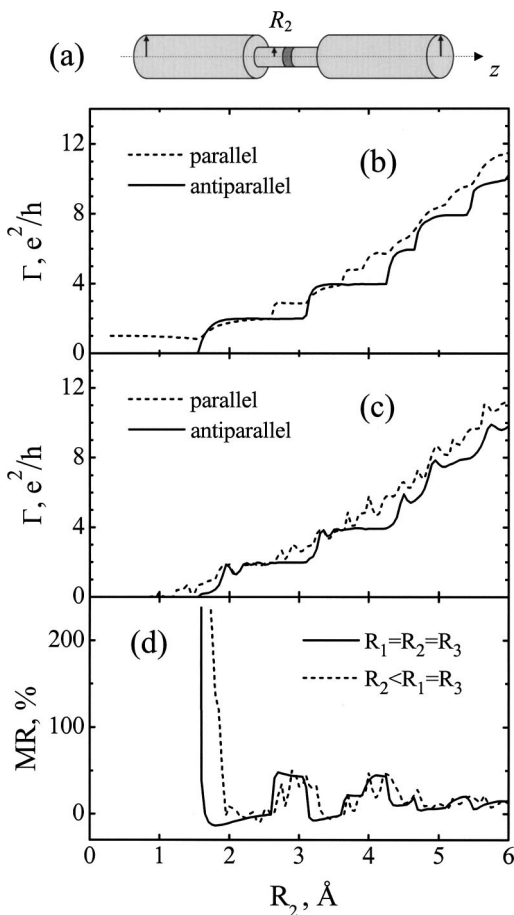


FIG. 2. (a) Segmented nanowire representing a nanoconstriction with a nonmagnetic region; (b) conductance for parallel and antiparallel alignment in a nanowire of constant radius $R=R_1=R_2=R_3$ as a function of R ; (c) conductance for parallel and antiparallel alignment in a segmented nanowire of radius $R_1=R_3=15$ Å and $L_2=20$ Å as a function of R_2 . The length of the middle segment is 2 Å; (d) magnetoresistance as a function of R_2 .

constant radius $R=R_1=R_2=R_3$ as a function of R . As is evident from this figure, at small R such that $R<R_0$ the spin blockade quenches the conductance of the antiparallel-aligned nanowire, whereas the conductance for the parallel-aligned nanowire remains nonzero, about e^2/h . This effect is also present in a segmented nanowire of radius $R_2<R_1=R_3$ [Fig. 2(c)]. When R_2 becomes smaller than the critical radius R_0 , the conductance for the antiparallel magnetization vanishes.¹⁶ Sizable fluctuations in the conductance seen in Fig. 2(c) are caused by scattering at the interfaces between the segments of different radius which irregularly changes the conductance, reflecting some specific interrelations between longitudinal momenta.

Figure 2(d) shows magnetoresistance (MR) defined by the standard ratio $MR=(\Gamma_P-\Gamma_{AP})/\Gamma_{AP}$, where Γ_P and Γ_{AP} are the conductance for the parallel and antiparallel magnetization of the electrodes. For the nanowire of variable radius the MR displays noisy features, but the overall dependence on R_2 is similar to that for the nanowire of constant radius. As is seen from Fig. 2(d), the MR increases at small radius of

the constriction. This is consistent with the experimental observations of MR in ballistic Ni break junctions,¹⁷ which were explained in terms of a constrained domain wall formed within the nanocontact.^{15,18,19} At $R_2<R_0$ the MR becomes infinitely large. In this regime the nanoconstriction works as a perfect spin valve that can be switched between conducting and nonconducting states. We note, however, that this mechanism cannot explain huge values of MR in electrodeposited nanocontacts²⁰ which were observed not only for atomic-size contacts but also for larger cross sections of the constrictions up to a few nm.²

In conclusion, we have shown that atomic-size constrictions can be used to obtain a fully spin-polarized current as well as a valve which can be switched between conducting and nonconducting states. The latter can be achieved due to the spin blockade effect which quenches the conductance of the antiparallel-aligned nanowire in the regime when only one spin channel is open in each electrode.

This work is supported by NSF (Grant Nos. DMR-0203359 and MRSEC: DMR-0213808), the Nebraska Research Initiative, and W. M. Keck Foundation. A.V.V. is grateful to J. Fourier University, Grenoble for hospitality and the Russian Fund for Basic Research for partial financial support.

¹B. J. van Wees, H. van Houten, C. W. J. Beenakker, J. G. Williams, L. P. Kouwenhoven, D. van der Marel, and C. T. Foxon, *Phys. Rev. Lett.* **60**, 848 (1988).

²J. I. Pascual, J. Méndez, J. Gómez-Herrero, A. M. Baró, N. García, and V. T. Binh, *Phys. Rev. Lett.* **71**, 1852 (1993).

³L. Olesen, E. Lægsgaard, I. Stensgaard, F. Besenbacher, J. Schiøtz, P. Stoltze, K. W. Jacobsen, and J. K. Nørskov, *Phys. Rev. Lett.* **72**, 2251 (1994).

⁴J. M. Krans, J. M. van Ruitenbeek, V. V. Fisun, I. K. Yanson, and L. J. de Jongh, *Nature (London)* **375**, 767 (1995).

⁵R. Landauer, *IBM J. Res. Dev.* **32**, 306 (1988).

⁶L. I. Glazman, G. B. Lesovik, D. E. Khmel'nitskii, and R. I. Shekhter, *JETP Lett.* **48**, 238 (1988).

⁷T. Ono, Y. Ooka, and H. Miyajima, *Appl. Phys. Lett.* **75**, 1622 (1999).

⁸F. Elhoussine, S. Mátéfi-Tempfli, A. Encinas, and L. Piraux, *Appl. Phys. Lett.* **81**, 1681 (2002).

⁹F. Komori and K. Nakatsuji, *Mater. Sci. Eng., B* **84**, 102 (2001).

¹⁰C.-S. Yang, J. Thiltges, B. Doudin, and M. Johnson, *J. Phys.: Condens. Matter* **14**, L765 (2002).

¹¹W. E. Pickett and J. S. Moodera, *Phys. Today* **5**, 39 (2001).

¹²M. Ye, Zhuravlev, H. O. Lutz, and A. V. Vedyayev, *Phys. Rev. B* **63**, 174409 (2001).

¹³A. Weissshaar, J. Lary, S. M. Goodnick, and V. K. Tripathi, *J. Appl. Phys.* **70**, 355 (1991); A. L. Sakhnovich, *J. Math. Anal. Appl.* **247**, 410 (2000).

¹⁴F. Kassubek, C. A. Stafford, and H. Grabert, *Phys. Rev. B* **59**, 7560 (1999).

¹⁵H. Imamura, N. Kobayashi, S. Takahashi, and S. Maekawa, *Phys. Rev. Lett.* **84**, 1003 (2000).

¹⁶Note that this conclusion is valid provided that no spin-flip scattering due to, e.g., spin-orbit interaction is taken into account. The spin-orbit interaction, H_{SO} , makes Γ_{AP} nonzero for $R<R_0$. In this case the MR ratio, $(\Gamma_P-\Gamma_{AP})/\Gamma_{AP}$, can be estimated as $(E_F/H_{SO})^2$. Assuming that $H_{SO}\sim 0.1$ eV, we find $MR\sim 10^3$.

¹⁷N. García, M. Muñoz, and Y.-W. Zhao, *Phys. Rev. Lett.* **82**, 2923 (1999).

¹⁸A. K. Zvezdin and A. F. Popkov, *JETP Lett.* **71**, 209 (2000).

¹⁹L. R. Tagirov, B. P. Vodopyanov, and K. B. Efetov, *Phys. Rev. B* **65**, 214419 (2002).

²⁰H. D. Chopra and S. Z. Hua, *Phys. Rev. B* **66**, 020403 (2002).