## University of Nebraska - Lincoln Digital Commons@University of Nebraska - Lincoln

**Christian Binek Publications** 

Research Papers in Physics and Astronomy

8-14-2000

# Crossover from transient spin structures of the field-induced Griffiths phase of FeBr2

Christian Binek University of Nebraska-Lincoln, cbinek2@unl.edu

Follow this and additional works at: http://digitalcommons.unl.edu/physicsbinek



Part of the Physics Commons

Binek, Christian, "Crossover from transient spin structures of the field-induced Griffiths phase of FeBr2" (2000). Christian Binek Publications. Paper 48.

http://digitalcommons.unl.edu/physicsbinek/48

This Article is brought to you for free and open access by the Research Papers in Physics and Astronomy at Digital Commons@University of Nebraska -Lincoln. It has been accepted for inclusion in Christian Binek Publications by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.





## Crossover from transient spin structures to the field-induced Griffiths phase of FeBr<sub>2</sub>

Ch. Binek a,\*, M.M.P. de Azevedo a, W. Kleemann a, D. Bertrand b

<sup>a</sup> Angewandte Physik, Gerhard-Mercator-Universität Duisburg, 47048 Duisburg, Germany <sup>b</sup> Laboratoire de Physique des Solides <sup>1</sup>, INSA, F-31077 Toulouse Cedex, France

#### Abstract

In the presence of an applied axial magnetic field  $H_a$  the uniaxial antiferromagnets  $\operatorname{FeCl}_2$  and  $\operatorname{FeBr}_2$  show fluctuating domain-like antiferromagnetic correlations above the phase boundary  $T_c(H_a)$ . They are detected by SQUID measurements of the low frequency out-of-phase susceptibility  $\chi''$  and indicate a field-induced Griffiths phase at temperatures  $T_c(H_a) < T < T_N$ . In contrast to  $\operatorname{FeCl}_2$ , important additional frustration-induced intraplanar non-critical contributions to  $\chi''$  vs. T are found in  $\operatorname{FeBr}_2$ . For external fields above the  $T_c(H_a)$  line,  $H_a > 2.6$  MA/m, they are shown to superimpose linearly on the Griffiths contributions. These dominate at  $H_a = 2.67$  MA/m and are unequivocally modeled within the Landau theory of fluctuations near phase transitions by introducing a Lorentzian  $T_c$  distribution.

The Griffiths phase conjecture was theoretically introduced for diluted Ising-ferromagnets [1]. It is based on the idea of 'local phase transitions' in a diluted system due to the finite probability of arbitrarily large pure and differently diluted clusters. However, despite a possible dynamical signature of the Griffiths phase in inelastic neutron scattering data of KMn<sub>0.3</sub>Ni<sub>0.7</sub>F<sub>3</sub> [2] and recent Monte Carlo simulations [3], its clear experimental verification is still lacking. A more favorable situation is encountered in an analogous experimental realisation of a Griffiths phaselike phenomenon. It was recently detected on the uniaxial antiferromagnet FeCl2 in an applied axial magnetic field [4]. Domain-like antiferromagnetic correlations are created by fluctuating demagnetizing fields and, hence, transition temperatures due to the unambiguous relationship  $T_c =$  $T_{\rm c}(H_{\rm a})$ . Within the temperature regime  $T_{\rm c}(H_{\rm a}) < T <$  $T_{\rm c}(H_{\rm a}=0)\equiv T_{\rm N}$  the quasicritical order parameter fluctuations give rise to anomalous contributions to the magnetic loss function  $\chi''$  at low frequencies 0.1 < f < 10 Hz. Regions with local antiferromagnetic correlations are analogous to the non-diluted clusters, which are responsible for the Griffiths phase in diluted ferromagnets. As shown in Ref. [4], these antiferromagnetic fluctuations are suitably described within the framework of the Landau theory of fluctuations near second-order phase transitions [5]. In addition, the concept of local transition temperatures, which

is accounted for by a Lorentzian  $T_c$  distribution function, allows one to model the temperature dependence of the

out-of phase susceptibility  $\chi''$  within and above the Grif-

fiths regime  $T_c(H_a) < T < T_N$ . An approximate analytic

expression is given by [6]

 $\chi'' \propto \frac{\epsilon}{\pi V D q^2 (\epsilon^2 + t_c^2)}$ 

with  $t_{\rm c}=T-T_{\rm c},\ t_{\rm N}=T-T_{\rm N},\ A_0$  and D the Landau expansion coefficients of the quadratic and gradient term of the Gibbs free energy density,  $\epsilon=b/T$  the temperature-dependent width of the  $T_{\rm c}$  distribution, V the sample volume and q the wave-vector of the order parameter fluctuations. While the field-induced Griffiths phase is driven by inhomogeneous demagnetizing fields, FeBr<sub>2</sub> shows an important additional intrinsic loss mechanism. As outlined in Ref. [7], non-critical fluctuations are attributed to intraplanar frustration. It gives rise to transient non-uniform spin structures, which carry excess magnetisation. Their location in the  $H_{\rm a}-T$  phase diagram is shown in Fig. 1. Below the  $T_{\rm c}(H_{\rm a})$  line they appear only on the

 $<sup>\</sup>times \begin{cases} T_{\rm N} - T_{\rm c} + \frac{t_{\rm c} \left(t_{\rm c}^2 - t_{\rm N}^2\right)}{\epsilon^2 + t_{\rm c}^2} \\ \\ - \frac{A_0}{Dq^2 T} \left(\frac{1}{2} t_{\rm c}^2 + t_{\rm N}^2\right) & \text{if } T \leq T_{\rm N}, \end{cases}$   $T_{\rm N} - T_{\rm c} + \left(\frac{t_{\rm c}}{\epsilon^2 + t_{\rm c}^2} - \frac{A_0}{2Dq^2 T}\right) \\ \times \left(t_{\rm c}^2 - t_{\rm N}^2\right) & \text{if } T > T_{\rm N}, \end{cases}$ 

<sup>\*</sup> Corresponding author. Fax: +49-203-379 3163; email: binek@kleemann.uni-dujsburg.de.

<sup>&</sup>lt;sup>1</sup> Laboratoire associé au CNRS (URA 74).

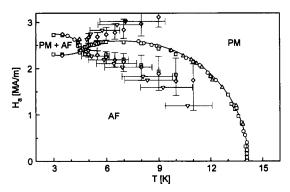


Fig. 1.  $H_a-T$  phase diagram (data points with eye-guiding lines) and regimes of strong non-critical fluctuations (data points with bars indicating full widths at 0.6 maximum) obtained from M vs.  $T(\bigcirc)$  and  $H_a(\bigcirc)$ ,  $\chi'$  vs.  $T(\triangle)$ ,  $\chi''$  vs.  $T(\nabla)$  and  $H_a(\bigcirc)$  [7].

sublattice with magnetisation antiparallel to  $H_a$ , whereas above  $T_c(H_a)$  they are assumed to spread over all Fe<sup>2+</sup> layers by symmetry.

Fig. 2a (circles) shows  $\chi''$  vs. T measured by SQUID magnetometry at  $H_a = 3.02$  MA/m and constant frequency f = 5 Hz obtained for a [0001] oriented Bridgmangrown single crystal with  $\sim 0.2$  mm thickness. The noncritical fluctuations above the phase transition are responsible for the maximum of  $\chi''$  vs. T at T = 7.1 K (solid symbol in Fig. 1). With increasing temperature,  $\chi''$  decreases due to the thermal decay of spin clusters. However, contributions from the field-induced Griffiths phase cause a delay of the thermal decay in the vicinity of the 'Griffiths-temperature'  $T_N = 14.1$  K. With decreasing external

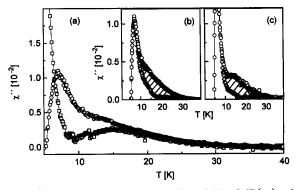


Fig. 2. (a)  $\chi''$  vs. T measured at f=5 Hz and  $H_a=2.67$  ( $\square$ ) and  $H_a=3.02$  MA/m ( $\bigcirc$ ). The solid line is a least-squares fit to the theory (see text). The insets show  $\chi''$  vs. T for  $H_a=3.02$  (b) and  $H_a=2.86$  MA/m (c) before ( $\bigcirc$ ) and after ( $\diamondsuit$ ) subtracting the Griffiths-type contribution, see text. The hatched areas indicate the excess in  $\chi''$  due to the Griffiths contributions.

field, the frustration-induced fluctuations shift to lower temperatures and thus gradually separate from the Griffiths-like contributions appearing at higher T. At  $H_{\rm a}=2.67$  MA/m this is indicated by a clear minimum close to zero at T=8.5 K (Fig. 2a, squares).

The solid line in Fig. 2a shows the least-squares fit of the above function to these data.  $T_N$ ,  $T_c$ ,  $A_0/Dq^2$ , b and an additional proportionality constant are involved as fit parameters. The result from the fitting procedure,  $T_N =$ 13.97 K, comes close to the experimental value,  $T_N = 14.1$ K, which was obtained by the temperature dependence of the low-field magnetization. This demonstrates that the concept of the field-induced Griffiths phase can be extended from the prototype FeCl<sub>2</sub> [4] to the frustrated Ising system FeBr2. Under the assumption that the field-dependent change of  $\chi''$  vs. T is mainly caused by the frustration-induced fluctuations, we are able to separate these and the virtually constant Griffiths contributions from each other. As a result, Figs. 2b and c show  $\chi''$  vs. T for  $H_a = 3.02$  and 2.86 MA/m, respectively, before and after subtracting the Griffiths-type contribution. This is taken from the fit of the data at  $H_a = 2.67$  MA/m (Fig. 2a) and represented by the hatched areas in Figs. 2b and c. As expected, the frustration-induced fluctuations increase with increasing field from  $H_a = 2.86$  to 3.02 MA/m. This is consistent with the phase diagram as discussed in Ref. [7]. It shows that in contrast to the Griffiths contributions, the frustration-induced fluctuations develop their main intensity far from the phase transition line. This is observed above and also below [7] the  $T_c(H_a)$  line. This remarkable property and the interplay of the frustration-induced and three-dimensional critical fluctuations are still under investigation.

Acknowledgement: Work supported by DFG through SFB 166.

### References

- [1] R.B. Griffiths, Phys. Rev. Lett. 23 (1969) 17.
- [2] R.G. Lloyd and P.W. Mitchell, J. Phys. C 1 (1989) 5013.
- [3] V.B. Andreichenko, W. Selke and A.L. Talapov, J. Phys. A 25 (1992) L283.
- [4] Ch. Binek and W. Kleemann, Phys. Rev. Lett. 72 (1994) 1287.
- [5] A.Z. Patashinskii and V.L. Pokrovskii, Fluctuation Theory of Phase Transition (Pergamon, Oxford, 1979).
- [6] Ch. Binek and W. Kleemann, Proc. 19th Meeting Middle Europ. Coop. Statis. Physics, Smolenice, 1994, Acta Phys. Slovaca 44 (1994) 435.
- [7] M.M.P. de Azevedo, Ch. Binek, J. Kushauer, W. Kleemann and D. Bertrand, J. Magn. Magn. Mater. 140-144 (1995) 1557 (these Proceedings).