

University of Nebraska - Lincoln

DigitalCommons@University of Nebraska - Lincoln

Si-Hwang Liou Publications

Research Papers in Physics and Astronomy

May 2000

FePt:SiO₂ granular thin film for high density magnetic recording

C.P. Luo

University of Nebraska - Lincoln

Sy_Hwang Liou

University of Nebraska-Lincoln, sliou@unl.edu

David J. Sellmyer

University of Nebraska-Lincoln, dsellmyer@unl.edu

Follow this and additional works at: <https://digitalcommons.unl.edu/physicsliou>



Part of the [Physics Commons](#)

Luo, C.P.; Liou, Sy_Hwang; and Sellmyer, David J., "FePt:SiO₂ granular thin film for high density magnetic recording" (2000). *Si-Hwang Liou Publications*. 71.

<https://digitalcommons.unl.edu/physicsliou/71>

This Article is brought to you for free and open access by the Research Papers in Physics and Astronomy at DigitalCommons@University of Nebraska - Lincoln. It has been accepted for inclusion in Si-Hwang Liou Publications by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.

FePt:SiO₂ granular thin film for high density magnetic recording

C. P. Luo,^{a)} S. H. Liou, and D. J. Sellmyer

Behlen Laboratory of Physics and Center for Materials Research and Analysis, University of Nebraska, Lincoln, Nebraska 68588-0111

Nanocomposite FePt:SiO₂ thin films consisting of high anisotropy FePt particles embedded in a SiO₂ matrix have been successfully fabricated by annealing the as-deposited FePt/SiO₂ multilayers. By adjusting the annealing temperatures and compositions, films were obtained with coercivity of 3.8 kOe and grain size of 10 nm, which are suitable for high-density magnetic recording. Magnetic activation volumes were measured and thermal stability is discussed. © 2000 American Institute of Physics. [S0021-8979(00)46608-9]

I. INTRODUCTION

The growth and microstructure of FePt thin films with the $L1_0$ ordered structure have received extensive attention due to their high anisotropy energy¹ and potential applications as high density longitudinal recording media,^{2,3} magneto-optical recording media,⁴ and high energy magnets.⁵ It is expected that future 100 Gb/in.² recording media require higher anisotropy energy than current conventional Co alloys media because such high-density magnetic recording requires media with grain sizes of 10 nm or less, which is approaching the superparamagnetic limit of current media. Therefore, higher anisotropy energy is needed to retain thermal stability.^{6,7} It also requires that the magnetic particles must be isolated to reduce intergrain interactions, which leads to lower media noise. In this research we studied the potential of FePt:SiO₂ granular thin films, which consist of high anisotropy FePt particles embedded in a SiO₂ matrix, for high-density media.

II. EXPERIMENT

FePt/SiO₂ multilayers were deposited on 7059 glass substrates by dc- and rf-magnetron sputtering. The base pressure of the deposition chamber was 2×10^{-7} Torr and high pure Ar was used for deposition at a pressure of 5 mTorr. The compositions of the films were adjusted by changing the FePt- and SiO₂-layer thickness. The as-deposited films were annealed in vacuum for 30 min in a temperature range from 500 to 650 °C. The structures of the films were investigated by x-ray diffraction (XRD) with Cu $K\alpha$ radiation. Magnetic properties were measured with a superconducting quantum interference device (SQUID) and an alternating gradient field magnetometer (AGFM). Domain pictures were taken by a magnetic force microscope (MFM).

III. RESULTS AND DISCUSSION

As shown in Fig. 1(a), the as-deposited multilayers have a disordered face-centered-cubic (fcc) structure, which is magnetically soft with coercivity less than 100 Oe. When annealed in vacuum at temperatures of 500 °C and above, FePt films undergo a phase transition from the disordered fcc phase to the ordered face-centered-tetragonal (fct) phase

($L1_0$).² A highly ordered fct structure, characterized by the (001) and (002) superlattice peaks, was obtained after annealing at 650 °C for 30 min, as shown in Fig. 1(b). The long-range order parameter,⁸ which quantifies the order-disorder transition, is determined by the integral intensity of the superlattice peaks. The ordered fct phase is magnetically hard, as shown by the hysteresis loop in Fig. 2. Very similar loops were measured with applied field in the film plane and perpendicular to the film plane. A large coercivity of 8 kOe was obtained. The long-range order parameter, grain size, and coercivity of the films are sensitive to the annealing temperatures, as discussed elsewhere.⁹

High-density recording requires media with a coercivity of 3–4 kOe and grain size of 10 nm or less. We can adjust the coercivities and grain size of FePt:SiO₂ nanocomposite films by controlling the film composition, annealing temperature, and time. Under certain annealing temperatures and times, coercivities and grain sizes decrease as SiO₂ concentration increases, as shown in Fig. 3(a). The perpendicular grain sizes were estimated by the Scherrer formula¹⁰ from the (111) peak width of XRD scans. When annealed at 600 °C for 30 min, the sample with 24 vol % of SiO₂ shows a coercivity of 3.8 kOe and a grain size of 10 nm, which is suitable for high-density magnetic recording. Since the SiO₂ matrix hinders the growth of FePt particles, the grain size decreases to well below 10 nm as SiO₂ concentration increases to over 50 vol %. However, the coercivity also de-

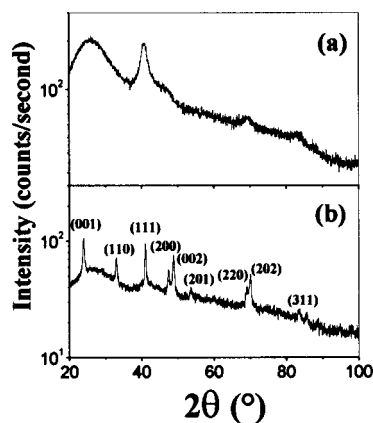


FIG. 1. XRD scans of (FePt38 Å/SiO₂12 Å)₁₀ thin film. (a) as-deposited; (b) annealed at 650 °C for 30 min.

^{a)}Electronic mail: cluo@unlserve.unl.edu

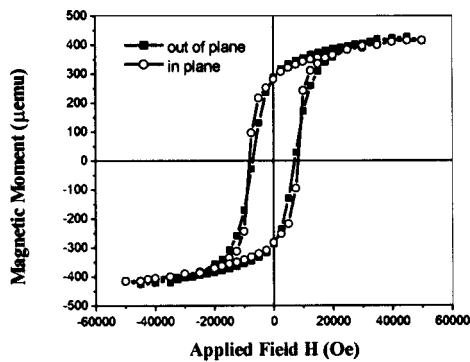


FIG. 2. Hysteresis loop of $(\text{FePt}38 \text{ \AA}/\text{SiO}_2 12 \text{ \AA})_{10}$ annealed at $650 \text{ }^\circ\text{C}$ for 30 min.

creases rapidly. The decrease of coercivity may be due to smaller grains and the incomplete transition from fcc to fct phase.

The M_r/M_s ratio also decreases as SiO_2 concentration increases, as shown in Fig. 3(b). The decrease of M_r/M_s ratio may be due to the reduced exchange interactions between grains. δM plots shown in Fig. 4 indicate that exchange coupling has been reduced as SiO_2 concentration increases. For films with SiO_2 more than 50 vol% only dipole interactions were observed. At the same time the M_r/M_s ratio decreases to near the value of 0.5 for noninteracting Stoner–Wohlfarth particles. This suggests that the high anisotropy FePt particles were randomly distributed and isolated by the SiO_2 matrix.

Figure 5 shows the domain pattern of the film with 24 vol% of SiO_2 . The domain pattern consists of segmented stripes with an average domain width of 60 nm.

As recording density approaches 100 Gb/in.^2 the bit size and grain size become smaller and smaller in order to retain a reasonable signal-to-noise ratio. As grain size approaches the superparamagnetic limit, thermal fluctuations become very important. Thermal stability is usually determined by the activation volume V^* , which can be determined by measuring the viscosity coefficient S and the irreversible susceptibility χ_{irr} :¹¹

$$V^* = k_B T \chi_{\text{irr}} / M_s S,$$

where S is measured by the time decay of magnetization:

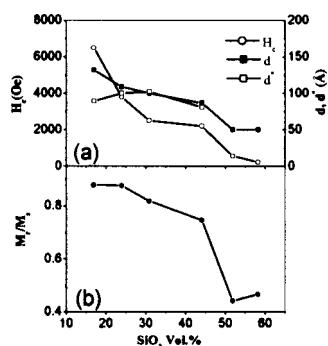


FIG. 3. The dependence of H_c , grain size d , magnetic grain size d^* , and M_r/M_s ratio on SiO_2 concentration.

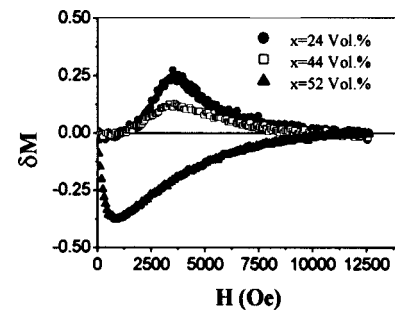


FIG. 4. δM plots of $(\text{FePt}38 \text{ \AA}/\text{SiO}_2 x \text{ \AA})_{10}$ annealed at $600 \text{ }^\circ\text{C}$ for 30 min.

$$M(H, t) = M_0 - S(H) \ln(t/t_0),$$

where M_0 and t_0 are constants independent of time. Figure 6 shows the linear dependence of magnetization on $\ln(t/t_0)$, which allows the determination of the magnetic viscosity coefficient S . The activation volume is on the order of $1 \times 10^{-18} \text{ cm}^3$, and does not change much with composition. The magnetic grain size d^* , defined as $(V^*)^{1/3}$, was found very close to the physical grain size d for most samples, as shown in Fig. 3(a). This, along with the δM results, suggests that the particles reverse as units which are only weakly exchange coupled. The $K_u V^*/k_B T$ value is about 850 (assuming $K_u = 3.5 \times 10^7 \text{ erg/cc}$ for the FePt phase¹²), much above the required value of 60 for thermally stable media.¹³

IV. SUMMARY

FePt: SiO_2 nanocomposite films were successfully synthesized with controlled grain sizes and magnetic properties by varying film compositions and annealing temperatures. These films consist of high anisotropy FePt particles isolated by a SiO_2 matrix. Films were obtained with desired magnetic properties ($H_c \sim 3.8 \text{ kOe}$) and grain size ($\sim 10 \text{ nm}$) which are suitable for high-density magnetic recording. Magnetic viscosity studies indicate that these films have excellent thermal stability. Altogether the results suggest that FePt: SiO_2 nanostructured films are promising candidates for future high-density recording media.

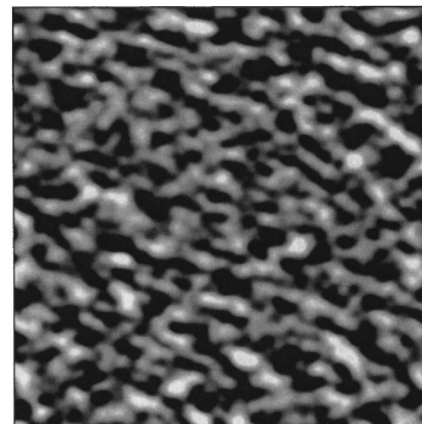


FIG. 5. MFM image of the FePt: SiO_2 nanocomposite film with 24 vol% of SiO_2 . The size of the image is $2 \text{ } \mu\text{m}$.

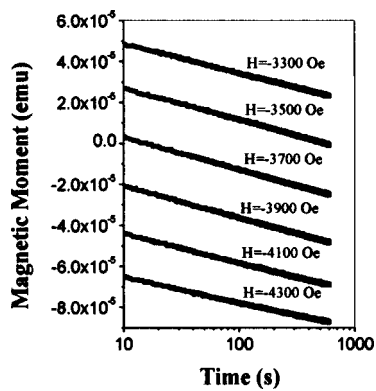


FIG. 6. The dependence of magnetization on $\ln t$.

ACKNOWLEDGMENTS

This research work is supported by the NSF under Grant No. DMR9623992, USDOE under Grant No. DE-FG-03-

98ER45703, Army Research Office under Grant No. DAAG55-98-1-0014, and CMRA.

- ¹B. Zhang and W. A. Soffa, *IEEE Trans. Magn.* **26**, 1388 (1990).
- ²C. P. Luo and D. J. Sellmyer, *IEEE Trans. Magn.* **31**, 2764 (1995).
- ³K. R. Coffey, M. A. Parker, and J. K. Howard, *IEEE Trans. Magn.* **31**, 2737 (1995).
- ⁴D. Treves, J. T. Jacobs, and E. Sawatsky, *J. Appl. Phys.* **46**, 2760 (1995).
- ⁵J. P. Liu, C. P. Luo, Y. Liu, and D. J. Sellmyer, *Appl. Phys. Lett.* **72**, 483 (1998).
- ⁶M. Yu, M. F. Doerner, and D. J. Sellmyer, *IEEE Trans. Magn.* **34**, 1534 (1998).
- ⁷D. N. Lambeth, E. M. T. Velu, G. H. Bellesis, L. L. Lee, and D. E. Laughlin, *J. Appl. Phys.* **79**, 4496 (1996).
- ⁸B. E. Warren, *X-Ray Diffraction* (Addison-Wesley, Reading, MA, 1969).
- ⁹C. P. Luo and D. J. Sellmyer, *Appl. Phys. Lett.* **75**, 3162 (1999).
- ¹⁰B. D. Cullity, *Elements of X-Ray Diffraction*, 2nd ed. (Addison-Wesley, Reading, MA, 1978), p. 102.
- ¹¹R. Street and J. C. Woolley, *Proc. Phys. Soc., London, Sect. A* **62**, 562 (1949).
- ¹²C. P. Luo, S. H. Liou, and D. J. Sellmyer (unpublished).
- ¹³S. H. Charap, P-L. Lu, and Y. He, *IEEE Trans. Magn.* **33**, 978 (1997).