

University of Nebraska - Lincoln

DigitalCommons@University of Nebraska - Lincoln

---

Construction Systems -- Dissertations & Theses

Construction Systems

---

9-2012

## AN ANALYSIS OF THE IMPACTS OF TEMPERATURE SEGREGATION ON HOT MIX ASPHALT

Thaddaeus A. Bode

University of Nebraska, stayfocused11@gmail.com

Follow this and additional works at: <https://digitalcommons.unl.edu/constructiondiss>



Part of the [Construction Engineering and Management Commons](#)

---

Bode, Thaddaeus A., "AN ANALYSIS OF THE IMPACTS OF TEMPERATURE SEGREGATION ON HOT MIX ASPHALT" (2012). *Construction Systems -- Dissertations & Theses*. 10.

<https://digitalcommons.unl.edu/constructiondiss/10>

This Article is brought to you for free and open access by the Construction Systems at DigitalCommons@University of Nebraska - Lincoln. It has been accepted for inclusion in Construction Systems -- Dissertations & Theses by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.

AN ANALYSIS OF THE IMPACTS OF TEMPERATURE  
SEGREGATION ON HOT MIX ASPHALT

by

Thaddaeus A. Bode

A THESIS

Presented to the Faculty of  
The Graduate College of the University of Nebraska

In Partial Fulfillment of Requirements  
For the Degree of Master of Science

Major: Construction

Under the Supervision of  
Professor Yong K. Cho

Lincoln, Nebraska

September, 2012

# AN ANALYSIS OF THE IMPACTS OF TEMPERATURE SEGREGATION ON HOT MIX

Thaddaeus Adam Bode, M.S.

University of Nebraska, 2012

Advisor: Yong K. Cho

This research was conducted to produce a more realistic picture of how variables are created and dealt with during hot mix asphalt (HMA) paving construction. Several paving projects across the State of Nebraska have been visited where sensing devices were used to test how the selected variables contribute to temperature differentials. These variables include density, moisture content within the asphalt, material surface temperature, internal temperature, wind speed, haul time, and equipment type. Areas of high temperature differentials are identified using an infrared camera whose usefulness was initially confirmed with a penetrating thermometer. A non-nuclear density device was also used to record how the lower temperature asphalt density compares to the more consistent high temperature area. After all variables were recorded, the locations were marked digitally via a handheld global positioning system (GPS) to aid in locating points of interest for future site inspections in order to verify research findings. In addition to the location-based database system using Google Earth, an extensive database query system was built which contains all data collected and analyzed during the period of this study. These research findings indicate that previously assumed variables thought to contribute to decreased density due to temperature differentials, such as haul time and air temperature, have little impact on overall pavement quality. Data analysis results also

indicate a significant correlation between material temperature differentials and premature distress one to three freeze thaw seasons after roadway construction.

## **ACKNOWLEDGMENTS**

I must give full credit of my accomplishments within to all those involved in helping me complete this research. Without the team of people who accompanied me in conducting field analysis and data analysis, Hyoseok Hwang, Diego Martinez, Koudous Kabassi, and Chao Wang, I could not have done it by myself. Above all I must thank Heejung Im, She was always up for a site visit, and more than helpful in conducting data analyses.

To the Staff at the Nebraska Department of Roads ( NDOR), I graciously thank you for funding the bulk of this research project. NDOR team members I would like to thank specifically include: Bob Rea, Laird Weishahn, Mick Syslo, Amy Starr, Jodi Gibson, and Matt Beran for their technical support and discussion.

In addition to the teams at the University and at NDOR, I have to thank the constructors who allowed me onto their jobsites, to get in their way, ask questions, and slow them down. In particular I would like to thank Jeff Boettcher of Constructors, for his help and understanding.

Last, but certainly not least, I would like to thank my advising professor, Dr. Yong K. Cho. Without his guidance and patience, my tenure as a graduate student would have been far less fulfilling and enjoyable.

## **DEDICATION**

I would like to dedicate this paper to my amazing family, Dad, Mom, Thomas, Christina, and Catherine. You have each impacted my life in countless and powerful ways. I am truly blessed to have grown up surrounded by each of your caring personalities, crazy quirks, supportive shoulders, and faithful teachings.

I cannot forget my beautiful bride to be Akanksha, who I would like to dedicate any future successes this graduate degree may bring me. Without her compassion, competitiveness, understanding, and playful interludes, I am certain my sanity and drive to succeed would not be intact. You are my all.

<b>Table of Contents</b>	<b>Page</b>
<b>Title Page</b> .....	i
<b>Abstract</b> .....	ii
<b>Acknowledgments</b> .....	iv
<b>Dedication</b> .....	v
<b>Chapter 1 Introduction</b> .....	1
<b>1.1 Research Objectives</b> .....	3
<b>1.2 Research Approach</b> .....	4
<b>1.3 Organization of this Report</b> .....	5
<b>1.4 Chapter 1 Summary</b> .....	6
<b>Chapter 2 Literature Review</b> .....	7
<b>2.1 Aggregate Segregation</b> .....	7
<b>2.2 Compaction</b> .....	9
<b>2.3 HMA Equipment</b> .....	12
<b>2.4 Thermography Driven HMA Inspection</b> .....	15
<b>2.5 Chapter 2 Summary</b> .....	16
<b>Chapter 3 Research Methodology</b> .....	18
<b>3.1 Sensing Devices</b> .....	18
<b>3.1.1 Infrared Camera</b> .....	18
<b>3.1.2 Non-Nuclear Density Gauge</b> .....	19
<b>3.1.3 Anemometer</b> .....	22
<b>3.2 Location Tracking</b> .....	22

<b>3.2.1 GPS</b> .....	23
<b>3. 2.2 Physical Markers</b> .....	23
<b>3.3 Other Collected Data</b> .....	24
<b>3.3.1 Observed Data</b> .....	24
<b>3.3.2 Received Data</b> .....	25
<b>3.4 Data Collection Process Overview</b> .....	26
<b>3.5 Chapter 3 Summary</b> .....	27
<b>Chapter 4 Data Analysis</b> .....	29
<b>4.1 Temperature Differential vs. Density</b> .....	29
<b>4.2 Other Variables Investigated</b> .....	32
<b>4.2.1 Air Temperature</b> .....	32
<b>4.2.2 Haul Time</b> .....	33
<b>4.2.3 Material Feeding Machines</b> .....	34
<b>4.2.4 Wind Speed</b> .....	35
<b>4.3 Chapter 4 Summary</b> .....	36
<b>Chapter 5 Inspection Analysis</b> .....	37
<b>5.1 Types of Premature Flaws</b> .....	38
<b>5.1.1 Transverse Crack</b> .....	40
<b>5.1.2 Multi-Crack Joint</b> .....	40
<b>5.1.3 Segregation</b> .....	41
<b>5.1.4 Surface Voids (Small Potholes)</b> .....	42
<b>5.2 Site Inspection Procedure and Data Collection</b> .....	43



<b>5.3 Site Inspection Analysis .....</b>	<b>44</b>
<b>5.3.1 Site Inspection Analysis by Distress Type .....</b>	<b>44</b>
<b>5.3.1.1 Transverse Crack Premature Distress.....</b>	<b>45</b>
<b>5.3.1.2 Reflective Crack Premature Distress.....</b>	<b>46</b>
<b>5.3.1.3 Surface Void Premature Distress.....</b>	<b>48</b>
<b>5.3.1.4 Multi-Crack Joint Premature Distress.....</b>	<b>50</b>
<b>5.3.1.5 Aggregate Segregation Flaws.....</b>	<b>51</b>
<b>5.3.2 Overall Inspection Data Analysis.....</b>	<b>53</b>
<b>5.4 Chapter 5 Summary .....</b>	<b>62</b>
<b>Chapter 6 Data Management .....</b>	<b>63</b>
<b>6.1. Google Earth based Visualization of Pavement Data.....</b>	<b>63</b>
<b>6.1.1 Google Earth File Type .....</b>	<b>66</b>
<b>6.2 Database in Microsoft Access™ .....</b>	<b>67</b>
<b>6.3 Chapter 6 Summary.....</b>	<b>69</b>
<b>Chapter 7 Conclusions and Recommendations.....</b>	<b>70</b>
<b>7.1 Conclusions .....</b>	<b>70</b>
<b>7.2 Recommendations .....</b>	<b>73</b>
<b>7.3 Future Studies.....</b>	<b>75</b>
<b>References .....</b>	<b>77</b>
<b>Appendix .....</b>	<b>80</b>

## List of Figures

Figure		Page
3.1	FlexCam infrared camera.....	19
3.2	Heat loss from truck and temperature differential from HMA.....	19
3.3	Taking PQI density readings onsite.....	21
3.4	Taking cores for PQI calibration.....	22
3.5	Handheld GPS device and jobsite location tags.....	23
3.6	Physical location markers.....	24
4.1	Theoretical relationship between temperature differential (TD) and density (DEN).....	29
4.2	Relationship for all collected data between temperature differential (TD) and density (DEN).....	30
4.3	A graphical representation of the relationship between individual temperature groups and TD and DEN.....	31
4.4	Relationship between ambient jobsite air temperature and temperature differentials.....	32
4.5	Relationship between haul time and temperature differentials.....	34
4.6	Direct dump between truck and paver.....	34
4.7	Pick-up machine with paver.....	34
4.8	Temperature differential based on feeding types.....	35
4.9	Relationship between wind speed and temperature differentials (TD).....	36
5.1	Instances of premature distress (PD).....	39

5.2	Observed transverse crack.....	40
5.3	Observed multi-crack joint.....	41
5.4	Observed material segregation.....	42
5.5	Observed surface void.....	43
5.6	Observed marker after one freeze thaw cycle.....	44
5.7	Relationship of TD and DEN among transverse cracks.....	45
5.8	Plan view of roadway exhibiting reflective cracks (Left) Observed reflective cracking (Right).....	46
5.9	Temperature differentials (TD) and density (DEN) relationship among reflective cracks.....	47
5.10	Relationship between Temperature Differentials (TD) and Density (DEN) excluding reflective cracks .....	48
5.11	Relationship between temperature differentials (TD) and Density (DEN) among surface voids.....	49
5.12	Correlation between temperature differentials (TD) and density (DEN) among multi-crack joints.....	51
5.13	Relationship between temperature differentials (TD) among aggregate segregation.....	52
5.14	Relationship between temperature differentials (TD) and density (DEN) among all observed premature distresses.....	54
5.15	Relationship between temperature differentials (TD) and premature distress, excluding small surface voids.....	55

5.16	Relationship between the correlation of TD and DEN for a given temperature range.....	57
5.17	Correlation between the percentage of premature distresses (PD) found within a specified temperature range when surface voids are included...	60
5.18	Correlation between the percentages of premature distresses (PD), excluding surface voids, found within a specified temperature range.....	61
6.1	Project specific Data Management System.....	63
6.2	Google Earth based database.....	65
6.3	Location specific data via Google Earth.....	65
6.4	Site Designed Database Form.....	68
6.5	Data Designed Database Form.....	68

## List of Tables

4.1	Shows the correlation between a given temperature group and the relationship between TD and DEN.....	30
5.1	Total premature distresses vs. good condition.....	38
5.2	Instances of premature distresses by type.....	39
5.3	Corresponding temperature differential (TD) and density (DEN) of all premature distresses.....	53
5.4	Relationship between $R^2$ and corresponding TD groups.....	56
5.5	Temperature differential range (TD) vs. premature distress (PD) type.....	59

## Chapter 1

### Introduction

Generally, hot-mix asphalt pavements are designed to last 15 or more years. However, many fail prematurely due to cracks, potholes, raveling and other problems, thus not meeting its original design expectations (Phillips, 2008). Approximately 90% of the highways and roads in the U.S. are paved by hot mix asphalt (HMA). In 1988, the Transportation Research Board (TRB) launched a \$150 million Strategic Highway Research Program to reduce premature failure of roads resulting from poor construction methods. In 1993, SuperPave<sup>®</sup> (SUPERior PERforming Asphalt PAVEMENTS) was developed through the TRB program as a set of optimized mix designs and analysis methods and standards. Even after adoption of the SuperPave<sup>®</sup> mixture, premature distress of hot-mix asphalt (HMA) pavement still persisted (Phillips et al. 2003). The expected life of a segregated pavement could be less than half of its expected 15 years. The various causes of these premature distresses are numerous and lead to the squandering of roadway funds. s

In a series of thermographic research studies performed by the University of Washington and Clemson University (Willoughby, 2003; Amirkhani, 2006), it was found that excessive temperature differentials, also known as temperature segregation, during pavement construction cause density differentials to develop. Temperature segregation within HMA construction is the occurrence of inconsistently cold material surrounded by material of a more consistent warmer temperature. These temperature

differentials lead to a lower durability of pavements than designed. The cause was attributed to the surface and boundary cooling of hot-mix asphalt during transportation from an asphalt plant to a construction site. During the transport of HMA several areas of the material are prone to rapid cooling. When the material is unloaded, it is often not remixed thoroughly and portions are therefore stiffer and more resistant to compaction. These areas of cooler material typically occur again and again in the repetitive process of HMA paving; this reoccurring problem is commonly termed 'cyclic segregation'. Cyclic segregation is simply a repetitive occurrence of low-density pavement areas within the HMA paving process.

Further study by the University of Washington has detailed that the cooler areas of hot-mix with a temperature differential greater than 25°F exhibited lower densities after compaction. It was also found that asphalt that is cooler than 175°F is relatively stiff, and resists compaction, which results in a lower density than hotter areas after compaction. The less dense material is therefore prone to premature distress (Willoughby, 2003).

In addition to temperature differential development during transportation, there are other suspected variables that contribute to premature distress. Coarse aggregate segregation is the first likely suspect leading to premature distress visible through temperature segregation. Aggregate segregation is routinely visible during paving as temperature segregation because coarse aggregate cools more rapidly than fine aggregate (Gilbert, 2005).

Course aggregate segregation is an imbalance in the gradation of pavement material that includes a disproportionate amount of coarse aggregate to fine aggregate (Williams, et al. 1996).

One of the major conclusions formulated by previous research projects was that some type of remixing must be performed immediately prior to the unloading of the mix. This remixing was found to be crucial in order to achieve a uniform temperature and thus compaction. The most common remixing method is the use of a material transfer vehicle (MTV). An MTV breaks up larger masses of cooler material and remixes it, resulting in a smooth mix and a consistent temperature profile (Willoughby, 2003; Gilbert, 2005). However, a careful and detailed cost-benefit analysis should be considered before involving the added cost of incorporating an MTV as a solution. There have been no proven results revealed thus far that all MTVs will eliminate temperature segregation to a desirable level. In fact, a 2005 Colorado Department of Transportation study found windrow elevators to be just as effective at preventing temperature segregation as material transfer vehicles (Gilbert, 2005). Due to the expensive of equipment cost, the Nebraska Department of Roads (NDOR) has not regulated the use of MTVs for paving construction. Problems leading to temperature segregation could occur with the HMA truck delivery process, dumping and rolling practices, and meteorological working conditions. With these possible problems in mind, this report presents how to utilize various sensor devices to identify or control the variables associated with HMA pavement quality during construction.



## **1.1 Research Objectives**

The primary objective of this study is to identify and measure variables which have a significant effect on HMA temperature segregation during roadway construction in the State of Nebraska using various portable non-destructive sensing devices. In addition, the long term impact of temperature segregation on overall pavement quality was a vital aspect of this research.

## **1.2 Research Approach**

In order to accomplish the goals that were set for this investigation, two phases were created for this study. Phase one included: (1) a literature review of available non-destructive sensory devices that could be used for monitoring quality control in the HMA construction process, and (2) an evaluation of the possible reasons for the occurrence of thermal differentials during HMA paving. Phase two included: (3) the selection and procurement of sensory devices to be used within the study, (4) the validation of the effectiveness of infrared thermography as a test modality for assessing thermal differentials in HMA, (5) the validation of the effectiveness of the other sensory devices as a test modality for assessing HMA qualities, and finally, (6) the development of a practical and economical method of preventing and managing HMA thermal differentials.

To accomplish the objectives listed above a very close collaboration with state and local constructors was crucial. Obtaining such a high level of cooperation was achieved relatively easily as the results of this study will ultimately help constructors mitigate temperature segregation in the HMA paving process. It is also expected that the research

previously performed by other states with suitable information brings significant benefits to this research. However, due to different environments, construction methods, and regulations in different states, the outcome of applying the technology may vary.

### **1.3 Organization of this Report**

The following report is comprised of seven chapters. Chapter 2 highlights the findings of previously published reports that deal specifically with thermography-driven HMA inspection, and the causes and effects of temperature segregation within the HMA construction process. Chapter 3 introduces and validates the sensor devices that were used throughout this investigation, in addition to the procedure used for data collection and position tracking. Chapter 4 shows the analysis of the collected field data including temperature differential vs. density relationships, and other variables. Chapter 5 introduces an audit of previous field research locations to determine what, if any, premature defects occurred at the specific locations where data had been collected previously. Chapter 6 briefly overviews the methods utilized as a part of this study to sort, analyze, and present data. Finally, Chapter 7 presents a summary of this investigation's findings and draw conclusions from those findings.

### **1.4 Chapter 1 Summary**

Even though significant advancements have been made in mix design and material research, long term quality issues persist. Past research has proven a difference in adjacent material temperature can cause density differentials to form. HMA temperature segregation is assuredly rooted in the typical construction process and

typically happens repeatedly in a cyclical fashion. Aggregate segregation can also be indicative of temperature segregation as coarse aggregate cools more quickly. A number of studies have concluded that specific truck types and remixing procedures must be implemented to adequately prevent temperature segregation; these equipment changes are expensive and not required in the State of Nebraska.

In an effort to identify and measure variables impacting temperature segregation initial data collection will take place at the time of paving, followed by annual inspections to gauge pavement health. From these sources of data, conclusions are drawn about when temperature segregation takes place and how to prevent it.

## **Chapter 2 Literature Review**

Temperature segregation has received varied amounts of attention in the last three decades as a construction related problem (Muench, 1998); however, the concept has only recently gained attention from researchers (Henault, 1999). There are conflicting views on the extent of thermal segregation and its impacts on the HMA construction process. To effectively understand the HMA temperature differential phenomenon being studied, it is important to first review the topics surrounding it. Below is a brief assessment of past and ongoing research dealing specifically with temperature differentials. Topics to be reviewed are:

- Aggregate Segregation
- Compaction
- HMA Equipment and Temperature Differentials
- Thermography Driven HMA Inspection

### **2.1 Aggregate Segregation**

“The non-uniform distribution of coarse and fine aggregate components within the asphalt mixture,” is commonly agreed upon as the accepted definition for aggregate segregation according to Willoughby et al. (2001) and AASHTO (1997). Aggregate segregation has long been suspected to cause a breakdown in the overall quality of HMA, and lead to premature pavement flaws. Though the effects of aggregate segregation were given attention by Bryant (Byant, 1967), it was not until two decades later that a sustained effort was made towards understanding the issues surrounding it (Brock, 1986).

Within HMA research the term “segregation” typically is taken to mean “coarse aggregate segregation”. Coarse aggregate segregation is an imbalance in the gradation of pavement material that includes a disproportionate amount of coarse to fine aggregate (Williams, et al. 1996). Coarse aggregate segregation often has a rough surface texture, low asphalt content, and lower density, all which lead to premature raveling and fatigue failure (Williams et al. 1996); (Amirkhanian & Putman, 2006). Coarse aggregate segregation is widely discussed along with temperature segregation because coarse aggregate cools quicker than fine aggregate (Gilbert, 2005), allowing for its identification through temperature segregation. In fact, Gilbert found mix designs with larger aggregate size to be three times more likely than fine aggregate segregation to have thermal segregation. This is contrary to the findings of Henault (1999) that cold spots and hot spots in the pavement do not typically possess varied relative gradations. Though fine aggregate segregation does occur, it is rare and is typically not included within HMA segregation investigations. The Colorado study (Gilbert, 2005) on thermal segregation suggests that switching to a finer gradation mix whenever possible should be done to reduce the introduction of temperature variances to the construction process.

It is important to note that the typical signs of coarse aggregate segregation do not always mean segregation is occurring. Inadequate compaction, poor mix design and material tearing can all generate similar symptoms that mirror coarse aggregate segregation (Hughes 1989). Particular attention should be paid to the misdiagnosis of poor compaction as aggregate segregation.

Segregation can occur within any part of the HMA process, from mix design to transportation, to compaction. Temperature differentials generated by the HMA construction process can often be controlled through proper planning and good construction practices. However, without an adequately designed mix, thermal segregation will not be fully prevented by these methods (Brock 1986). Brock's study points to this by finding a properly designed mix as having the greatest effect at mitigating aggregate segregation.

## **2.2 Compaction**

As many individuals are concerned with solving the mystery of exactly where temperature differentials are created within the HMA process, it is widely accepted that once HMA has cooled to specific temperatures, achieving required densities becomes difficult. Along with decreased pavement density, increases in air voids and permeability occur which, in turn, leads to a loss of pavement service life. Additionally, Henault's study in 1999 concluded that although temperature segregation may not appear to be an issue during initial lay down, it became more pronounced during material rolling (Henault, 1999). For those reasons significant weight is placed on the importance of proper rolling techniques.

Though the concept of studying temperature differentials is relatively new, the connection between decreased compaction temperatures has accompanied lower pavement densities for some time (Parker, 1959; Kennedy et al. 1984). Willoughby et al.

describes the importance material temperature plays in achieving overall density though the analysis of past researches' findings (Willoughby et al., 2001). Their findings showed that a sample compacted at 200 °F possessed double the amount of air voids contained in a sample compacted at 275 °F, with the air void discrepancy quadrupling when the sample was compacted at 150 °F. As the HMA cools, the asphalt binder eventually becomes stiff enough to effectively prevent any further reduction in air voids regardless of the applied compressive force. The temperature at which this occurs is commonly referred to as cessation temperature (Pavement Interactive, 2009). A recommended minimum compaction temperature for most HMA sites of 225°F was found and has been supported through later research most recently by Kennedy et al. (1984). In some literature it is reported to be about 175°F for dense-graded HMA (Scherocman, 1984b; Hughes, 1989). Below cessation temperature, rollers can still be operated on the mat to improve smoothness and surface texture but further compaction will generally not occur (Pavement Interactive, 2009).

The air voids and permeability that accompany decreased compaction have drastic effects. Brown (1984) points out that proper density must be achieved to obtain correct percent air voids and shear strength for the material. When increased permeability is present, the material loses its waterproofing ability and the asphalt binder will break down due to oxidation (Brown, 1984; Cooley & Brown, 2001). A strong relationship was found to exist between permeability and pavement air voids, leading to Cooley & Brown's (2001) recommendation that field permeability should be used as a quality control method for "selected HMA construction projects." Another possible method to

guard against permeability and its associated problems is to increase the lift thickness on HMA jobsites (Mallick, 1999).

In 1984 Scherocman and Marteson identified non-uniform material textures as often accompanying temperature segregation. This is an important point to recognize because varied HMA surface texture is typically found to cause poor compaction. The same authors reiterate that a decrease in achieved density translates to a decrease in useful life of pavement. They note density as being the standard indicator to how a pavement will perform. In fact, Gilbert (2005) found that temperature segregation does often lead to decreased densities, but also notes that 77% of the locations exhibiting signs of temperature segregation achieved adequate relative compaction within the Colorado study.

Although there are many causes of inadequate pavement compaction, which in turn leads to a multitude of negative pavement qualities, they can be readily mitigated through proper compaction techniques. Because many believe poor compaction densities are caused by decreased material temperatures, effectively pacing the correct number of rollers with the speed of the HMA paver is a key to decreasing the effects of temperature segregation (Muench, 1998).



### **2.3 HMA Equipment**

When investigating where and why temperature segregation occurs in the HMA construction process, the equipment and its operation is immediately considered. It is helpful to research past findings of equipment used within the State of Nebraska as well as others. Although it was requested that material transfer vehicles (MTVs) not be included in the State's final recommendation, they should be, at a minimum, briefly covered through this literary investigation.

Three types of HMA haul trucks are used within the State of Nebraska, 1) rear dump truck, 2) belly or bottom dump truck, and 3) live belly or bottom dump truck. On a whole, material transport trucks have been widely noted as the initial cause of temperature differentials (Read, 1996). In a HMA transport truck, the surface or peripheral material cools at a much faster rate than the material in the center of the load. These cooler areas of material are transferred into the paver and appear as temperature segregated pavement areas (Willoughby, 2003). Steps can be taken to mitigate the rate at which the outer crust cools (Read, 1996); however, the nature of the HMA construction process is such that, no matter what form of truck is used, a cyclical pattern of cold material will always be introduced onsite. Because of the thermal segregation inducing properties present in HMA trucks, it is important to select an appropriate haul truck.

The direct dump truck or rear dump truck has been the standard in HMA construction for several years. The rear dump truck transfers its load by directly dumping the material into the paver's hopper. Proper staging is crucial to the success of this

process because truck operators are constantly required to interface with the paver hopper to keep the construction process moving (Muench, 1998). This process is rapidly losing favor among state DOTs and constructors for its temperature differential inducing properties and small capacity. It was suggested to the Colorado Department of Roads that these trucks only be utilized when coupled with a remixing device (Gilbert, 2005).

Bottom dump trucks are quickly becoming the standard within the HMA construction process. Brock and Jakob (1997) have estimated a rise in construction productivity at 35-40% when using this type of truck. Bottom dump trucks are tractor-trailer style trucks that receive HMA through the top of the trailer and then distribute their load on the pavement ahead of the paver through a hatch in the bed of trailer. Some form of material transfer device is required as part of this process. Instances of thermal segregation created by the truck are minimal when compared to direct dump trucks; however, many contend that dumping material onto the colder existing pavement promotes temperature segregation as well (Brock & Jakob, 1997).

Live bottom haul trucks are not as common in Nebraska. They are similar to the bottom dump trucks mentioned above; however, instead of transferring their load to the pavement, they transfer their load directly into a transfer device through a conveyor at the bottom of the truck. Again this truck typically sees a decrease in thermal segregation when compared to the direct dump method (Brock & Jakob, 1997).

As noted earlier, aggregate segregation is thought to be very closely tied to thermal segregation. To decrease the likelihood of aggregate segregation during transport, Kennedy et al. (1987) and Brock (1988) suggest that trucks should be loaded in multiple dumps. By following a multiple load pattern there is a decreased chance for large aggregate to roll away to the sides of the truck and later causing gradation and temperature problems.

After the trucks have delivered the material to the site, it is up to transfer equipment to adequately remix and deposit the material into the paver's hopper. There are three primary forms of material transfer equipment: 1) material transfer vehicles (MTVs), 2) material transfer devices (MTDs) and 3) windrow elevators.

MTVs and MTDs are large external remixing devices. Rather than depositing the material directly to be fed straight into the paver, the trucks load a staging hopper within the MTV and MTD. The material is then thoroughly remixed by large augers. This ensures a consistent gradation of the HMA and reduces temperature segregation. The use of these vehicles also allows for a smoother work process because the paver never needs to stop to receive HMA as long as the MTD or MTV has material stockpiled (Brock & Jakob, 1997). Amirghanian & Putman (2006) notes that the Connecticut and Washington DOTs have seen marked decreases in the instances of thermal segregation on their jobsites since these types of equipment began to be used (Read, 1996; Henault, 1999).

Windrow elevators are not designed for material remixing. The elevator simply collects the deposited material from the existing pavement left behind by the haul trucks and transfers it to the paver hopper. The paddles used to scoop up the material and conveyor do, however, provide some level of remixing. Gilbert (2005) found windrow elevators to be just as effective at achieving proper levels of remixing as the more expensive MTVs and MTDs. Admirkhanian & Putman (2006) have also found the usefulness of windrow elevators not only for its remixing properties, but also because a decreased number of cold joints and less streaking occurs when they are employed.

Finally, the paver is examined. In particular, a HMA paver's hopper wings have been tied to the generation of thermal segregation. As material is dumped into the hopper, the unfolded wings collect material that sits static and does not enter the paver unless the wings are closed. As the wings are closed, the cooled material drops into the paver and is then introduced into the roadway pavement as a pronounced area of temperature segregation (Read, 1996; Henault, 1999; Amirkhanian, 2006). It is suggested from these past findings that hopper wings not be folded during the HMA paving process because it only promotes more extreme temperature differentials.

#### **2.4 Thermography Driven HMA Inspection:**

Infrared heat guns have been used in the paving industry for some time; however, the use of their next generation counterparts, infrared cameras, is somewhat new within the paving industry. These cameras are incredibly efficient at identifying and quantifying temperatures segregation. Gardiner et al. (1999) are credited as being among the first to

use infrared thermography to quantify temperature differential damage. Through their analysis they were able to identify areas of poor density and decreased asphalt content. Additionally, the Washington State and Clemson University studies on HMA segregation found the use of infrared cameras adequate tools for identifying thermal segregation (Willoughby & Kim, 2001; Amirkhanian & Putman, 2006). In Gilbert's (2005) report on thermal segregation, the cameras were again found to be useful in identifying and analyzing the extent of the thermal segregation.

## **2.5 Chapter 2 Summary**

Chapter 2 was broken down into general issues relating to pavement quality. Discussed first is the concept of aggregate segregation. Both fine and coarse aggregate segregation can cause temperature segregation, and both are represented by an imbalance of gradation within a mixture at a specific location typically caused during transportation.

The temperature at which material is compacted is also a key component during construction. Materials reaching its cessation temperature will no longer compact well, highlighting the problems associated temperature segregation. Poor compaction leads to problems with air voids, permeability, and overall pavement quality.

HMA equipment has been found to be a key contributor to variability in pavement quality. In Nebraska alone, three general truck types are used to transport HMA, each offering a different degree of mixing within the paving process. In addition to trucks, material transfer vehicles are often cited as an effective means of pavement remixing just prior to paving; MTVs, however, are not required on Nebraska State paving projects.

Roadway pavers are also thought to cause temperature segregation as material collects and cools on their hopper wings.

## **Chapter 3 Research Methodology**

During the paving seasons of 2007-2009, eighteen HMA paving sites were visited for data collection. The data contains variables which are considered to cause thermal differentials within HMA pavement. The targeted variables at each site include: location, time of day, air temperature, material temperature, ground temperature, humidity, wind speed, equipment type, mix type, and haul time. After compaction, thermographic imaging was used to locate points of interest not readily visible to inspectors. These locations were found after compaction so all possible causes of temperature segregation had a chance of occurring within the HMA paving process. At the individual locations, HMA density, moisture content, and surface temperature were collected.


### **3.1 Sensory Devices**

#### **3.1.1 Infrared Camera**

For verification of the use of thermal image data in HMA applications, temperature readings were initially taken on the surface of the HMA as well as internally using a temperature probe. The internal and external temperature readings were compared to those obtained by the infrared camera. This was also done to ensure the specific infrared camera used in this study provided accurate temperature measurements. The accuracy of infrared cameras in general has already been proven in HMA applications from the University of Washington study, noting that both temperature probes and infrared cameras are adequate tools for proving temperature differentials (Willoughby & Kim, 2001). Figure 3.1 shows a Flex Cam XR2, the infrared camera used in this research. Figure 3.2 shows infrared images taken from Nebraska paving sites.



**Figure 3.1 Infrared camera**

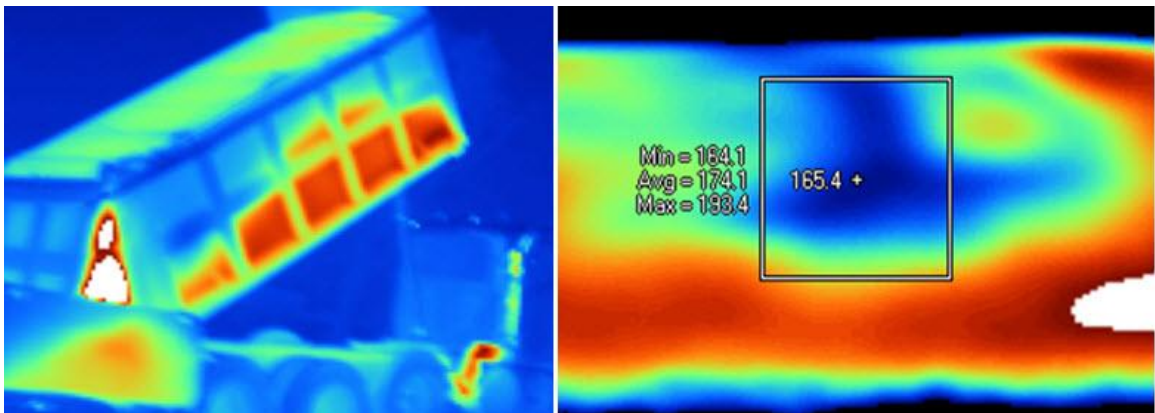

**Figure 3.2 Heat loss from a truck (left) and temperature differential from a HMA mat (right)**

**(temperatures shown in °F.)**

### **3.1.2 Non-Nuclear Density Gauge**

For the last several decades, density of freshly laid HMA material has been measured by constructors using nuclear density gauges. However, use of these devices requires the user to maintain an inordinate amount of records for the equipment. These requirements include calibration and recalibration records, certification records of the



operators, records of radiation badges, and periodic testing of the operator's badges for radiation exposure. In addition, there is a concern about possible accidents involving the gauges that might expose the radiation source to the operators or other bystanders (Schmitt, 2006; Sargand, 2005). Due to the issues and concerns associated with using nuclear gauges, this study adopted a non-nuclear density measurement method for paving quality control. After a thorough literature review, the Pavement Quality Indicator™ (PQI) 301 developed by TransTech Systems Inc. was selected (TransTech, 2008). The validation and effectiveness of the PQI has been tested in several states including: Texas (Sebesta et al. 2003), Kentucky (Allen et al. 2003), New York (Rondinaro, 2003), Utah (Romero, 2002), Ohio (Sargand, 2005), and Nebraska (Hilderbrand, 2008). Results of the investigations on the PQI have been primarily positive for quality control; especially following the release of TransTech's updated model, the PQI 301. The PQI uses electricity to measure the dielectric constant of the tested material using a toroidal electrical sensing field established by its sensing plate. The onboard electronics in the PQI then convert the field signals into material density. Once calibrated, direct density readings can be consistently obtained (TransTech, 2008). In this study, the PQI was calibrated by using one of two methods depending on site conditions. First, by comparing the PQI's density measurements with core samples (Bulk Specific Gravity) at each site as the manufacturer suggests. A Maximum Theoretical Density (MTD) value (RICE# or Maximum Specific Gravity) is required for the initial device calibration which can be provided from the asphalt mix designer. Then, the offset is adjusted after PQI calibration readings have been taken (Figure 3.3), and cores have been obtained from those same reading areas (Figure 3.4). Second, as an alternative method, a calibrated nuclear gauge

was used in place of lab tested core samples to generate the offset needed by the PQI. Using a nuclear gauge to calibrate the PQI has been validated by the Wisconsin DOT (Schmitt, 2006). Both methods were used as part of this study.



**Figure 3.3 Taking PQI density readings onsite**



**Figure 3.4 Taking cores for PQI calibration**

### **3.1.3 Anemometer**

In addition to site temperature and humidity, the wind speed was measured at each location investigated. This information was collected with the intention of correlating wind speed to how asphalt cools and develops temperature segregation.

### **3.2 Location Tracking**

To verify the hypotheses created by the analyzed data, it is necessary to compare it against real-world results. This research has involved the inspection of previously investigated sites to collect the visual images needed to analyze any premature distresses or changes in density after public use of the investigated roads. This activity required

information to be marked about the pavement where suspicious temperature and density differentials were observed.

### 3.2.1 Global Positioning System (GPS)

The approximate location for each mark was digitally recorded by a Garmin GPSmap 60CSx handheld GPS device. The unit's accuracy is noted as being capable of displaying readings within about 3 meters of the exact location (Garmin, 2007). By using GPS tags for each location, data was easily sorted during analysis and tied to digital maps which will be discussed later. It also allowed for the navigation back to selected locations, streamlining site re-visitation.

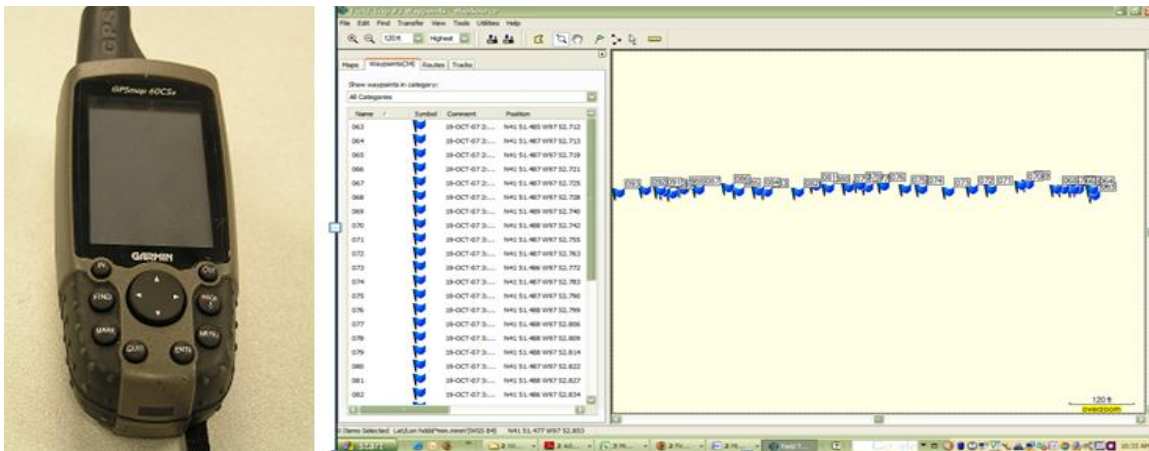


Figure 3.5 Handheld GPS device and jobsite location tags

### 3. 2.2 Physical Markers

In addition to digital markers, physical markers were used to mark the exact location of points of particular interest to the research team. These markers were specially designed pavement marking nails similar to surveyor markers shown in Figure 3.6. The

physical markers were driven into the shoulder pavement while still malleable and a distance directly across from the marker to the location was recorded.



**Figure 3.6 Physical location markers**

### **3.3 Other Collected Data**

#### **3.3.1 Observed Data**

While onsite, the research team collected a great deal of data from simple visual inspection. Though all the data was not used for analysis, its availability in comparisons may be crucial in later research. The observed data for this project includes: 1) Date, time, and location information, 2) Constructor and crew information, 3) Paving equipment, and 4) an overall jobsite description. The date, time, and location information can later be used in analyzing if temperature segregation occurs more at a certain time of the year or day. It was important to collect constructor and crew information to allow for the possibility of analyzing certain constructors or crews in regards to artisanship. Unfortunately, the number of crews performing HMA work did not allow for an adequate sampling to be used for analysis due to the nature of the fast paving process. Paving

equipment was noted during site visits so conclusions could be drawn about the relationships of certain equipment types involved in the HMA paving process.

### **3.3.2 Received Data**

Data received through outside sources on the day of the site visit, and after proved pivotal to the success of the project. Information that was provided includes: 1) the RICE value, or maximum theoretical density (MTD), 2) the mix type, and 3) haul times. The MTD was key to calibrating the device used to measure the achieved pavement density after compaction. Though current recommendations are that the PQI be used as a quality control device, pairing achieved density of the PQI to the MTD could later help establish the PQI as an accepted form of quality control or even assurance for the Nebraska Department of Roads.

The mix type of the pavement being investigated was also collected to be used in analyzing the susceptibility toward temperature segregation specific mix types may possess. Provided haul times and distances were used to draw correlations between temperature segregation and how far away asphalt plants are, or how different truck types are affected by varied haul times.

### 3.4 Data Collection Process Overview

In an effort to collect reliable and consistent data, the method used to collect information onsite was strictly followed. Described below is the work process used onsite:

- 1) Permission was obtained from the constructor and superintendant for the research crew to be onsite.
- 2) The MTD value was requested for gauge calibration, along with all other received data described in Section 3.3.2.
- 3) Six PQI readings were taken on HMA still over 120 ° F for calibration purposes and marked using construction crayons to outline the footprint of the gauge.
- 4) The six locations were marked so they could later be cored and tested to provide a gauge offset. The offset from cores would be applied to all data after collection. Or, a calibrated nuclear gauge was used to take readings immediately after the PQI. The nuclear readings were used to create a similar gauge offset just as the cores were used.
- 5) An infrared camera was used to search for and locate areas of temperature segregation. Infrared radiometric images were taken of the locations with the lens of camera facing the direction of paving. The camera was kept between 5 ft and 10 ft from each measurement location being investigated.
- 6) Density readings were taken using the non-nuclear density gauge at each location in a “single reading mode.”
- 7) Additionally, moisture values and current wind speed at each location were recorded.

- 8) After all characteristics of the location have been collected, the location was digitally marked using a handheld GPS unit.
- 9) If the location is of particular significance, a pavement marker was driven near the shoulder of the main road directly across from the area being measured.
- 10) At least of 30 locations were measured on each site whenever possible, however on some sites inadequate temperature segregation prevented this. From the 30 or more points collected, at least 60 density readings were generated. Each location generated two readings: one of the areas with a relative high temperature and the other with a relative low temperature.
- 11) After collecting specific material characteristics, the paving process including pavement equipment, and activity process was visually observed and noted.
- 12) After each site visit, collected data was added to a pool of previously collected data and analyses were updated.
- 13) Following one complete freeze thaw season of the pavement, the site was visually inspected for changes in pavement quality where data was collected.

### **3.5 Chapter 3 Summary**

Eighteen HMA sites were visited to collect a number of different types of data. Data collection always occurred after pavement compaction. The two primary sensory devices used for this project are an infrared camera and non-nuclear density measuring device. The infrared camera was used to identify locations of temperature segregation, and the density device was used to take readings at those locations. As a means of



tracking and revisiting past paving sites GPS coordinates were collected at each location, with physical markers being placed near areas of particular interest to the researchers. In addition to temperature and density readings, a host of other information was collected to be analyzed later.

## Chapter 4 Data Analysis

### 4.1 Temperature Differential vs. Density

Throughout this project, 304 locations have been evaluated with the primary intention of investigating the effect that temperature differentials (TD) have within the HMA paving process. As found from earlier studies, the areas possessing increased temperature differentials after final compaction are expected to yield lower densities (Figure 4.1).


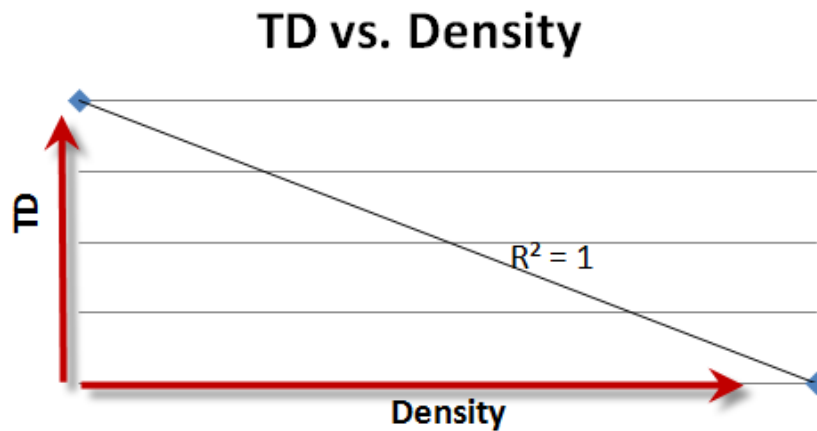


Figure 4.1 Theoretical relationship between temperature differential (TD) and pavement density

Including all 304 density readings and charting them against their corresponding temperature differentials provides a slight negative relationship. On the other hand, a more detailed look at the relationship between temperature differential (TD) after compaction and pavement density (DEN) to be insignificant (Figure 4.2).

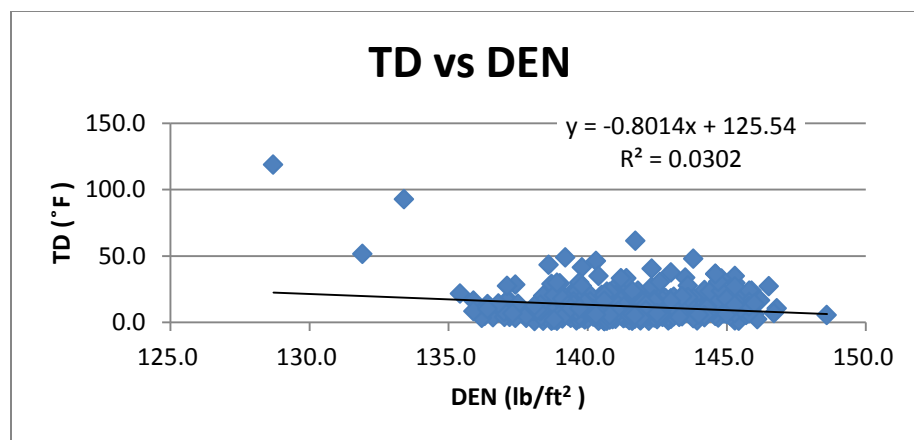


**Figure 4.2 Relationship for All Collected Data Between temperature differential (TD) and density (DEN)**

Although a direct relationship was not found between TD and Density, it is useful to investigate where temperature differentials in the HMA process begin to affect density. To do this, all locations were separated into sets of temperature groups. Each temperature group was then analyzed for its relation to temperature differentials and density; this is the correlation coefficient and shown as  $R^2$ . For example, if the temperature group “25°F and Up” was found to have an  $R^2$  (TD/DEN Relationship) of 0.44. It could be assumed that if a patch of material onsite were found to be 25 °F cooler than the surrounding material after final compaction, that the location would show a 44% correlation between temperature differentials and density. When developing these relationships for each temperature group, a trend line was created that showed how likely the relationship between TD and density is to hold true. These analyses are graphically represented below in Figure 4.3. It is easily seen that the severity of temperature differential in HMA significantly impacts the relationship between density; that is to say that as the temperature variation increases so too does the likelihood decreased densities will be observed.

**Table 4.1 Shows the correlation between a given temperature group and the relationship between TD and DEN**

Group Number	TD Data Group	TD/DEN Relationship	Data Points	Group Number	TD Data Group	TD/DEN Relationship	Data Points
1	Whole	0.0302	408	15	14°F & Up	0.1717	121
2	1°F & Up	0.0306	407	16	15°F & Up	0.1747	109
3	2°F & Up	0.0355	389	17	16°F & Up	0.1824	102
4	3°F & Up	0.0389	369	18	17°F & Up	0.2243	87
5	4°F & Up	0.0549	342	19	18°F & Up	0.2545	77
6	5°F & Up	0.0649	313	20	19°F & Up	0.2573	69
7	6°F & Up	0.0706	281	21	20°F & Up	0.2519	65
8	7°F & Up	0.0681	250	22	21°F & Up	0.3261	53
9	8°F & Up	0.0716	234	23	22°F & Up	0.3994	48
10	9°F & Up	0.0873	218	24	23°F & Up	0.4243	45
11	10°F & Up	0.1114	194	25	24°F & Up	0.4383	37
12	11°F & Up	0.1221	175	26	25°F & Up	0.4422	34
13	12°F & Up	0.1387	156	27	30°F & Up	0.6344	22
14	13°F & Up	0.146	139	28	40°F & Up	0.5829	10

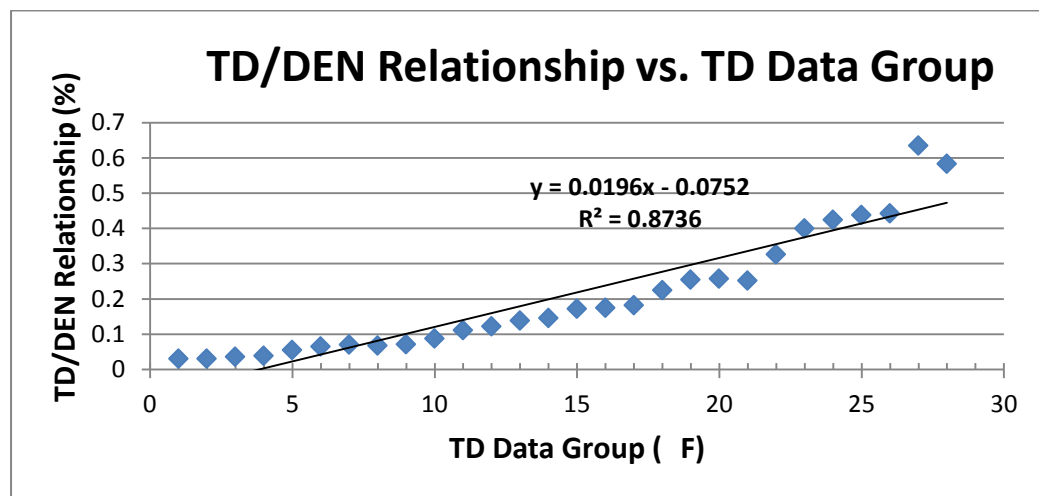

**Figure 4.3 A graphical representation of the relationship between individual temperature groups and TD and DEN**

## 4.2 Other Variables Investigated

### 4.2.1 Air Temperature

The 18 site visits carried out during this project occurred at varied times throughout the paving season across Nebraska. Sites were visited in early spring, the middle of summer, and far into the fall paving season. By visiting at varied times of the year, the effect outside air temperature has on the instances of temperature differentials (TD) was able to be studied. It is a common practice for mix types to compensate for cold weather. Essentially, boosting the mix temperature during manufacturing gives the lay down crew adequate time to use the material before it reaches its cessation point. It is still important however to investigate if these changes are sufficient at reducing temperature segregation. As can be seen in Figure 4.4 there was no statistically significant relationship ( $R^2 = 0.026$ ) between the outside air temperature (AirTemp) and the occurrence of temperature differentials (TD) during the two typical paving seasons in which this study took place.

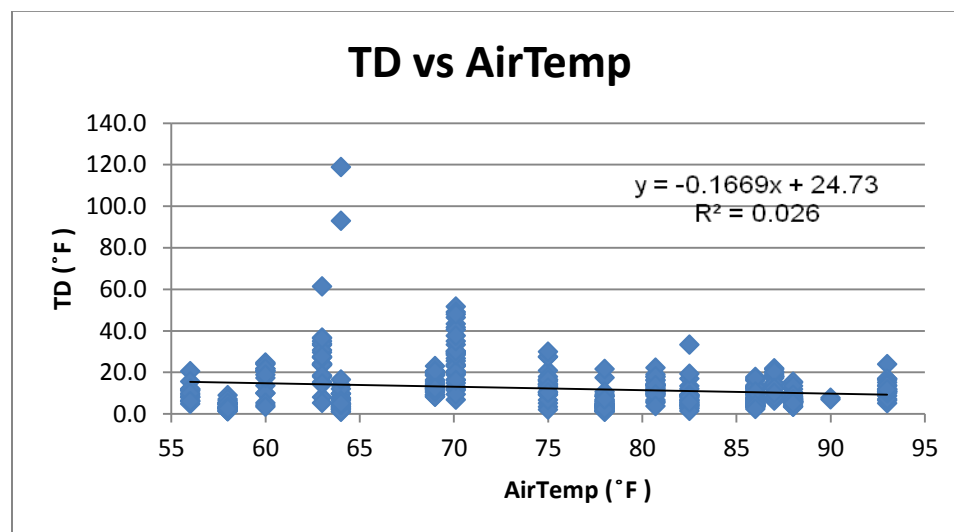


Figure 4.4 Relationship between ambient jobsite air temperature and temperature differential

#### 4.2.2 Haul Time

The effect of haul time in generating temperature segregations was investigated in this study. Increased effort was placed on visiting sites with longer haul distances. It was thought that increased haul times would translate to a thicker crust being generated during transportation. The thicker crust is generated because the periphery of the material cools faster in the truck bed than the interior material. Also, variations in temperature differentials are created during transport due to varied gradation and binder content in different mix types. This point was proven through the data analysis of Site 13. Site 13 had the longest material transport time at 90 minutes (Figure 4.5); however, it exhibited decreased signs of temperature segregation. This is likely due to the gap graded crumb rubber modified binder used in the mix. These rubber modified mixes are manufactured at higher temperatures which extends their allowable transport time. Overall the relationship between haul time and temperature differentials was calculated at 3% (Figure 4.5). Greater than a 90 minute haul time may be required to see significant impacts on temperature differentials; longer haul distances could not be found to include as part of this study. A brief investigation of the mix types Nebraska uses and their allowable haul time would be a very appropriate study to further identify which mixes can be used for sites that are at risk of developing temperature differentials due to increased haul times. Overall, this investigation indicates that current remixing practices carried out onsite are sufficient at preventing temperature segregated material as a result of transport.

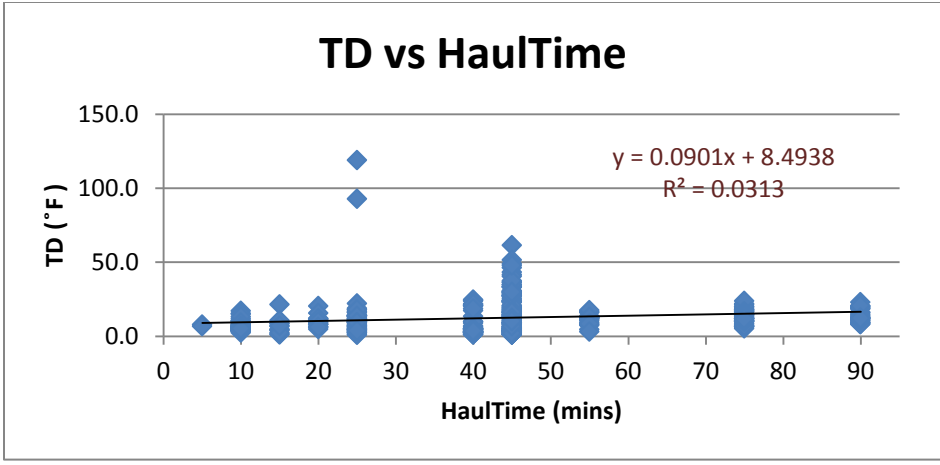


Figure 4.5 Relationship between Haul Time and Temperature Differentials

### 4.2.3 Material Feeding Machines

There are two types of material feeding processes from a delivery truck to a paver used in Nebraska. Either HMA trucks directly dump delivered HMA into the hopper of a paver (Figure 4.6), or belly dump trucks and live belly dump trucks deposit the material ahead of a pickup machine which scoops up the HMA and transfers it into the hopper of a paving machine (Figure 4.7).



Figure 4.6 Direct dump between truck and paver

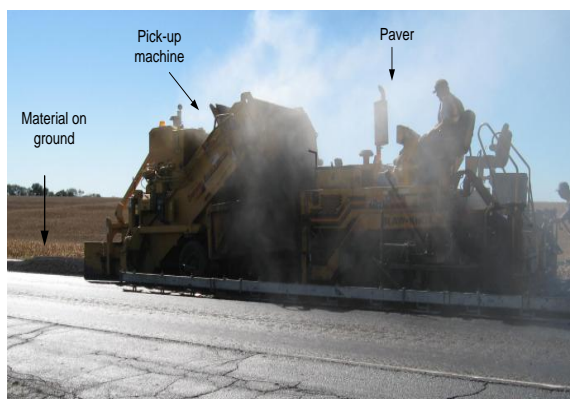


Figure 4.7 Pick-up machine with paver

Figure 4.8 shows the temperature differential variation for each material feeding process. When a pick-up machine is used between a belly dump truck and a paver, the completed material shows a more consistent temperature profile (standard deviation = 5.3°F) than when a truck directly dumps HMA material into a road paver's hopper (standard deviation = 13.1°F). The significantly smaller standard deviation demonstrates how a pickup machine is a very cost-effective solution to reduce temperature differential of delivered HMA without using expensive MTVs.


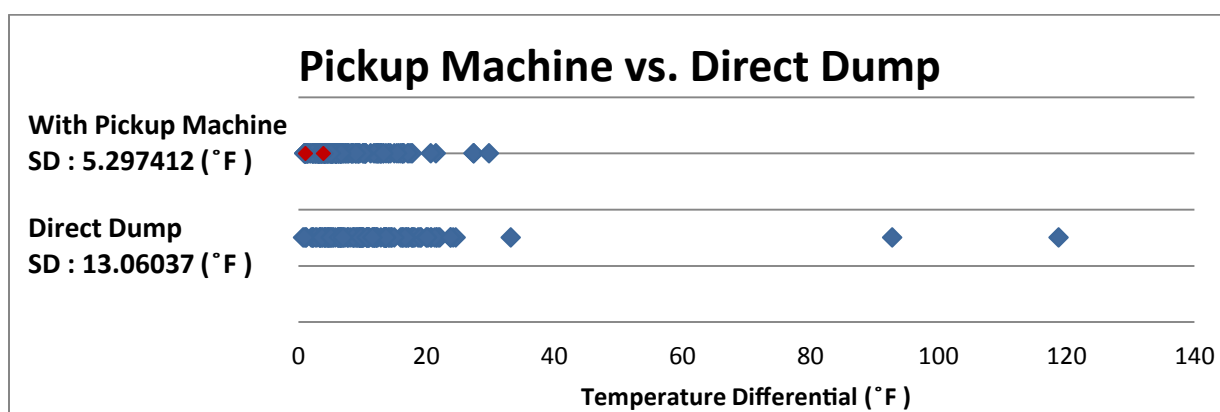


Figure 4.8 Temperature Differential based on feeding types

#### 4.2. 4 Wind Speed

Wind speed was collected at each location for Sites 11-15 with a hypothesis that its affects could lead to HMA temperature segregation (Figure 4.9). The data suggests that wind speed has a negligible effect on temperature segregation, showing less than a 1% relationship. This is because the wind is likely impacting the pavement overall, rather than at focalized areas.



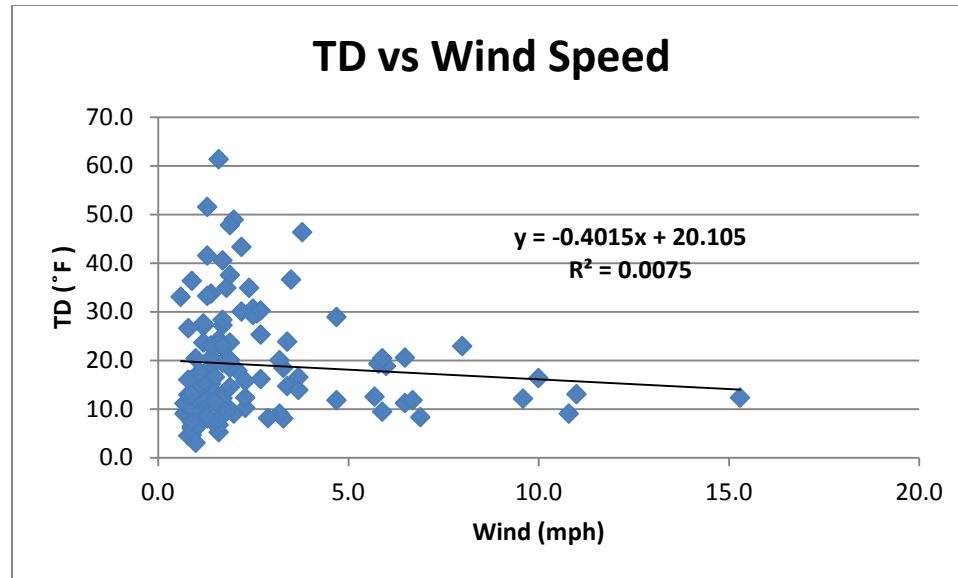

**Figure 4.9 Relationship between wind speed and temperature differentials (TD)**

### 4.3 Chapter Summary

A direct relationship between temperature differentials and density among all collected data was not found, however after separating those locations into discrete temperature groups a distinct relationship (87.3%) appears. Contrary to initial hypotheses, outside air temperature and material haul times did not appear to significantly impact the occurrence of temperature segregation. The material transportation method did have a noticeable effect on pavement temperature segregation, with trucks incorporating a pick up machine having a standard deviation of material temperature of half of that utilizing the direct dump truck method. Wind speed did not cause notable temperature segregation due to its tendency to impact the pavement overall and not at specific locations.

## Chapter 5 Inspection Analysis

Throughout the last two years, eighteen HMA paving projects have been visited to investigate the significance of temperature segregation. Of the 18 sites, each site has weathered at least one freeze-thaw cycle. In order to fully understand the ramifications that temperature segregation has on overall pavement quality, it is important to visually inspect a paving site throughout its useful life. Of the 18 sites, 15 sites have since been inspected with the exception of 8, 9, and 10. Sites 8 and 9 were originally paved as bypass routes and have now been demolished, and site 10 was not selected for inspection because a limited number of data points were located during the initial visit.

One year after initial data collection, 11 of the sites had completed one freeze-thaw season, and were therefore visited for inspection. Of the 259 data points in these 11 sites, 76 of them were found to show signs of premature distress, and 174 were found to still be in good condition. The remaining 9 locations could not be located for inspection.

Two years after initial data collection, the same 11 sites which had now completed two freeze-thaw cycles, and an additional 4 sites that had completed their first freeze-thaw cycle were inspected. Of the 367 data points comprised in these 15 sites, the number of premature distress locations now numbered 105, with 256 remaining in good condition and the remaining 7 locations not being located. A summary of these findings is displayed in Table 5.1

**Table 5.1 Total Premature Distresses vs. Good Condition**

Total Premature Distresses vs. Good Condition (First Revisit)			
Total	Premature Distresses	Good Condition	Unknown
259	76	174	9
100.00%	29%	67%	3.5%
Total Premature Distresses vs. Good Condition (Second Revisit)			
Total	Premature Distresses	Good Condition	Unknown
367	105	256	7
100.00%	28%	70%	2%

After the initial site inspection, 29% of the total data points exhibited signs of premature distress just eight months to one and a half years later. The remaining data points were still in good overall condition while 3.5% of the points could not be located. Results were largely unchanged after the second round of inspections. This indicates most premature distress will be visible a short year later. This finding could be beneficial for state and local maintenance crews in how they approach roadway crack sealing and maintenance.



### 5.1 Types of Premature Flaws

This study classified the observed premature distresses into four types: transverse, surface void (small potholes), multi-crack joint, and aggregate segregation. Table 5.2 and Figure 5.1 show a breakdown of how the flaws are distributed into the four distinct

categories after each round of inspections. A clear definition of each flaw type is given following the breakdown.

**Table 5.2 Instances of Premature Distress by Type**

Total Instances of Premature Distress by Type (First Revisit)				
Total	Transverse	Surface Void	Multi-Crack joint	Segregation
76	19	28	5	24
100.00%	25.00%	37%	6.5%	31.5%
Total Instances of Premature Distress by Type (Second Revisit)				
Total	Transverse	Surface Void	Multi-Crack joint	Segregation
105	27	32	6	40
100.00%	26%	30%	5%	38%

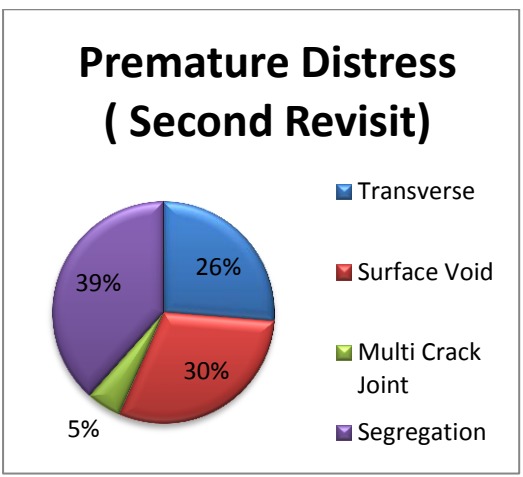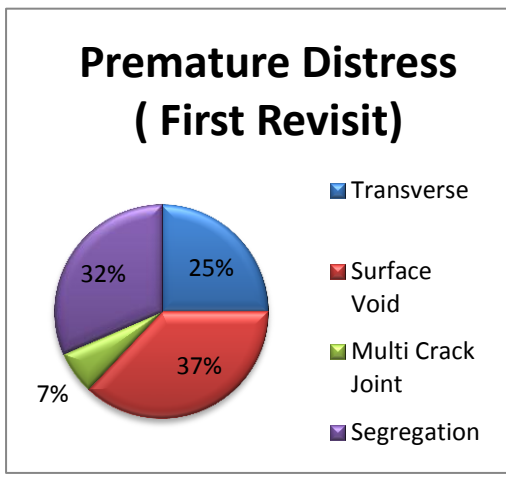

**Figure 5.1 Instances of Premature Distress after Each Inspection Phase**

### 5.1.1 Transverse Crack

The picture below is indicative of a transverse crack (Figure 5.2). Transverse cracks are formed perpendicular to the direction the asphalt paver travels, and are often the result of asphalt shrinkage. Because areas of different temperature expand and contract at different rates, transverse cracks are of particular interest in this investigation. Cracks of this type also often occur as reflective cracks which will be discussed later.



Figure 5.2 Observed Transverse Crack

### 5.1.2 Multi-Crack Joint

In referencing the Asphalt Institute's article on *Understanding Asphalt Pavement Distresses-Five Distresses Explained* (Walker, 2009), it was found that there was no singular designation for the type of flaw shown below in Figure 5.3. Because this flaw appears to be a meeting of one longitudinal crack and one transverse, it will be further identified as a multi-crack joint. The primary reasons these multi-crack flaws are formed

can be assumed to be a combination of the reasons for transverse cracks and longitudinal cracks. Longitudinal cracks are often formed due to shrinkage, reflective cracking, and longitudinal segregation caused by poor paver operation. The reason transverse cracks are formed have been stated previously (Walker, 2009).



**Figure 5.3 Observed multi-crack joint**

### **5.1.3 Segregation**

An example of segregation can be seen from a picture taken during inspection below in Figure 5.4. For clarity, during this investigation's site inspection phase areas exhibiting signs of aggregate segregation were noted simply as "segregation," in an effort to not confuse temperature segregation information. AASHTO explains aggregate segregation as, "the non-uniform distribution of coarse and fine aggregate components within the asphalt mixture (AASHTO, 1997)." Because a visual inspection was done to locate these flaws, only coarse aggregate segregation was located. Coarse aggregate

segregation can be thought of as including a disproportionate amount of coarse aggregate to fine aggregate as well as low asphalt content (Williams et al., 1996). Aggregate segregation in HMA can be caused by improper mixing. Aggregate segregation leads to flaws like: accelerated rutting, fatigue failure, and potholes (Williams et al., 1996; Walker, 2009).



**Figure 5.4 Observed Material Segregation**

#### **5.1.4 Surface Voids**

An example of an early pothole is shown below in Figure 5.5. To be clear, for inspection purposes, a small void was taken to be any small void larger than a quarter sized coin but less than a 12 oz. pop can's diameter of about 2 ½ in. These identified surface voids have not become detrimental to overall pavement quality yet, however, it was important for the research team to tag these locations, because these small surface voids have the potential of developing into major problems. It is the author's hypothesis that these small potholes have developed from large pieces of aggregate cracking or

popping out of the surface of the pavement during the freeze-thaw cycle. Because these voids have not degenerated the pavement quality to date, later data analysis deals with their inclusion at certain times only.




**Figure 5.5 Observed Surface Void**

## **5.2 Site Inspection Procedure and Data Collection**

Initial site inspections for all available sites were conducted between eight and eighteen months after the initial site visit, with the second phase of inspections taking place within the same time window one year later. At each site, a handheld GPS unit was used to locate each location that was investigated at the time of paving. Additionally, some exact locations were found based on survey markers placed along the shoulder of the road. Figure 5.6 shows what these markers looked like after one freeze thaw cycle.



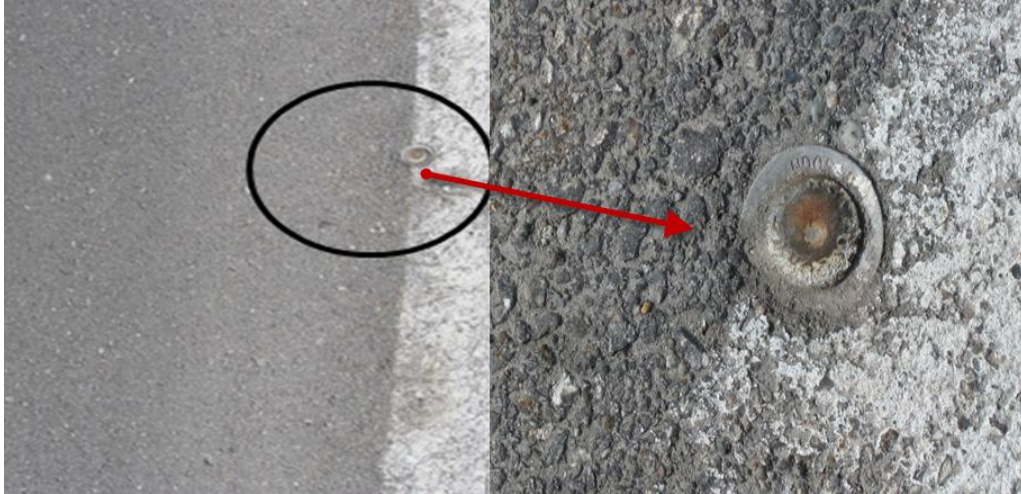

**Figure 5.6 Observed Marker After One Freeze Thaw Cycle**

At each location, a visual inspection was conducted. If a flaw was noticed, a brief description of the flaw was made, a digital picture of the location was taken, and a visual analysis of the flaw's surroundings was made to determine if it is an isolated flaw or repetitive. Extra care was taken to create four distinct flaw groups and what requirements must be present for the location to be deemed as flawed. These specific guidelines were created because classifying a location as flawed is a somewhat subjective process.

### **5.3 Site Inspection Analysis**

#### **5.3.1 Site Inspection Analysis by Distress Type**

All the data collected during site inspections were separated into the four specific flaw categories as outlined above. It is important to first analyze each flaw or distress type separately because different, often unique, reasons cause specific failures.

### 5.3.1.1 Transverse Crack Premature Distress

Nineteen instances of transverse cracks were noted during the first year's re-visitation. As this research is primarily concerned with the overall relationship between temperature differentials and density, all nineteen locations were evaluated based on that criterion. After calculating their relationship, a correlation ( $R^2$ ) of just over 27% was obtained (Figure 5.7). After the second year's inspection, 27 instances of transverse cracks were observed with a correlation of just over 23%. These correlations were lower than expected because the collected data include reflective cracks which are not affected by temperature differential.


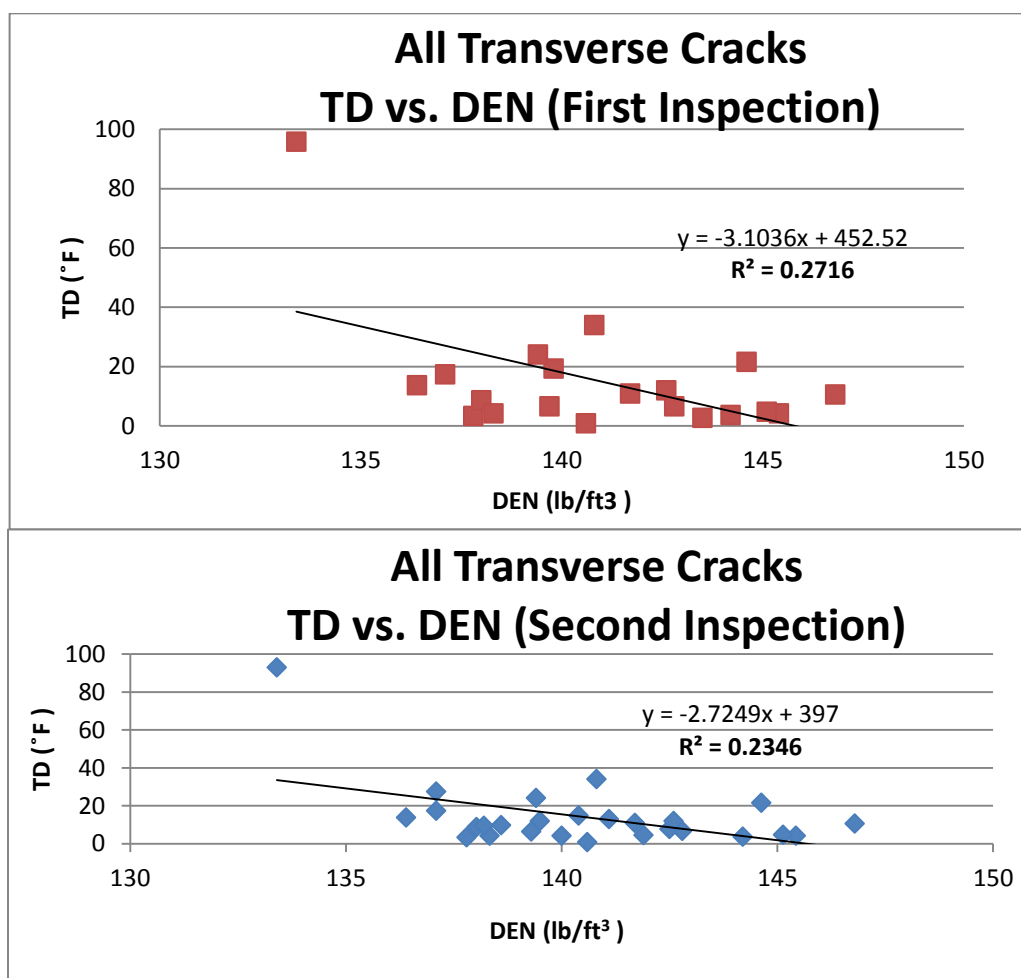


Figure 5.7 Relationship of TD and Density among Transverse Cracks

### 5.3.1.2 Reflective Crack Premature Distress


After collecting individual location data and preliminary analyses were conducted, each site was considered as a whole. It was during this second phase of data analysis that the research team decided it was important to take a closer look at the instances of repetitive transverse cracks because some were suspected of being reflective in nature. Reflective cracks occur when the cracks in older bituminous roadways are reflected upon a new asphalt overlay, this pavement anomaly is depicted graphically below (Figure 5.8).

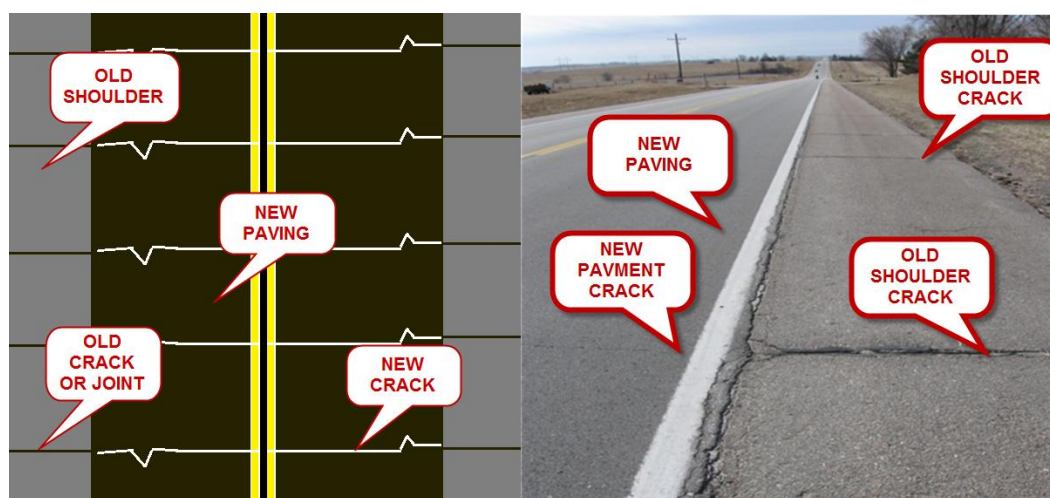

**Figure 5.8 Plan view of roadway exhibiting reflective cracks (Left) Observed reflective cracking (Right)**


From the 27 observed instances of transverse cracking, 15 were found to exhibit signs of reflective cracking. When analyzing the 15 locations alone, a relationship of less than 1% was found between temperature segregation and density. This analysis further solidifies the researchers' assumption that these locations were caused by cracks

permeating up through old layers of material and not due to temperature differentials (Figure 5.9).

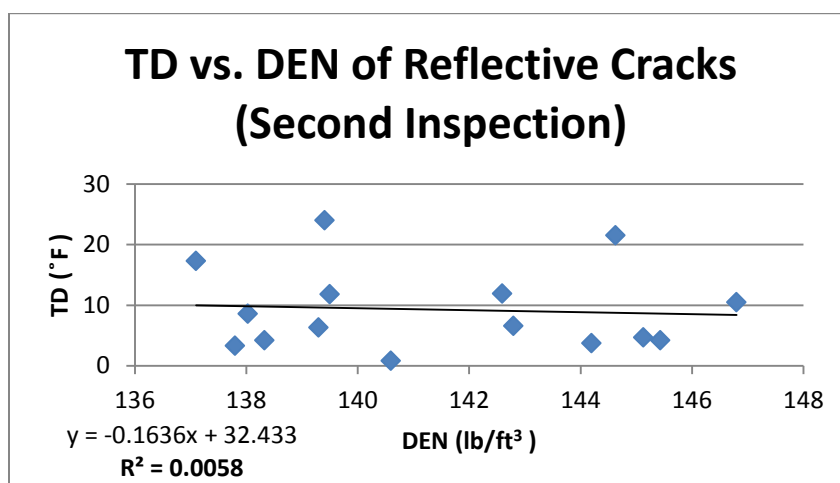

**Figure 5.9 Temperature Differentials and Density Relationship among Reflective Cracks**

The 15 locations were not further included in data analysis as these locations were almost certainly influenced primarily by the previous pavement underlayments. After excluding the suspected reflective cracks, the remaining six transverse cracks that had developed before the first inspection were found to possess an increased relationship (60.7%  $R^2$ ) between temperature differentials and density (Figure 5.10). Of the transverse cracks observed during the second year's inspection, the remaining twelve cracks were found to have a 40.4%  $R^2$  relationship between temperature differential and density.

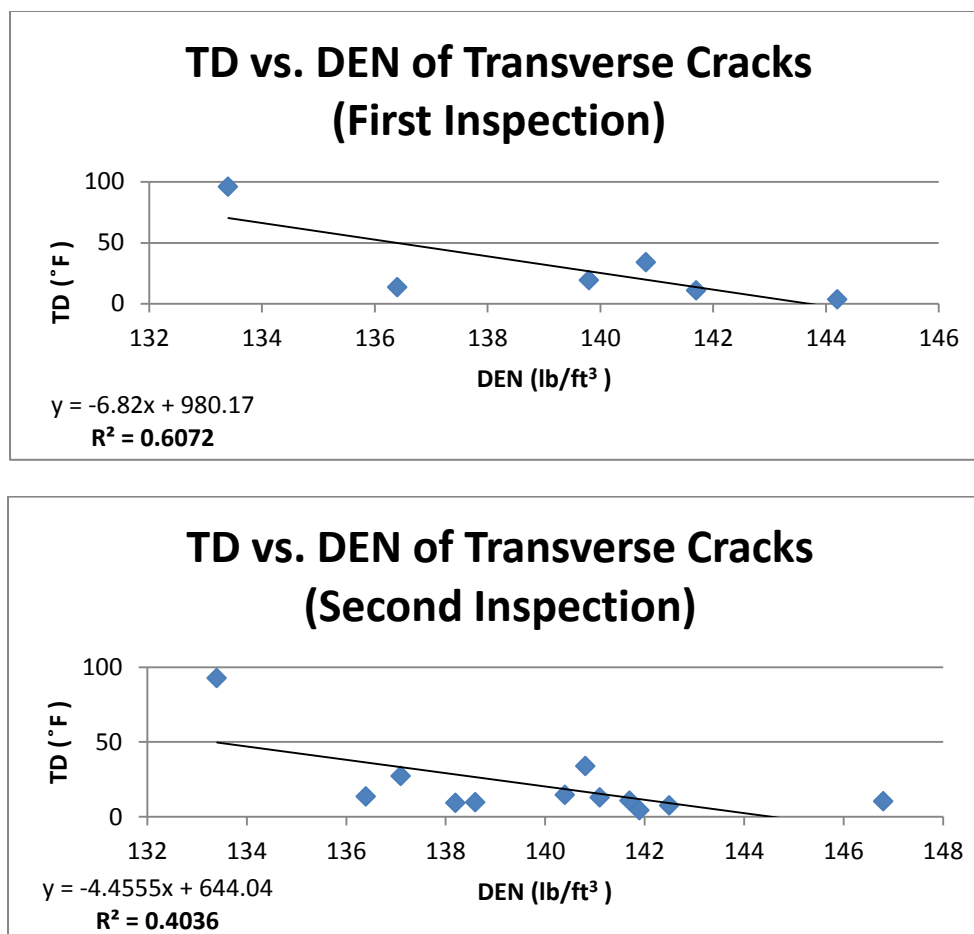

**Figure 5.10 Relationship between temperature differentials (TD) and density (DEN) excluding reflective cracks**

### 5.3.1.3 Surface Void Premature Distress

Small surface voids, or “potholes,” have proven to be a counter-intuitive flaw. It is assumed that surface voids in the pavement will begin to develop at specific locations because of inadequate densities. One primary cause of inadequate density, and the focus of this research, is due to temperature segregation, namely cold spots. It is assumed that these cold spots would “set up” faster than the surrounding warmer temperatures, thereby increasing the ability to resist compaction. However, when analyzing locations classified as a surface void (or pothole), a positive relationship was found between temperature

differentials and pavement density. This positive relationship follows counter to the assumed negative relationship where high temperature differentials would translate to low densities. This is more easily explained by referencing Figure 5.11 below.

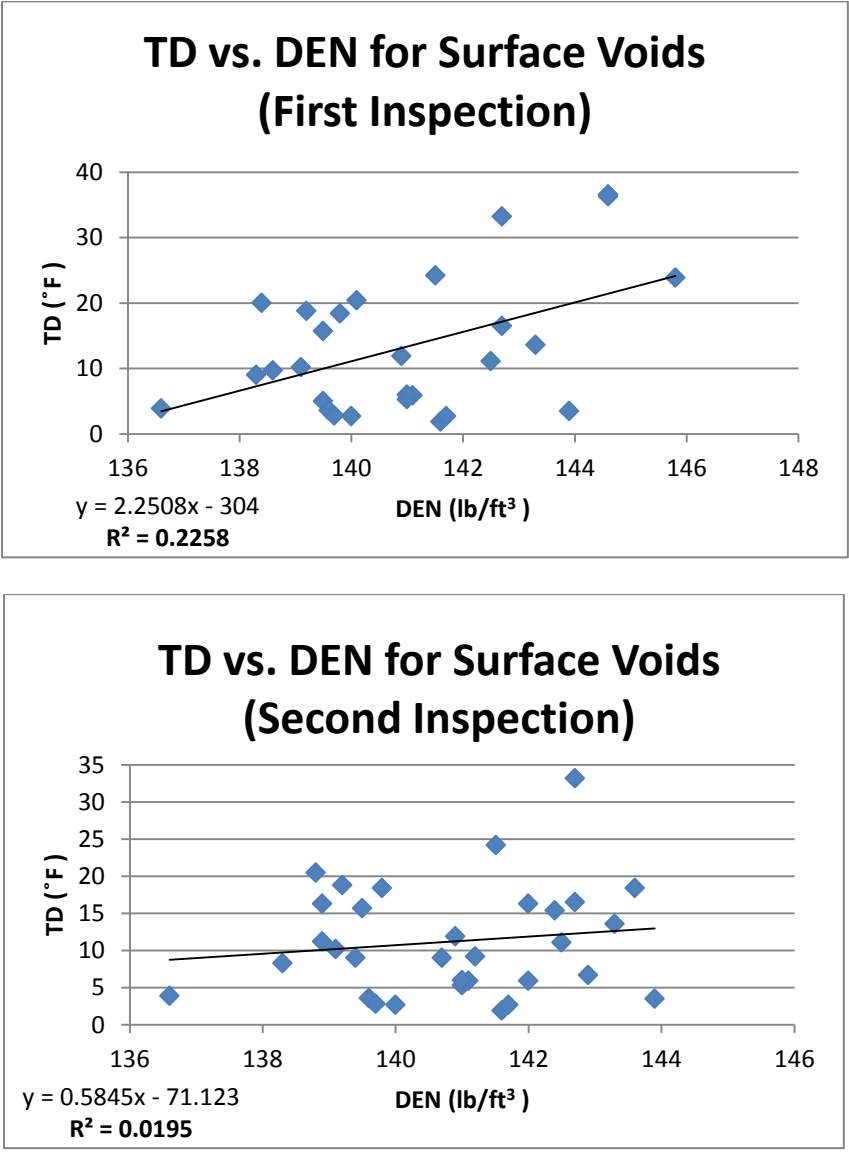


Figure 5.11 Relationship between temperature differentials (TD) and density (DEN) among surface voids

Significant consideration should not yet be given to the preceding analysis as these voids have not yet become pronounced enough to be fully classified as a premature failure. However, it is an interesting relationship, and one that might be explained more through the gradation of the mix design used rather than temperature differentials. By monitoring how these voids change in later years, time may show a decreased importance on temperature differential and an increased importance on mix gradation.

Due to the characteristics these voids possess in relation to other premature distresses, they were intentionally excluded from some of the premature distress analysis. Later inspection data may prove their worth in inclusion; however, at this time it is felt that the voids exclusion in overall premature distress analysis is warranted.

#### **5.3.1.4 Multi-Crack Joint Premature Distress**

Of the five instances of multi-crack joint type of premature flaws located during visual inspections, a 92% negative relationship was calculated between temperature differential and density. It should be noted that four of the five multi-crack joints were found during the first wave in inspections on jobsites at least one year old. It is also important to point out that if the extreme outlier with a temperature differential of 118 degrees is removed from the data set the relationship drops drastically to under 12%  $R^2$  (Figure 5.12). However, if considering only the three multi-crack joints found in the first year, the correlation between temperature differential and density remains in the 90<sup>th</sup> percentile.

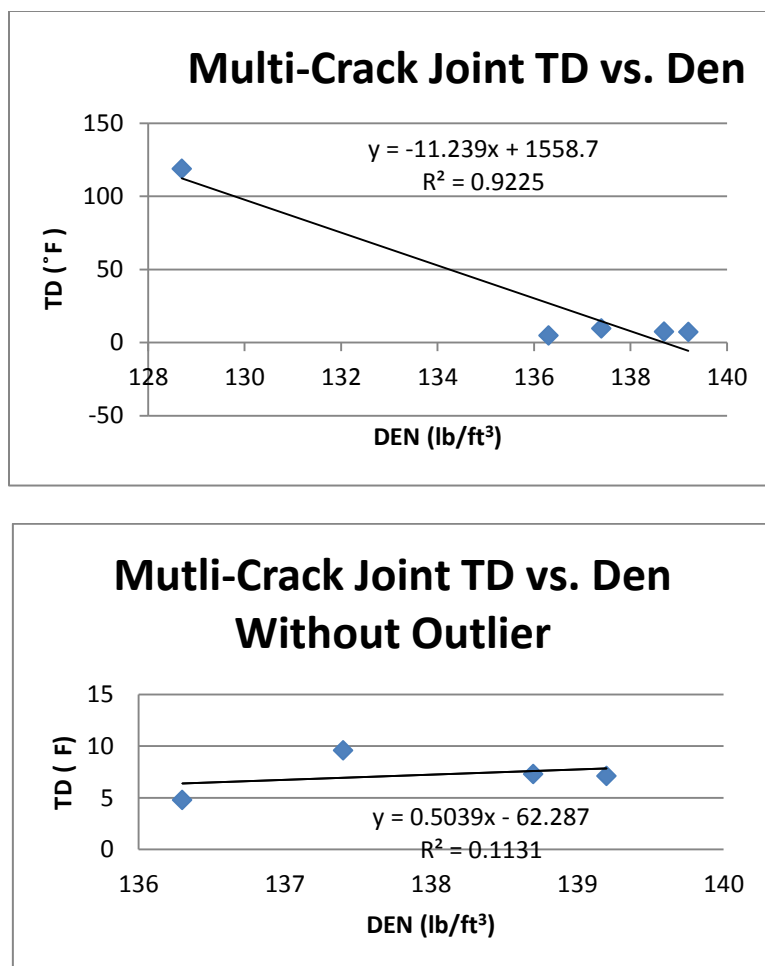


Figure 5.12 Correlation between temperature differential and density among multi-crack joints

### 5.3.1.5 Aggregate Segregation Flaws

Aggregate segregation was noted at 24 locations during the first year's site inspections, whereas 40 locations were noted during the second year's site inspections. Although the aggregate segregation was not yet contributing to the degeneration of roadway quality, they were noted because of their potential to eventually do so. Recall from the preceding discussion that aggregate segregation often means decreased binder content which will weaken the pavement at that location. Additionally, the presence of coarse gradation on the pavement surface is more likely to crack or pop free of the pavement during freeze-



thaw cycles, thereby turning into premature distresses in the form of surface voids or potholes. Of the 24 locations with visible material segregation, a 15% negative relationship was found between temperature differential (TD) and density (DEN) (Figure 5.13). The correlation between TD and DEN decreases further to under 5% in the second year, with 40 locations being noted.

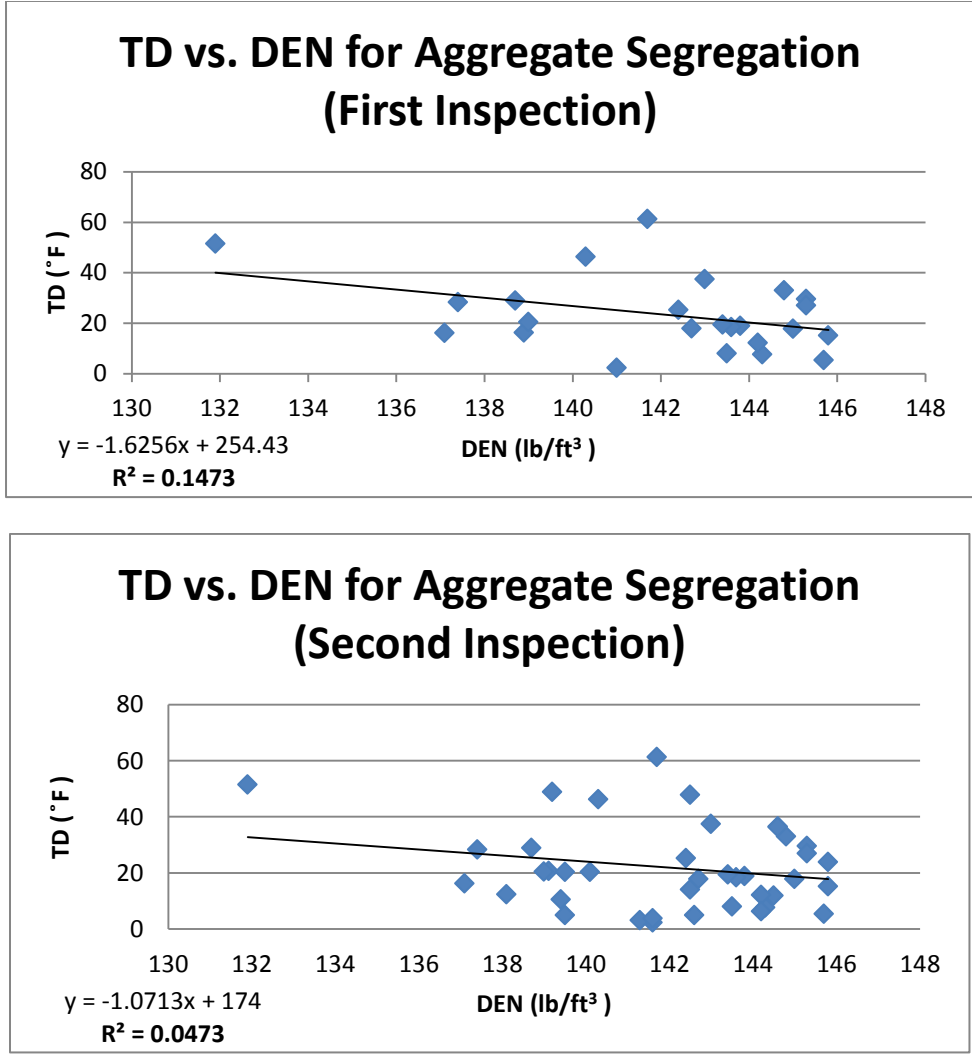


Figure 5.13 Relationship between temperature differentials (TD) among aggregate segregation

### 5.3.2 Overall Inspection Data Analysis


Paramount to completing the inspection analysis is the overall relationship between temperature differentials and density excluding reflective cracks. Table 5.3 shows all premature pavement flaws noted during this research project. Those fields highlighted in blue had been subjected to two freeze-thaw seasons. After the first and second year's inspections the premature pavement flaws exhibited a relationship of 18% and 15% respectively between temperature differentials and density (Figure 5.14).

**Table 5.3 First Year's Inspection Data Analysis**

Blue=Two Freeze Thaw Seasons

TD in ( °F), DEN in (lb/ft<sup>3</sup>)


NUM	TD	DEN	NUM	TD	DEN	NUM	TD	DEN	NUM	TD	DEN
1	1.9	141.6	23	7.3	138.7	45	13.6	143.3	67	20.5	139
2	2.3	141.6	24	7.7	142.5	46	13.7	136.4	68	20.7	139.1
3	2.7	140	25	7.7	144.3	47	14.1	142.5	69	23.9	145.8
4	2.7	141.7	26	8	143.5	48	14.7	140.4	70	24.2	141.5
5	2.8	139.7	27	8.3	138.3	49	15.2	145.8	71	25.3	142.4
6	3.1	141.3	28	9	139.4	50	15.4	142.4	72	27	145.3
7	3.5	143.9	29	9	140.7	51	15.7	139.5	73	27.4	137.1
8	3.6	139.6	30	9.2	141.2	52	16.2	137.1	74	28.3	137.4
9	3.8	141.6	31	9.4	138.2	53	16.3	138.9	75	28.9	138.7
10	3.9	136.6	32	9.6	137.4	54	16.3	142	76	29.6	145.3
11	4.5	141.9	33	9.7	138.6	55	16.5	142.7	77	33	144.8
12	4.8	136.3	34	10.2	139.1	56	17.8	145	78	33.2	142.7
13	4.9	142.6	35	10.5	146.8	57	17.9	142.7	79	34	140.8
14	5	139.5	36	10.5	139.4	58	18.4	143.6	80	36.3	144.6
15	5.3	141	37	10.9	141.7	59	18.4	139.8	81	36.6	144.6
16	5.4	145.7	38	11.1	142.5	60	18.4	143.6	82	37.5	143
17	5.9	141.1	39	11.2	138.9	61	18.8	139.2	83	46.3	140.3
18	5.9	142	40	11.9	140.9	62	18.9	143.8	84	47.8	142.5
19	6	141	41	11.9	144.5	63	19.5	143.4	85	48.9	139.2
20	6.3	144.2	42	12.2	144.2	64	20.4	139.5	86	51.5	131.9
21	6.7	142.9	43	12.4	138.1	65	20.4	140.1	87	61.3	141.7
22	7.1	139.2	44	12.9	141.1	66	20.5	138.8	88	95.8	133.4
									89	119	128.7

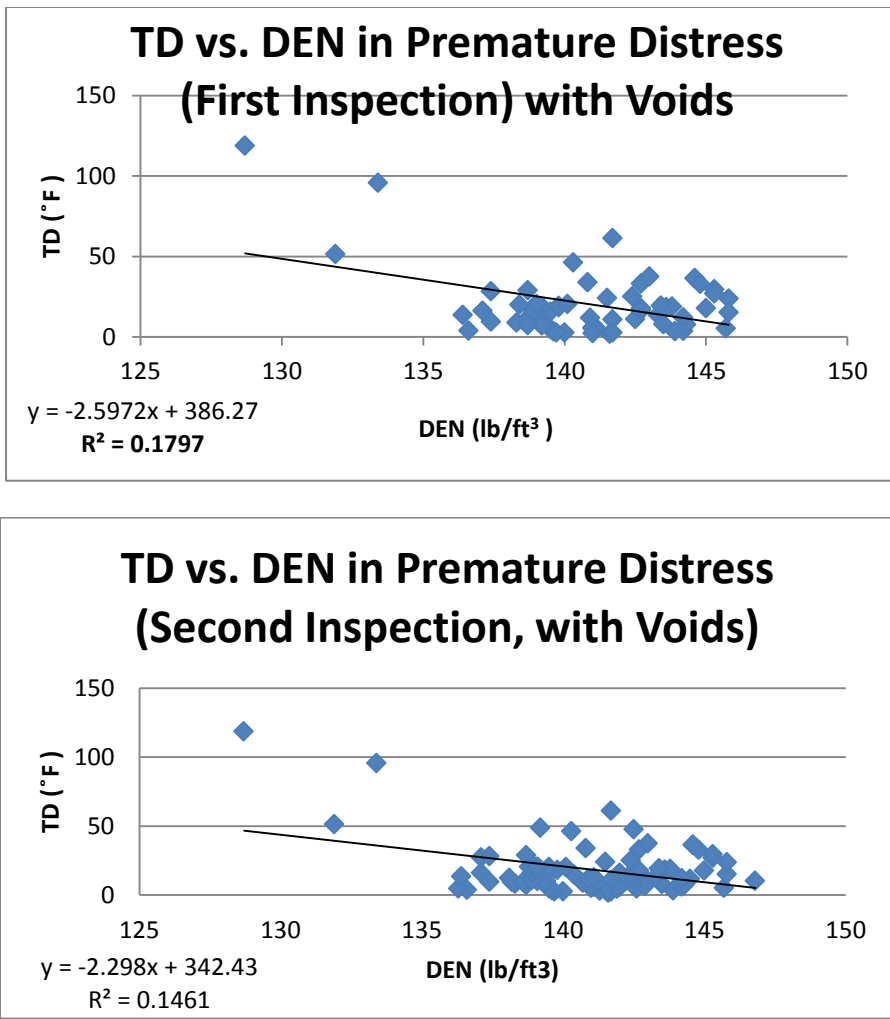

**Figure 5.14 Relationship between temperature differentials and density among total instances of observed premature distresses**

Recall, however, that when analyzed individually the surface void type of flaw exhibited a positive relationship between TD and density. Because all other flaw types show signs of being impacted by temperature differentials in regard to their corresponding densities, while the locations with small voids do not, they were removed from the data set. The remaining 34 (First Inspection) and 56 (Second Inspection) premature distresses or flaws were analyzed with regards to temperature differential and

density. Results are improved and shown graphically in Figure 5.15, with the first year's analysis improving 19% from 17% up to 37%, and the second year's analysis improving 7% from 15% up to 22%.

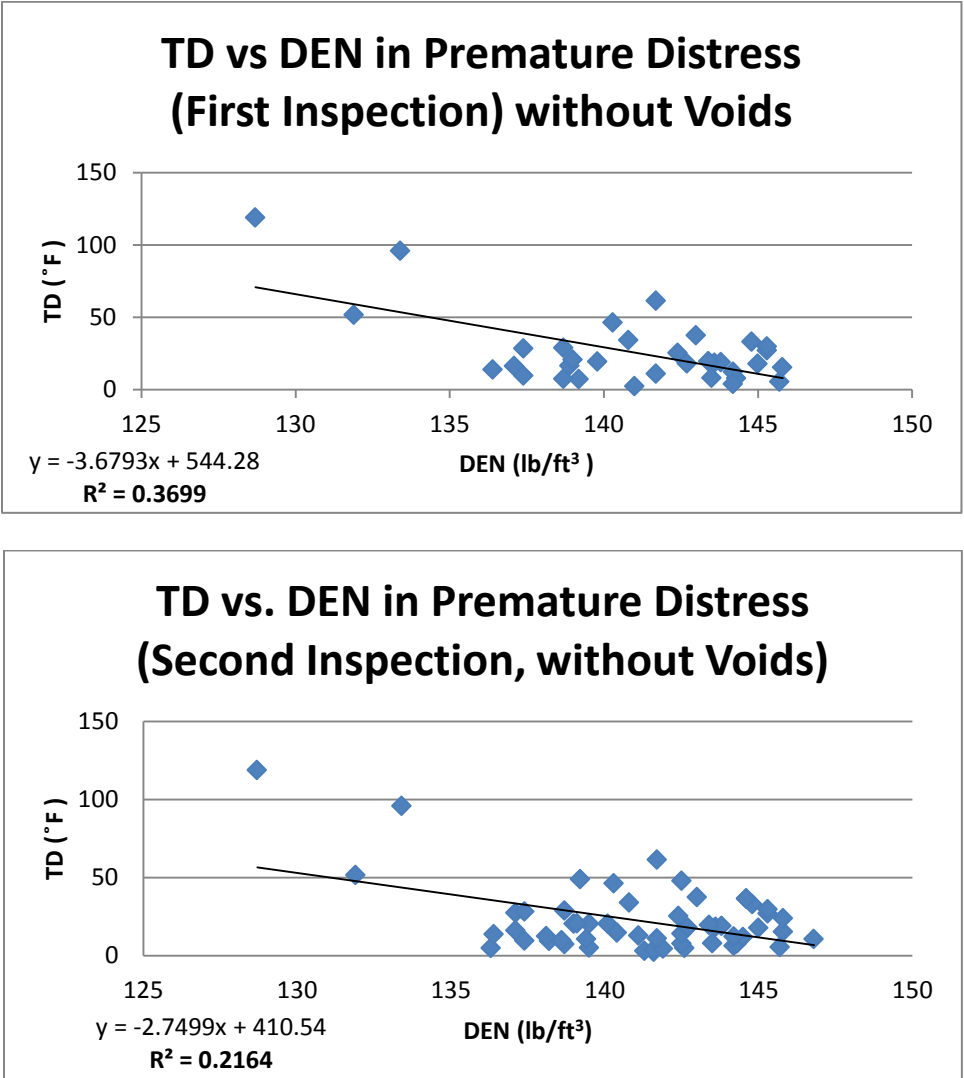

**Figure 5.15 Relationship between temperature differentials and premature distresses, excluding surface voids**



Although Figure 5.15 gives great insight to how the density of HMA is impacted by temperature differentials overall, it does not present a complete picture. It is helpful to

sort the locations showing signs of premature distresses into temperature differential groups as shown in Table 5.4. After sorting, the relationship ( $R^2$ ) between TD and density according to a temperature range is nearly perfect (99.76%) as shown in Figure 5.16 when analyzing the first year's inspection data and removing surface voids from the data set. Additionally, the same figure shows a 93 % relationship between TD and density according to prescribed temperature ranges. This illustrates that the prematurely distressed material caused by a temperature differentials have a higher probability of possessing lower densities as the temperature differential increases. What this relationship means, for example, is that if a site inspector is analyzing a particular location with a pavement defect after roadway construction and that location had a temperature differential of 15 ° F immediately after construction, the inspector can assume that location has nearly a 50% chance of holding true to the hypothesis that its lower density value is due in part to temperature segregation. The relationship also means that as locations are found to be hotter and hotter that inspector can be more confident that lower measured densities are indicative of temperature segregation.

**Table 5.4 Relationship between  $R^2$  and corresponding TD groups for premature distresses**

Num	Temperature Diff. Range (°F)	$R^2$	Included Premature Distresses Data Points Excluding Surface Voids (Year 1)
1	5 ° F and Up	0.3682	32
2	10 ° F and Up	0.4333	26
3	15 ° F and Up	0.4941	23
4	20 ° F and Up	0.5474	14
5	25 ° F and Up	0.5953	13
6	30 ° F and Up	0.6634	8

Num	Temperature Diff. Range (°F)	R <sup>2</sup>	Included Premature Distresses Data Points Including Surface Voids (Year 2)
1	5 °F and Up	0.06106	76
2	10 °F and Up	0.095545	56
3	15 °F and Up	0.134325	41
4	20 °F and Up	0.131669	26
5	25 °F and Up	0.210922	19
6	30 °F and Up	0.332316	13

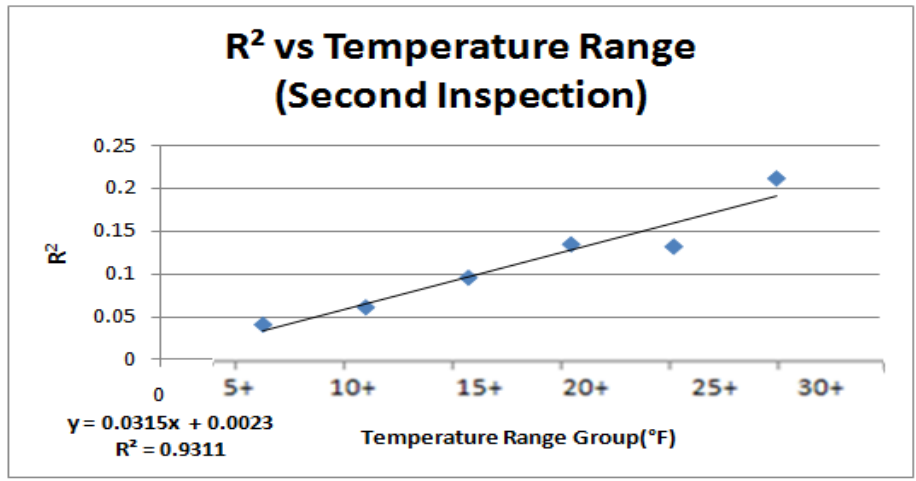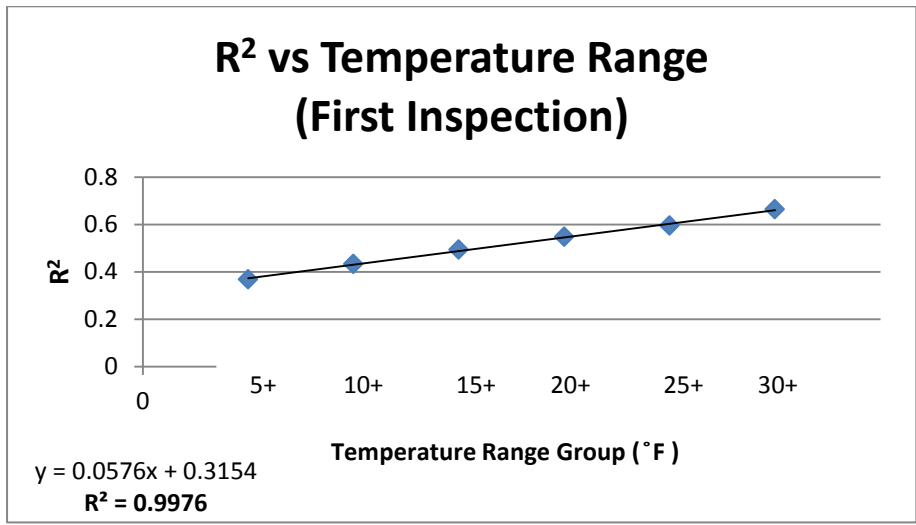

**Figure 5.16 Relationship between the correlation of TD and DEN for a given temperature range and the temperature range group**

It is useful to also investigate the simple relationship between temperature differentials and the occurrence of premature flaws. In order to do this, all premature distresses and noted flaws were separated into the corresponding temperature differential range that was documented at the time of paving (Table 5.5). These ranges were simply charted against how often premature distresses or flaws were noted out of all data points falling within the specified range (Figure 5.17). For example, when looking at all the locations investigated within the 15 °F to 20 °F temperature range, 39% of those locations have shown signs of premature distress or flaws between 8 months and 1½ years later. As would be expected, the observed percentage within the same temperature range after the next year's inspections increased to 42% (Figure 5.17).



In these analyses, graphs are provided both with the inclusion of small surface voids and without small surface voids (Figure 5.18). These graphs highlight the importance of including the voids in some analyses as their relationship between TD and density has been ruled out based on their positive relationship, but the simple relationship between TD and premature flaws has not. That is to say, there is a marked trend between the occurrence of premature pavement flaws and increasing temperature differentials. When looking at Figures 5.17 and 5.18 a more distinct relationship between temperature differentials and pavement flaws was found when including surface voids. This finding indicates that although density was unaffected by temperature differentials among noted surface voids, it is still important to consider temperature differentials as leading to surface void premature distresses. This relationship is important to note because the current quality control and quality assurance practices within the State of Nebraska do

not account for temperature differentials and would therefore not identify future premature distresses in the form of surface voids.

**Table 5.5 temperature differential range (TD) vs. type of premature distress (PD) (with surface voids)**

Premature Distresses by Type and Temperature Range After First Inspection											
TD (°F)	Transverse	%	Small Voids	%	Agg. Seg.	%	Multi-Crack	%	Total	Data Total	%
1-5	1	11.1	7	77.8	1	11.1	0	0.0	9	74	12.0
5-10	0	0.0	6	50.0	3	25.0	3	25.0	12	76	15.79
10-15	2	28.6	4	57.1	1	14.3	0	0.0	7	60	11.67
15-20	1	7.7	4	30.8	8	61.5	0	0.0	13	33	39.39
20-25	0	0.0	4	80.0	1	20.0	0	0.0	5	30	16.67
25-30	0	0.0	0	0.0	5	100.0	0	0.0	5	9	55.56
30-40	1	16.7	3	50.0	2	33.3	0	0.0	6	12	50.00
40+	1	20.0	0	0.0	3	60.0	1	20.0	5	10	50.00
<b>Total</b>	<b>6</b>	<b>9.7</b>	<b>28</b>	<b>45.2</b>	<b>24</b>	<b>38.7</b>	<b>4</b>	<b>6.45</b>	<b>62</b>	<b>304</b>	<b>20.39</b>
Premature Distresses by Type and Temperature Range After Second Inspection											
TD	Transverse	%	Small Voids	%	Agg. Seg.	%	Multi Crack	%	Total	Data Total	%
1-5	1	7.7	7	53.8	4	30.8	1	0.0	13	95	13.7
5-10	3	0.0	9	45.0	5	25.0	3	15.0	20	107	18.7
10-15	5	33.3	5	33.3	5	33.3	0	0.0	15	70	21.4
15-20	0	0.0	8	53.3	7	46.7	0	0.0	15	36	41.7
20-25	0	0.0	2	28.6	5	71.4	0	0.0	7	26	26.9
25-30	1	16.7	0	0.0	5	83.3	0	0.0	6	12	50.0
30-40	1	16.7	1	16.7	4	66.7	0	0.0	6	12	50.0
40+	1	14.3	0	0.0	5	71.4	1	14.3	7	10	70.0
<b>Total</b>	<b>12</b>	<b>13.5</b>	<b>32</b>	<b>36.0</b>	<b>40</b>	<b>44.94</b>	<b>5</b>	<b>4.81</b>	<b>89</b>	<b>368</b>	<b>24.1</b>



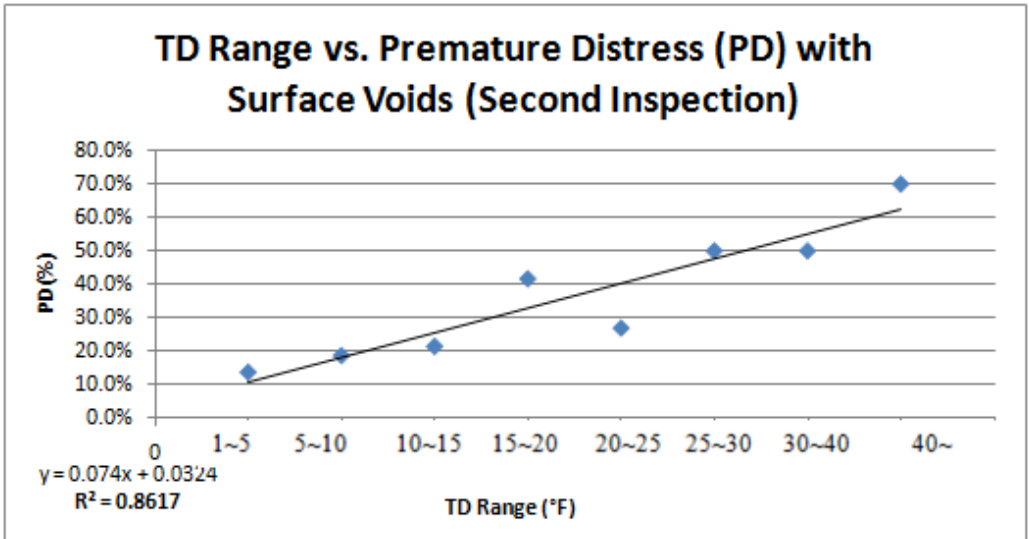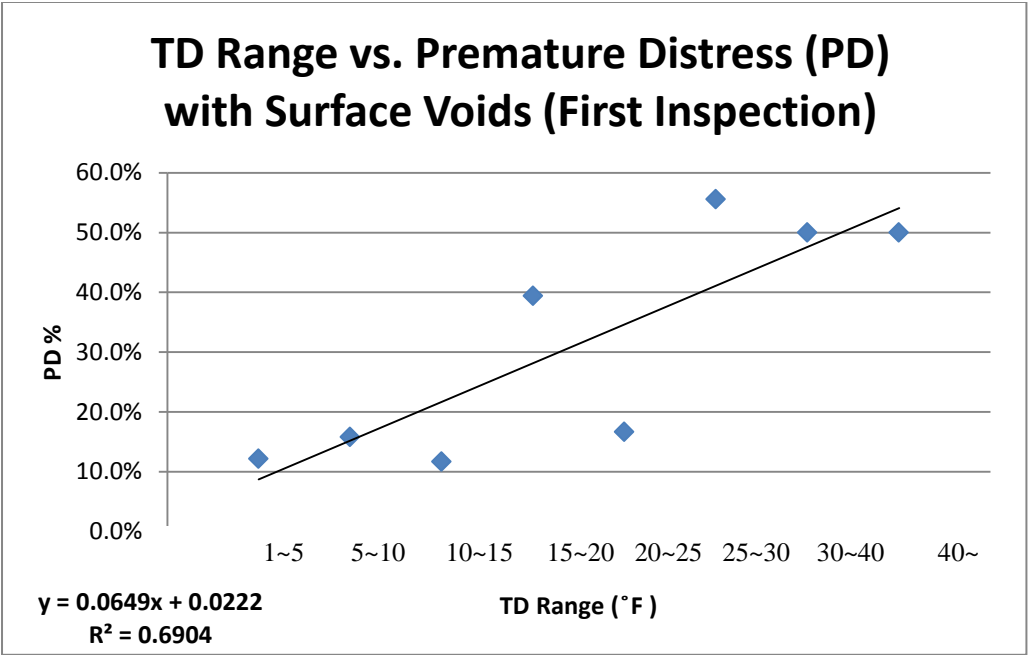

**Figure 5.17 Correlation between the percentages of premature distresses, including surface voids, found within a specified temperature range**

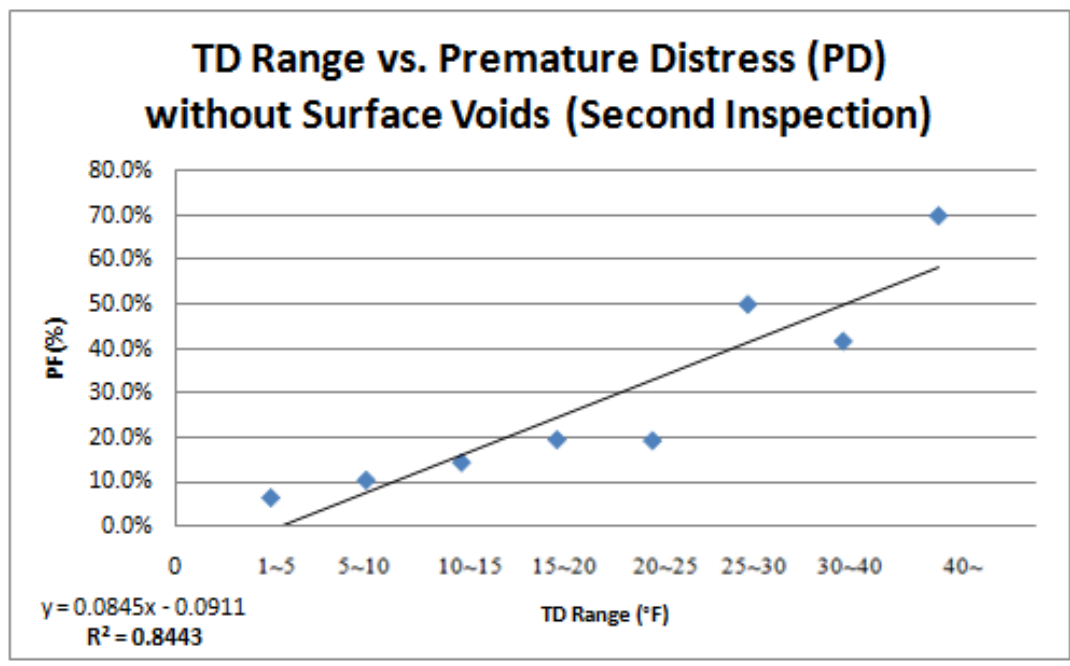
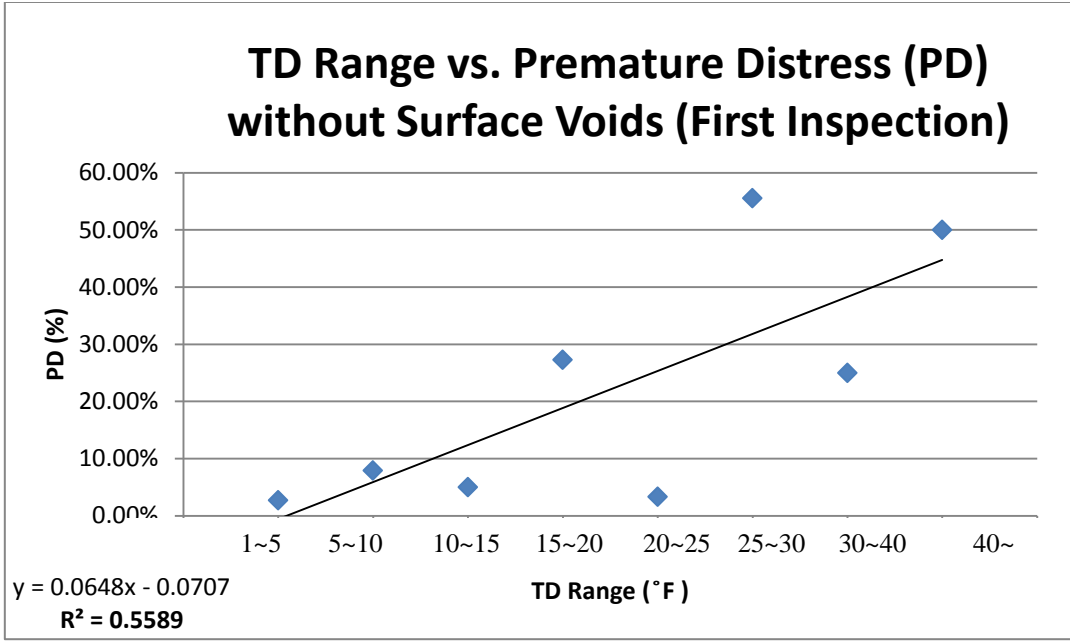


Figure 5.18 Correlation between the percentages of premature flaws, excluding surface voids, found within a specified temperature range

#### 5.4 Chapter 5 Summary


Chapter 5 dealt with the analyses of premature distress which were found at least one freeze-thaw cycle after initial paving and subsequent data collection. From the 367 locations that were initially investigated, 28% of them showed signs of premature distress. It was also proven that locations exhibiting signs of reflective cracking were not impacted by temperature segregation. Less the reflective crack, the remaining transverse cracks showed a temperature differential and density relationship of 40.4%. Because the majority of observed locations with premature distress occurred at relatively low temperature differentials, the remaining distress types, surface voids, multi-crack joints, and aggregate segregation, showed a low correlation between temperature differentials and density. Separating all distress locations by temperature differential range and graphing it against the relationship between temperature differentials and density yielded a nearly perfect correlation. This means that as temperature differentials trend higher, an individual can absolutely expect to find locations colder than surrounding material to have lower measured density after pavement compaction. Finally, the simple relationship between premature pavement distress and temperature differentials was investigated. Highlighting the impact temperature differentials have on pavement quality without considering density showed when inspectors could expect to observe future pavement distresses as a result of material temperature.

## **Chapter 6 Data Management**

Midway through the research contract it became apparent that the undertaking of this project necessitated a system to efficiently manage the growing amount of collected and analyzed data that had been accumulated. The author set out to develop a system to sort and represent data in a highly visual and intuitive manner. The developed system could be used in aid of the State's current pavement construction/maintenance management system.

### **6.1 Google Earth Based Visualization of Pavement Data**

In order to perform this investigation, a number of devices were utilized, those devices included: 1) a portable anemometer to record current weather conditions, 2) a portable GPS unit to digitally mark areas of interest for later inspection, 3) a thermal imaging camera to locate areas of HMA temperature segregation, 4) a penetrating thermometer to validate the thermal camera, 5) a digital camera to record site conditions and procedures, and 6) nuclear and non-nuclear pavement density devices to measure the compacted density of the material. In addition to data collected via portable devices, site specific information was collected that included: 1) pavement or mix type, 2) lift thickness, 3) haul time, 4) equipment used, and 5) location.

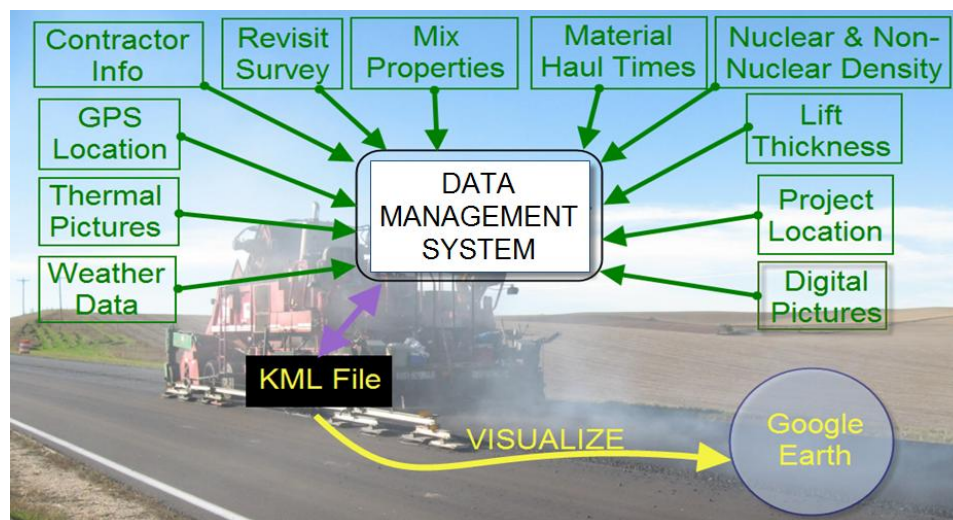

**Figure 6.1 Developed Data Management System**

The system was constructed during the paving offseason, and ready to be utilized at the start of the 2009 paving season in Nebraska. That spring all previous sites were inspected in an effort to measure or identify a change in overall pavement quality. Any changes in quality were documented and imported into the Google Earth (KML) language format database system that had previously been created. After all information from the inspection had been uploaded, users were able to simply “fly” around the Google Earth program and select individual sites to find site properties like the constructor, mix types, or even site data analyses (Figure 6.2). Once a particular site had been selected, users were able to further focus on a site specific data point (Figure 6.3). For example, when a flaw was noted at a specific location during site re-visitation, users were able to immediately call up that exact location to view relevant information that was logged at the time of construction that might explain the reason for the pavement’s premature distress. Information that might explain the pavement’s distress could have

included decreased density readings or thermal images showing drastic temperature segregation.

**SITE 1**  
SITE 1. Information & Analysis

SITE 1. Information	
Date	09-30-2007, 8:30 AM
Project Name	72nd St. N-36 to I-680
Project Number	STPE-3815(2)
Control Number	20506
Rice value	2.466
Haul Time	20~25min
Air Temperature	64 F
Truck Type	Direct dump
Paver	PF-5510 normal
Compactor	DD-90DD-24
Thickness	2.0"
Mic Type	SP-4(0.5)

**SITE PICTURES**

**SITE ANALYSIS**

The SITE 1 shows the relationship between temp differential(TD) and density(DEN). There are 72% significant relationship between TD and DEN in SITE1

**SITE1 TD&DEN**

Temp Differential(TD)

$y = -8.5172x + 1191.8$   
 $R^2 = 0.7031$

Figure 6.2 Google Earth based database

**Site1\_12**  
Site 1\_12 Data Information

Density : 136.4  
PQL Temperature : 100.8 °F

High Temp : 115.5°F  
Low Temp : 101.8°F  
Ave Temp : 107.8°F  
Temp Diff : 13.7°F

Min = 101.5  
Max = 105.0  
Avg = 104.7

Temperature of the Site1\_12

Directions: [To here](#) - [From here](#)

### **Figure 6.3 Location specific data via Google Earth**

Those working on the project were able to instantly recall location-specific data, typically in a highly visual manner, making decisions more fluent and reliable. Not only was this system easy to use and understand but it was an easy task to access from any computer with Google Earth already installed. If needed changes to project specific data could be made in real-time on the road and reflected back to users in the lab.

#### **6.1.1 Google Earth File Type**

This study has shown that the inclusion of Google Earth as a pavement construction database tool holds a valuable place; however, it is important to consider how it will be integrated with existing and future pavement or asset management systems. The Texas Transportation Institute of Texas A&M University highlighted this issue in their development of a web based tracking system for flexible pavement. The Institute noted that a system based on the XML language schema promoted easy data or file exchange (Krugler et al. 2008).

The current Google Earth program is built on a Keyhole Markup Language (KML) 2.2 Schema. In turn, the KML language schema is based on XML and was created specifically for the representation of geographic data (Open Geospatial Consortium, 2009). Most Google Earth users are familiar with the KMZ file format which is simply a zipped KML file. Though there are a number of software applications specifically designed to convert KML files to XML files and vice versa, it is easily done by opening

the KML file in a text file followed by opening and saving that text file in Excel as XML Data.

## **6.2 Database in Microsoft Access™**

The extent of this project and wide array of data types necessitated NDOR's request of a proprietary database in which to store all research data as part of the project's deliverables. The database allows the State to access historical data for later analysis if necessary. This is an important aspect of this type of research, as later findings will enhance the validity of previously collected data.

The database information is similar to the information included within the Google Earth application. In the database, site information includes: RICE value, haul time, truck type, control number, site project number, site project name, mix type, air temperature, paver type, lift thickness, roller type, site analysis summary, inspection date, inspection analysis summary, and three images of each site. Additionally, all 408 investigated locations have unique data stored in the database that includes: data number, hot temperature, cold temperature, temperature differential, pavement density, moisture content, wind speed, GPS location, infrared image, premature distress type, and 2 images of each data point.

The database was constructed using Microsoft Access™. The file extension generated by Microsoft Access is .accdb, which is easily transferred into the versatile XML schema. The database consists of four primary units, one data table called from



Excel, and three user integrated design forms (Figures 6.4, 6.5). The design forms are utilized via a simple drop down menu that then calls the appropriate data.

## Project of NDOR




Project Name:	Project1	Project Number:	HMA	Project Date:	5/3/2007	----	6/30/2009
Site Number:	Site1						

**Site1**

Date:	9/30/2007	Rice Value:	2.466	Haul Time:	25	Truck Type:	Normal
Control Number	20506	Site Project	STPE-3815(2)	Site Name	72nd,N-36 to I-680	Mix Type:	SP-4(0.5)
Air Tem	64°F	Paver Type:	PF-5510	Thickness:	2"	Compactor:	DD-90/DD-24

Site Picture:



Site Analysis:

The SITE 1 shows the relationship between temp differential(TD) and density(DEN). There are 72% significant relationship between TD and DEN in SITE1

Revisit Date:

4/20/2009

Resite Analysis:

Reflective cracking consitantly every 15-20' Unsure of underlayment.Scattered longitudinal cracking is also present. This seems to occur at areas of temp seg more often, where the reflective. Cracking is occuring regardless of temp seg. 56% of crack

**Figure 6.4 Site designed database form**

Data Number:


**Data1**

Temperature: ( Hot:  Cold:  TD:  )


Density:  H2O:  Wind:

GPS: ( W96 04.035 : N41 16.987 ) Comment:

Infrared Image:

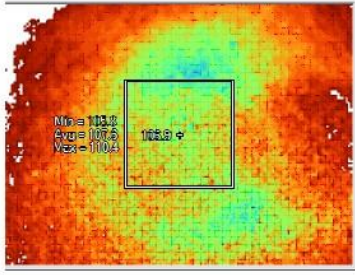

Crack Image



Crack:  Crack Type:

**Figure 6.5 Data designed database form**

### 6.3 Chapter 6 Summary

A data management system was implemented midway through the research project in an effort to organize and track the various types of information. The management system was comprised a Microsoft Access<sup>TM</sup> database and represented graphically via a Google Earth<sup>TM</sup> interface. The tracking system allowed the research team to call up previous year's data instantly, either out in the field or in the office to make decisions for analysis. The effectiveness of the management system proved that Google Earth is an effective tool for representing GIS data from a Pavement Management System.

## Chapter 7 Conclusions and Recommendations

### 7.1 Conclusions

The primary objectives of this report were to identify and measure variables which could have a significant effect on HMA temperature segregation during roadway construction in Nebraska, as well as report on the impacts temperature segregation occurrences have on overall pavement quality. Perhaps the most important conclusion of the research is that when organized according to defined temperature groups the relationship between temperature differentials and density was found to be 93%; while an 87% correlation exists between temperature differentials and the occurrence of premature distress. A more detailed overview of the findings generated in accomplishing the proposed objectives is described in the following material.

#### *1) Evaluating the possible reasons for the occurrence of thermal differentials during the HMA construction process*

The overall relationship between pavement temperature differentials and density was not readily apparent when areas of temperature segregation were identified after compaction. When taken as a whole the data did not exhibit a significant relationship between temperature differentials and density, exhibiting a 3% correlation. However, when separating the data into increasing temperature groups, a clear trend in the relationship between temperature differentials and density was found. Giving an example, when a temperature differential is 2 °F, the TD/DEN relationship is less than

5%, however when the temperature differential is increased to 30°F after compaction the relationship is increased to over 60%.

When analyzing independent construction variables within the HMA process, a very limited correlation was found. Jobsite air temperature at the time of paving was not found to be a significant indicator of increased or decreased air voids, showing a relationship of less than 3%. The activity of material hauling, in particular haul time, was also not found to be a good indicator of overall temperature segregation, again showing a 3% relationship. Discounting haul time, it was found that other material transport variables were more likely to lead to areas of temperature segregation. It was discovered that use of belly dump trucks that incorporated the use of a pickup machine was far superior to the direct dump paving process of traditional HMA trucks. The belly dump process was found to have a temperature variance of 5 °F, while the direct dump process was found to have a temperature variance of 13 °F.

The key to successfully drawing conclusions about the effects temperature segregation has within the HMA process was the inspection of past paving sites. Through these site visits, it was discovered that of the 367 investigated locations, 105 were exhibiting signs of premature distress one year later. It should be noted, however, that 15 of these flaws were decided to show signs of reflective cracking. The reflective cracks were found to hold less than a 1% relationship to temperature differentials and density, and were therefore excluded from analysis on that basis.

Transverse cracks, multiple crack joints, and aggregate segregation, were all found to have a significant relationship between temperature differentials and density, with relationships being 60.7%, 98%, and 14.73%, respectively, after the first year's inspection. Similarly, results after the second year's inspection were found to be 40.36%, 92%, 4.73%, respectively.

On the other hand, surface voids were not found to follow the typical relationship between temperature segregation and density. Later analysis did show that, although surface voids did not indicate a relationship in regards to density, it was still important to consider temperature differentials as leading to surface void premature distresses. If this trend continues, it can be assumed that under current quality control and quality assurance procedures in the State of Nebraska this flaw will remain unaccounted for. Additionally, the relatively loosely correlated relationship between temperature differentials and density for aggregate segregation highlighted in the previous paragraph is also thought of as being likely to transform into small surface voids as the larger aggregate is freed from the pavement during a freeze-thaw cycle. This could be an explanation for the weak relationship between temperature and density.

By organizing the collected premature distress data into discrete temperature ranges, the relationship between temperature differentials and density was found to be over 93%  $R^2$  after the second round of yearly inspections. Additionally, when temperature groups are compared to the instances of premature distresses there is a

marked trend, nearly 87%  $R^2$ , which indicates increases in temperature differentials lead to increases in premature distresses.

**2) *Developing a practical and economical method of preventing and managing HMA thermal differentials***

The results of this objective are discussed in Section 7.2.

**3) *Validating the effectiveness of infrared thermal images as a test modality for assessing thermal differentials in HMA***

The use of an infrared camera in indentifying areas of temperature segregation was a simple process. The research team was able to quickly focus on areas of temperature segregation and how they were created within the HMA construction process. The infrared readings generated by the infrared themography consistently showed relatively similar results to the onboard thermometer device on the non-nuclear density gauge (PQI) as well as temperature probes.

**4) *Validating the effectiveness of non-nuclear density gauge as a test modality for assessing HMA densities***

The non-destructive sensory devices selected by the research team were found to be very intuitive to potential users. The PQI 301 was found to be an effective tool in collecting HMA density readings. Its straightforward interface and ability to rapidly take HMA density readings earned it a place as an effective quality control device.

### **5) Other findings**

The location tracking system utilized as part of this study proved to be adequate. However some locations that were only marked digitally were unable to be located for inspection due to the variability of the GPS device. These locations were not included as part of the site inspection analysis.

Finally, the use of a database system that incorporated the visualization of collected data through Google Earth was found to be useful in analyzing and reviewing information. The XML platform that Google Earth's KML file type is based upon makes its incorporation into existing programs and database nearly seamless.

## **7.2 Recommendations**

1. The clear relationship between temperature segregation and premature distresses underline the importance of identifying thermal differences. The variability of each jobsite coupled with inexpensive thermography devices suggests that its inclusion as a quality control device for state inspectors is useful and economical. The funds spent on maintaining or replacing pavement failing due to temperature segregation would likely far exceed that of the purchase price of thermography equipment.
2. The use of rear dump trucks as a means of transporting HMA to the site should be prohibited unless a remixing machine is used. At a minimum, due to the material temperature relative to the outside air temperature, tight tarping of

truck beds with proper side insulation should be required year-round when using rear dump trucks.

3. Training or educational programs for the roller operators is recommended. Many compact roller operators observed in this study seemed to not have adequate knowledge on situational rolling patterns in terms of number of required rolling passes, timing, and required minimum mat temperature for rolling.
4. The inclusion of GIS based software like Google Earth or Microsoft Bing Map (Virtual Earth) could be useful as an aid to state pavement or asset management systems as a means of visualizing useful data through an intranet or the internet.
5. Possible methods of incorporating temperature segregation as a means of payment should be incorporated to the current pay structure.

### **7.3 Future Studies**

1. Further research is needed to investigate the extent of some of premature flaws such as surface voids which were identified to be caused primarily by temperature segregation rather than lower densities because current quality control/assurance activities focus on changes in material density rather than temperature segregation.



2. Further research is needed to investigate the economical impacts reflective cracks have on newly placed pavements' service lives, as well as methods to mitigate reflective cracking in general.
3. Compaction is the single most important factor to producing a durable pavement in the construction process. Even without temperature segregation, the material can still have lower density due to the incorrect rolling practices. To achieve optimum load-bearing and weathering characteristics, an asphalt mix must be compacted to within a specific range of density within a certain elapsed time.
4. It was interesting to note the vast majority of premature distresses were visible after the first year of paving, with relatively few new distresses occurring within the second year. With these findings in mind, a study analyzing the benefits of crack sealing after prescribed durations could help save roadway departments significant amounts of maintenance funds.

## References

- American Association of State Highway and Transportation Officials (AASHTO). (1997). "Segregation: Causes and Cures for Hot Mix Asphalt." Publication by the Joint Task Force on Segregation of AASHTO Subcommittee on Construction; AASHTO Subcommittee on Materials; and National Asphalt Pavement Association. AASHTO, Washington, D.C.
- Amirkhanian, S. N., B. J. Putman, (2006). "Laboratory and Field Investigation of Temperature Differential in HMA Mixtures Using an Infrared Camera." Clemson University. Report No. FHWA-SC-06-06. Clemson, SC.
- Brown, E.R. (1984). "Experiences of Corps of Engineers in Compaction of Hot Asphalt Mixtures." Placement and Compaction of Asphalt Mixtures, F.T. Wagner, Ed. ASTM Special Technical Publication 829. American Society for Testing and Materials, Philadelphia, PA. pp. 67-79.
- Brock, D. J. (1986). "Segregation of Asphaltic Mixtures." Proceedings of the Association of Asphalt Paving Technologists, Vol. 55. pp. 269-277.
- Brock, J. Don, "Hot Mix Asphalt Segregation: Causes and Cures," Quality Improvement Series 110/86, National Asphalt Pavement Association, Riverdale, Maryland, 1988.
- Brock, D. J; and Jakob, H. (1997). "Temperature Segregation/Temperature Differential Damage." Technical Paper T-134. Astec Industries, Chattanooga, TN.
- Bryant, L. J. (1967). "Effect of Segregation of an Asphaltic Concrete Mixture on Extracted Asphalt Percentage." Proceedings of the Association of Asphalt Paving Technologists, Vol. 36. pp. 269-277.
- Cooley, L.A, Jr., and E. R. Brown. Developing Critical Field Permeability and Pavement Density Values for Coarse Graded Superpave Pavements. Transportation Research Record: Journal of the Transportation Research Board, No. 1761, TRB; National Research Council, Washington, D.C., 2001,
- Gardiner, M. S., et al. "Using Infrared Thermography to Detect Non-Uniformity in Hot Mix Asphalt Pavements," Presented at the Transportation Research Board 78th Annual Meeting, Washington D.C., 1999.
- Garmin International, Inc (2007) GPSMAP 60CSx Owner's Manual Rev. E, [http://www8.garmin.com/manuals/GPSMAP60CSx\\_OwnersManual.pdf](http://www8.garmin.com/manuals/GPSMAP60CSx_OwnersManual.pdf) (December 10, 2009)

Gilbert, K., "Thermal Segregation," Colorado Department of Transportation, Report No: CDOT-DTD-R-2005-16, November 2005,

Henault, J. "Development of Guidelines for Reduction of Temperature Differential Damage (TDD) for Hot Mix Asphalt Pavement Projects in Connecticut", Construction Report No. 2222-1-99-5, Connecticut Department of Transportation, November 1999.

Hilderbrand, S (2009). "Pavement Quality Indicator Test," Nebraska Department of Road (NDOR) Project: F-385-3 (1009), <<http://www.transtechsys.com>>(August 29,2008).

Hughes, C.S. (1989). *National Cooperative Highway Research Program Synthesis of Highway Practice 152: Compaction of Asphalt Pavement*. Transportation Research Board, National Research Council. Washington, D.C.

Kennedy, T. W.; McGennis, R. B.; and Holmgreen, R. J. (1987). "Asphalt Mixture Segregation; Diagnostics and Remedies." Proceedings of the Association of Asphalt Paving Technologists, Vol. 56. pp. 304-329.

Kennedy, T. W.; Roberts, F. L.; and McGennis, R. B. (1984). "Effects of Compaction Temperature and Effort on the Engineering Properties of Asphalt Concrete Mixtures." Placement and Compaction of Asphalt Mixtures, F.T. Wagner, Ed. ASTM Special Technical Publication 829. American Society for Testing and Materials, Philadelphia, PA. pp.48-66.

Krugler, C.M.,Chang-Albitres, Scullion, T., Chowdhury, A. *Analysis of Successful Flexible Pavement Sections in Texas - Including Development of a Web Site and Database*. Research Report. 0-5472-1. Texas Transportation Institute, College Station, TX. October 2008.

Muench, T., (1998), "*Construction-Related Asphalt Concrete Pavement Temperature Differentials in Washington State*," University of Washington Civil Engineering Department, Seattle, WA.

Mallick, R. B., Cooly, L. A., Jr, Teto, M. *Evaluation of Permeability of Superpave mixes in Maine*. Final Report. Technical Report ME-001. Maine Department of Transportation, Augusta Maine, Nov. 1999

Parker, C. F. (1959). "Temperature in Bituminous Mixtures." Highway Research Board Special Report 54, Washington, D.C. pp. 28-33.

Pavementinteractive.org (2009). "Factors Affecting Compaction," [http://pavementinteractive.org/index.php?title=Factors\\_Affecting\\_Compaction](http://pavementinteractive.org/index.php?title=Factors_Affecting_Compaction) (Dec.9, 2009).

Phillips, L. (2008). "Infrared thermography Revolutionizes Asphalt Paving-Significant Cost Saving for States and Municipalities," FLIR in Focus, Cost Justification Series

Read, S. A., (1996), “*Construction Related Temperature Differential Damage in Asphalt Concrete Pavements*,” University of Washington M.S. Thesis, University of Washington Civil Engineering Department, Seattle, WA.

Sargand, S. M. (2005). “Non-Nuclear Density Gauge Comparative Study.” Ohio Research Institute for Transportation and the Environment. Report No. FHWA/OH-2005

Scherocman, J. A.; and Martenson, E. D. (1984). “Placement of Asphalt Concrete Mixtures.” Placement and Compaction of Asphalt Mixtures, F.T. Wagner, Ed. ASTM Special Technical Publication 829. American Society for Testing and Materials, Philadelphia, PA. pp. 3-27.

Scherocman, J.A. (1984, March). Guidelines for Compacting Asphalt Concrete Pavement. *Better Roads*, Vol. 54, No. 3. pp. 12-17.

Schmitt, R. (2006). “Non-Nuclear Density Testing Devices and Systems to Evaluate In Place Asphalt Pavement Density.” Wisconsin Highway Research Program. Report No. 0092-05-10

Sebesta, S., M., Zeig, and T. Scullion (2003). “Evaluation of Non-Nuclear Density Gauges for HMAC: Year 1 Report.” Texas Transportation Institute, Report No. 0-4577-1, College Station, TX, October 2003.

TransTech Systems Inc. (2008). Pavement Quality Indicator (PQI). <<http://www.transtechsys.com>> (August 29, 2008).

Williams, C. R.; Duncan, G. Jr.; and White, T. D. (1996). “Sources, Measurement, and Effects of Segregated Hot Mix Asphalt Pavement.” Report for the Joint Highway Research Project, Project No. C-36-36MM, File No. 2-4-39. Purdue University, West Lafayette, IN.

Walker, D “ Understanding Asphalt Pavement Distresses – Five Distresses Explained” . Asphalt Institute Online Magazine, 2009.

Willoughby, K. A. (August 2003) “Construction-Related Variability in Mat Density Due to Temperature Differentials.” Washington State Department of Transportation.

Willoughby, K. A., Mahoney, J., Pierce, L. M., Uhlmeier, J. S., Anderson, K., Read, S., Muench, S., Thompson, T. and R. Moore. “Construction-Related Asphalt Concrete Pavement Temperature Differentials and Corresponding Density Differentials”, Report Number WA-RD 476.1, Washington State Transportation Center, June 2001.

APPENDIX

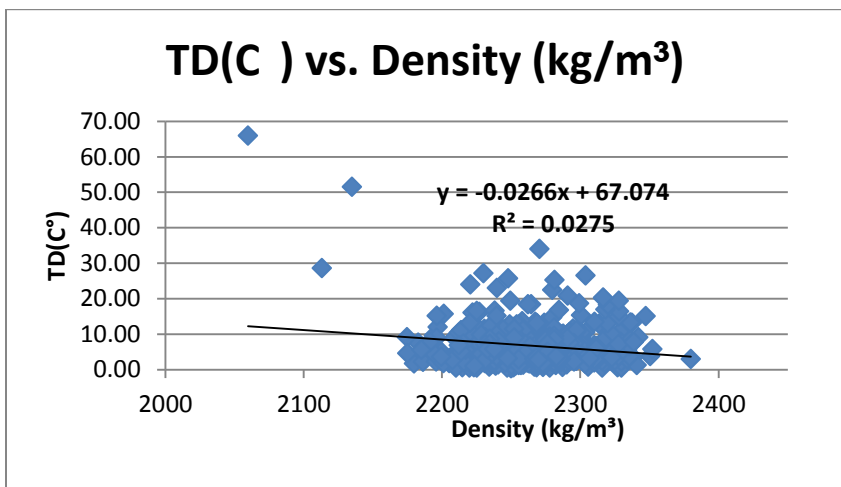


Figure 4.2 Relationship for All Collected Data Between temperature differential (TD) and density (DEN)

Table 4.1 Shows the correlation between a given temperature group and the relationship between TD and Den

TD GROUP OVER X °C	R-SQUARED	# OF DATA POINTS	TD GROUP OVER X °C	R-SQUARED	# OF DATA POINTS
Whole	0.0105	408	12°C	0.3394	51
1°C	0.0318	389	13°C	0.4242	43
2°C	0.0473	350	14°C	0.4371	34
3°C	0.069	297	15°C	0.4354	33
4°C	0.064	245	16°C	0.5291	27
5°C	0.082	217	17°C	0.6664	21
6°C	0.115	176	18°C	0.6562	20
7°C	0.1377	143	19°C	0.6507	16
8°C	0.1615	115	20°C	0.6547	14
9°C	0.1682	98	25°C	0.5932	10
10°C	0.2473	76	30°C	0.9882	3
11°C	0.2635	64	Total : R <sup>2</sup> = 0.9337		

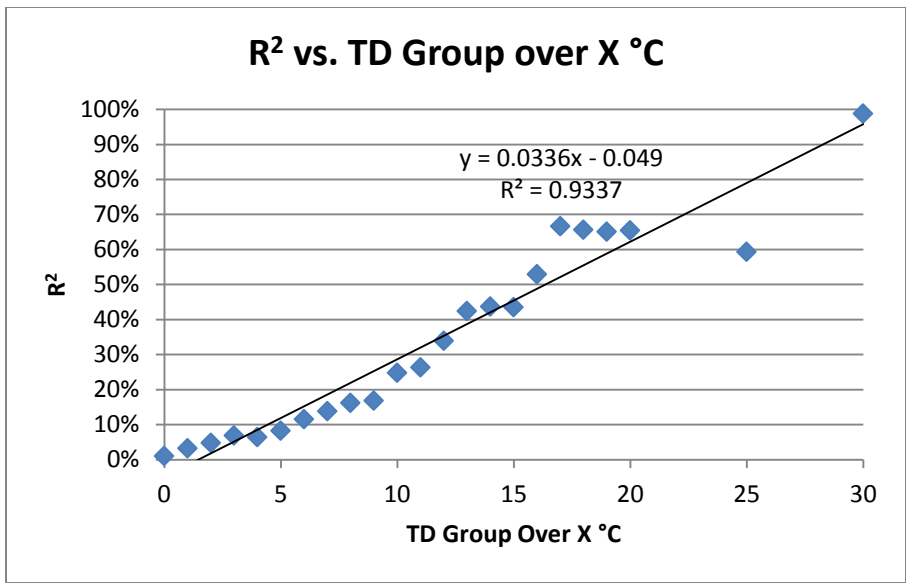


Figure 4.3 A graphical representation of the relationship between individual temperature groups and TD and DEN

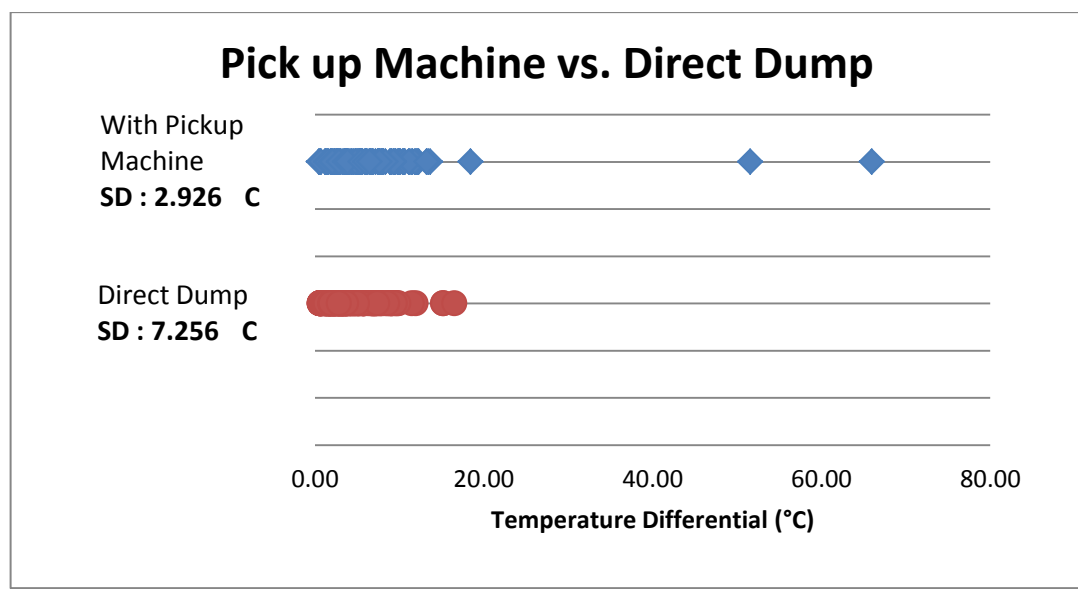


Figure 4.8 Temperature Differential based on feeding types

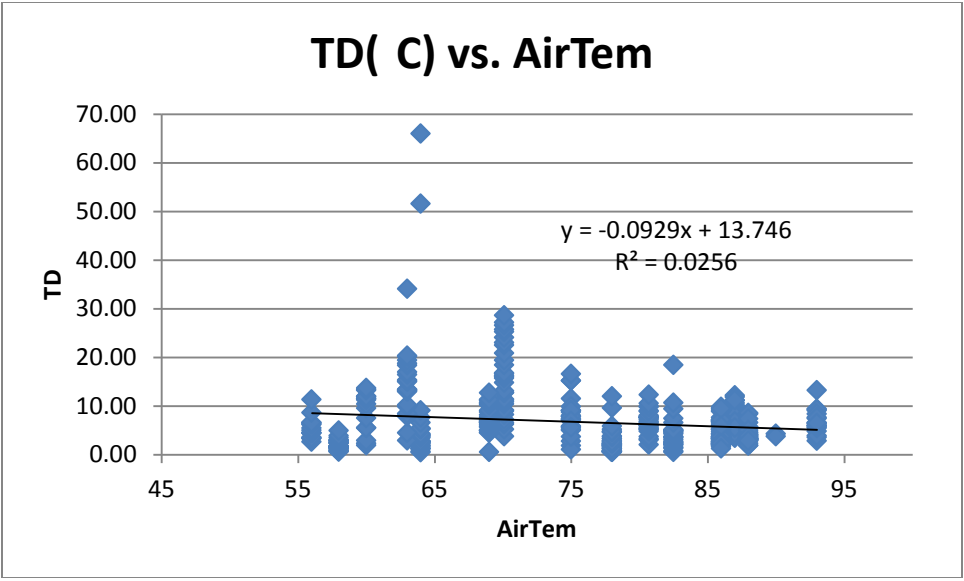


Figure 4.4 Relationship between ambient jobsite air temperature and temperature differential


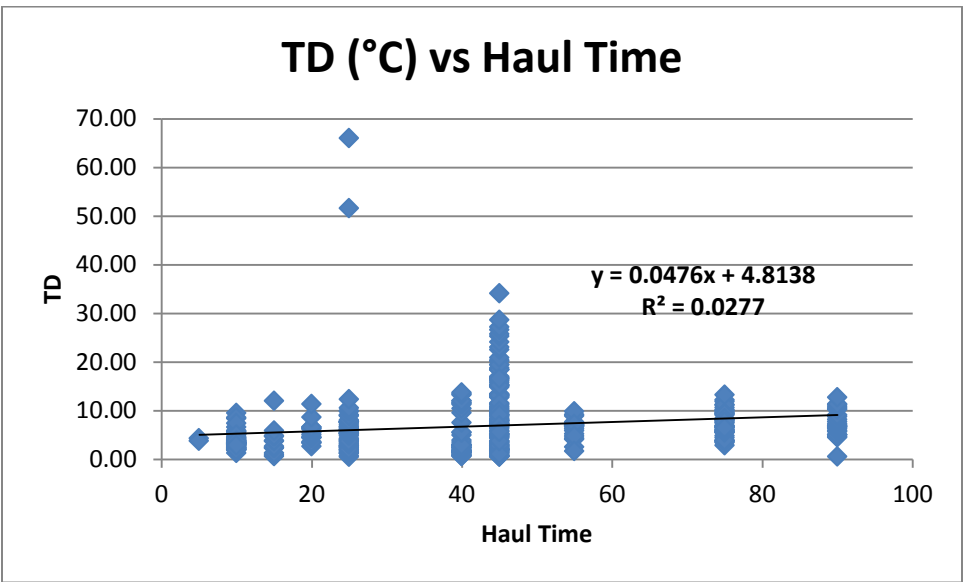


Figure 4.5 Relationship between Haul Time and Temperature Differentials

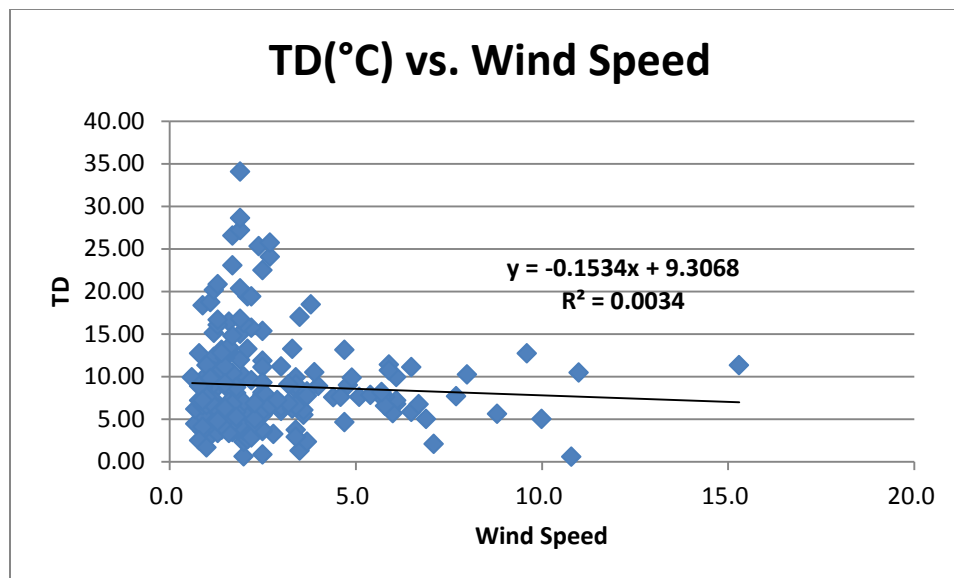

**Figure 4.9** Relationship between wind speed and temperature differentials (TD)



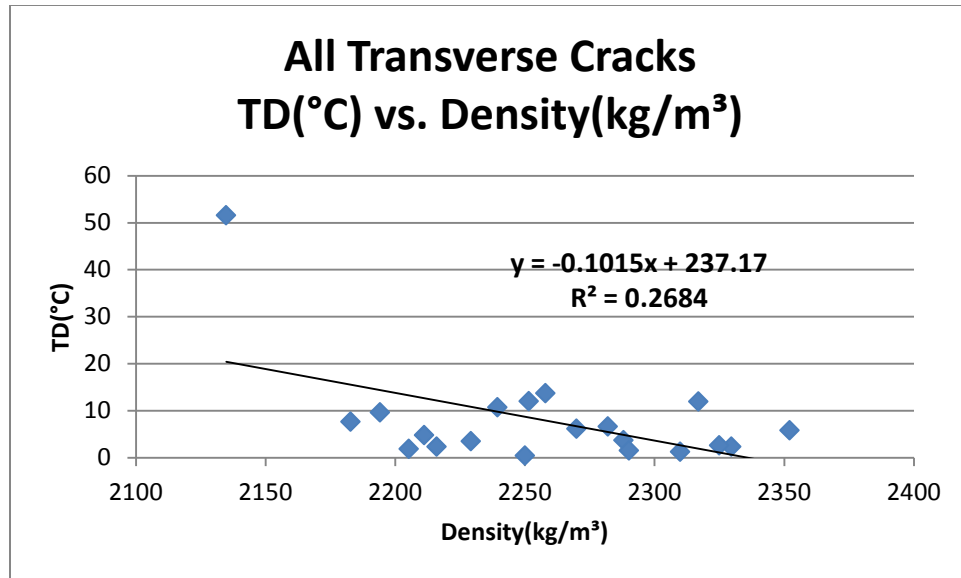


Figure 5.7 Relationship of TD and Density among Transverse Cracks

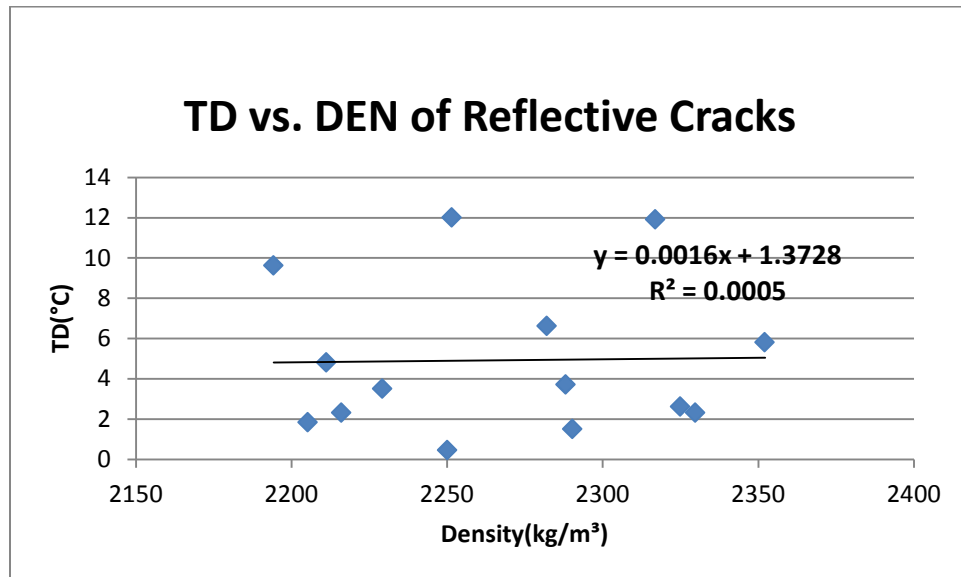


Figure 5.9 Temperature Differentials and Density Relationship Among Reflective Cracks

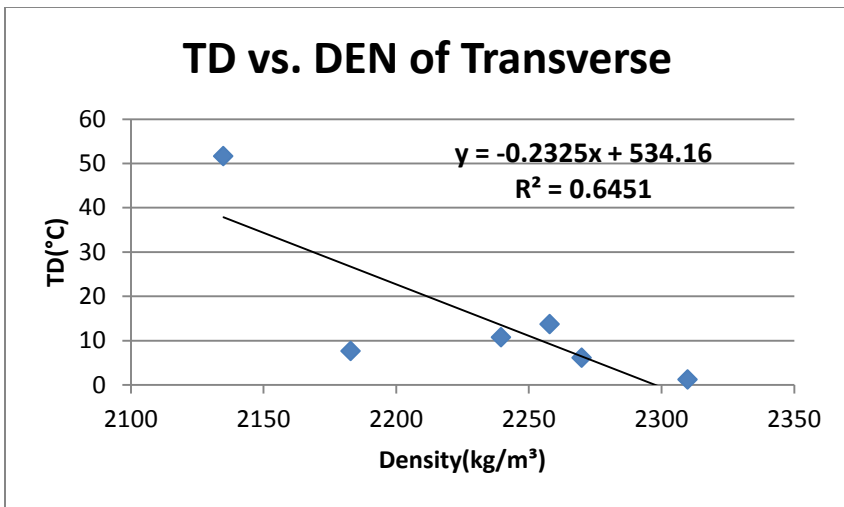


Figure 5.10 Relationship between temperature differentials (TD) and density (DEN) excluding reflective cracks

Table 5.3 Inspection Data Analysis

Num	TD (°C)	DEN(kg/m³)	Num	TD (°C)	DEN(kg/m³)	Num	TD (°C)	DEN(kg/m³)
1	1.1	2268.4	22	5.7	2228.382	43	11.3	2244.4
2	1.2	2310	23	6.1	2270	44	11.4	2227
3	1.3	2266.1	24	6.2	2282.9	45	13.3	2336.3
4	1.5	2130.7	25	6.6	2257.2	46	13.4	2267.6
5	1.5	2270	26	6.8	2321.3	47	13.7	2258
6	1.6	2236	27	7.6	2295.7	48	14.1	2281.5
7	1.9	2317.6	28	7.6	2182.9	49	15.0	2328
8	2.0	2237.6	29	8.4	2336.3	50	15.7	2201.4
9	2.2	2186.3	30	8.7	2234.79	51	16.1	2222.3
10	2.8	2232.5	31	9.0	2196.342	52	16.4	2328.3
11	2.9	2258.8	32	9.1	2225.178	53	18.3	2320.2
12	3.0	2334.114	33	9.2	2286.3	54	18.4	2264.7
13	3.3	2258.4	34	9.9	2286.054	55	20.2	2316.8
14	3.3	2258.8	35	9.9	2323.2	56	20.3	2316.8
15	3.9	2227.7	36	10.2	2300.8	57	20.8	2291.1
16	4.1	2219.7	37	10.2	2239.596	58	25.7	2247.9
17	4.3	2320.8	38	10.4	2229.984	59	28.6	2113.3
18	4.4	2299.2	39	10.5	2303.676	60	34.1	2270.3
19	5.0	2215.566	40	10.7	2239.596	61	51.6	2134.9
20	5.3	2198.9	41	10.8	2297.5	62	66.0	2059.7
21	5.4	2218.1	42	11.1	2217.168			

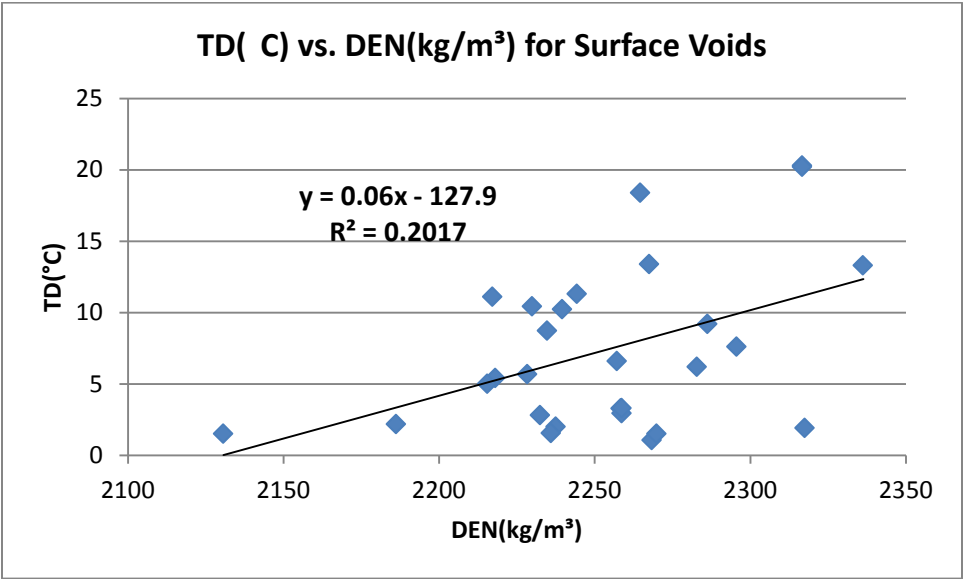


Figure 5.11 Relationship Between Temperature Differentials (TD) and Density (DEN) Among Surface Voids

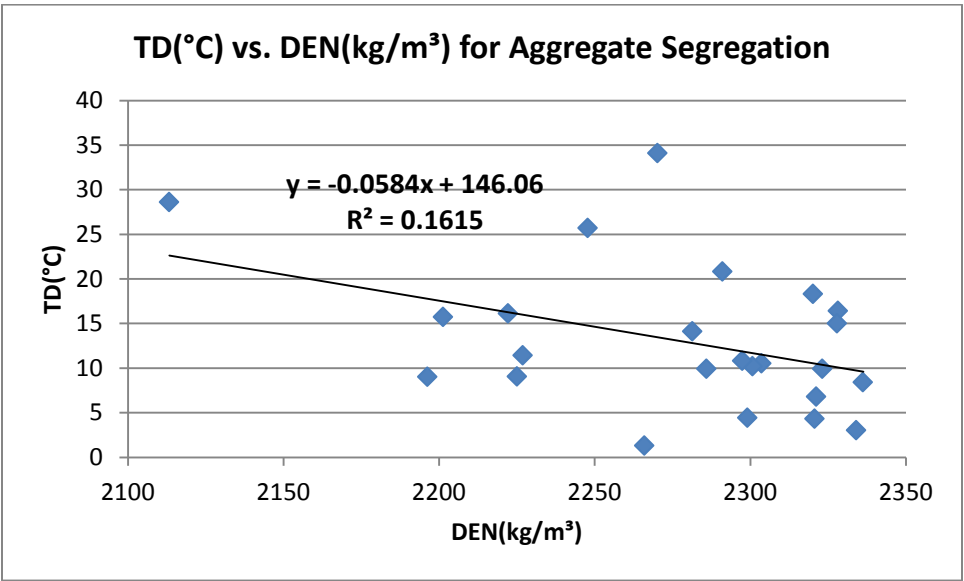


Figure 5.12 Relationship Between Temperature Differentials (TD) among Aggregate Segregation

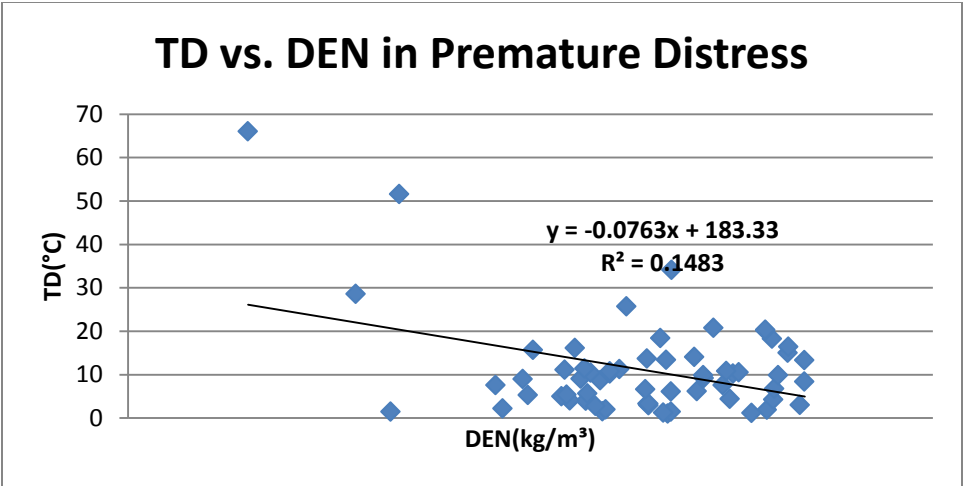


Figure 5.13 Relationships between Temperature Differentials and Density Among Total Instances of Observed Premature Distresses


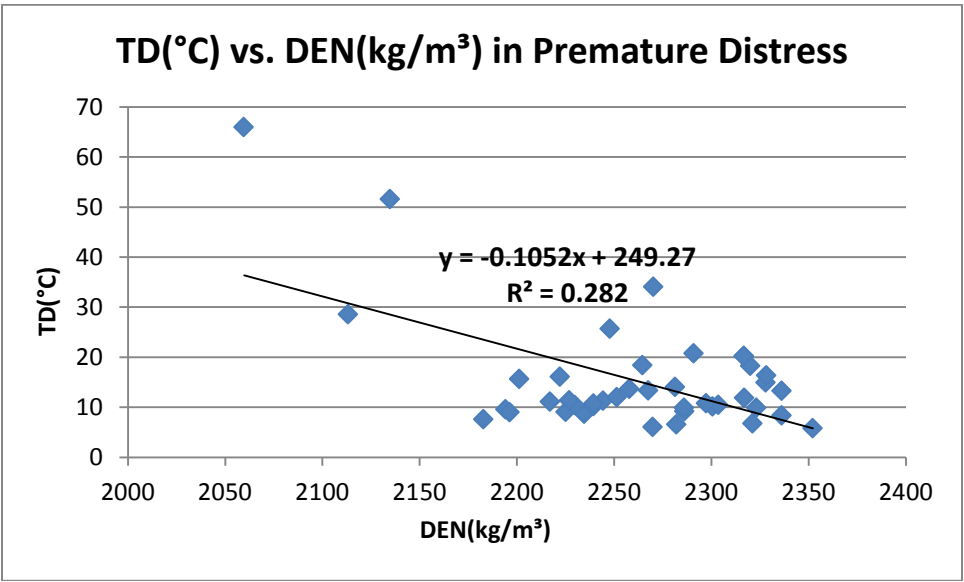


Figure 5.14 Relationship Between Temperature Differentials and Premature Distresses, Excluding Small Surface Voids

**Table 5.4 Relationship between R<sup>2</sup> and corresponding TD groups for premature distresses**


Num	Temperature Diff. Range(°C)	R-Squared	Included Premature Distress Data Points
1	whole	0.282	48
2	5°C and Up	0.3693	32
3	10°C and Up	0.5707	20
4	15°C and Up	0.5904	11
5	20°C and Up	0.5966	6
6	30°C and Up	0.9885	3

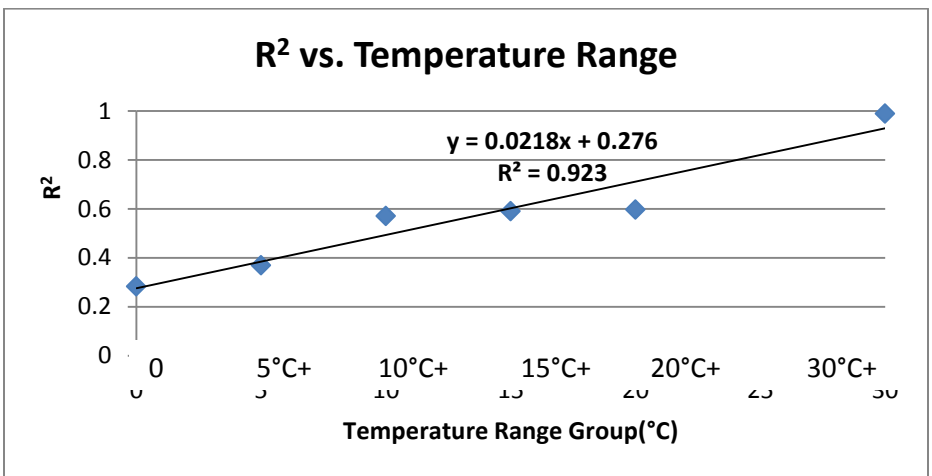


**Figure 5.15 Relationship between the correlation of TD and DEN for a given temperature range and the temperature range group**

**Table 5.5 Temperature Differential Range (TD) vs. Type of Premature Distress (PD) (with surface voids)**

TD (°C)	Transverse	Small Voids	Agg.segregation	Multi-Crack	Total	DATA Total	%
1-5	1	11	4	2	18	123	14.6%
5-10	2	8	6	1	17	75	22.7%
10-15	2	6	5	0	13	34	38.2%
15-20	0	1	5	0	6	16	37.5%
20-25	0	2	1	0	3	6	50.0%
25-30	0	0	2	0	2	5	40.0%
30+	1	0	1	1	3	3	100.0%
<b>Total</b>	<b>6</b>	<b>28</b>	<b>24</b>	<b>4</b>	<b>62</b>	<b>262</b>	<b>43.3%</b>

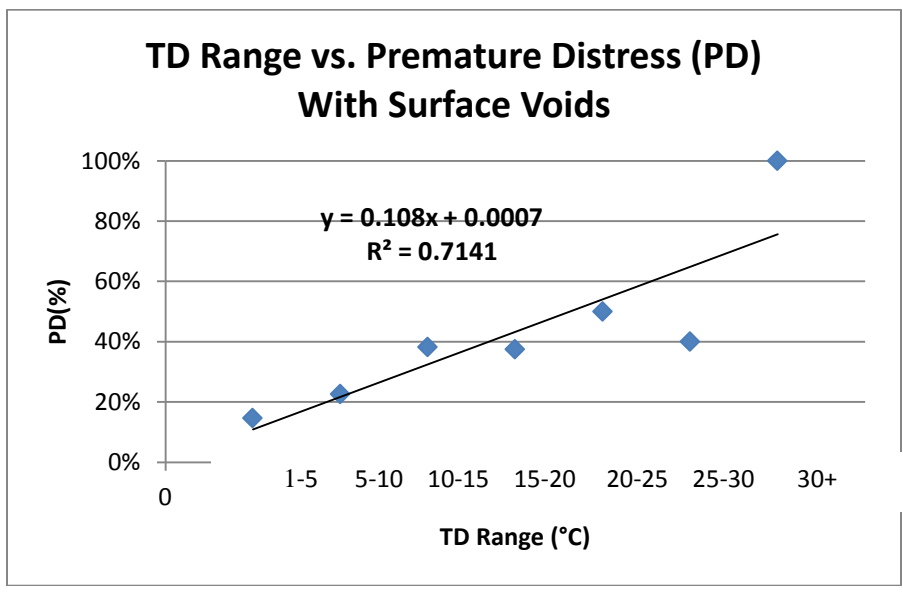

**Figure 5.16 Correlation between the percentages of premature distresses, including surface voids, found within a specified temperature range**

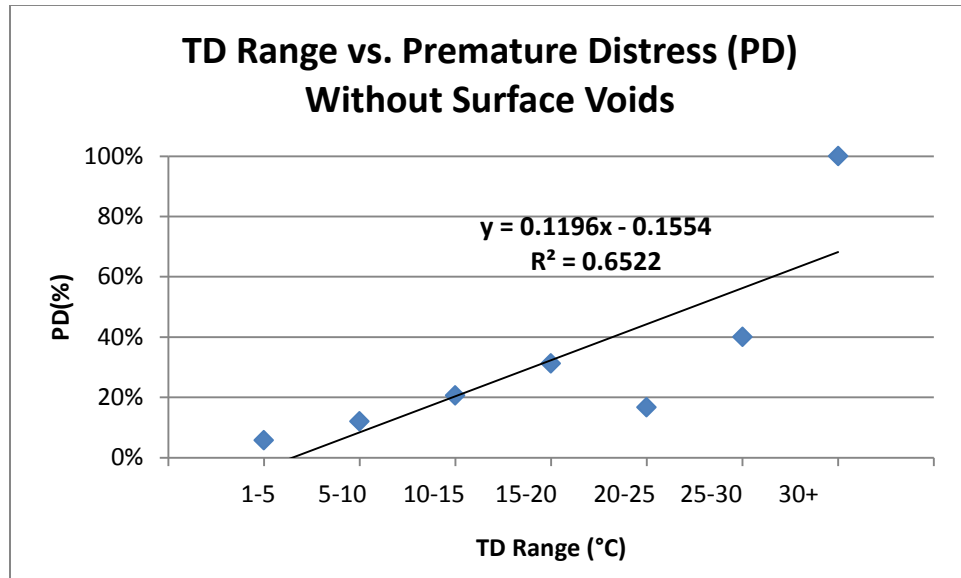

**Figure 5.17** Correlation between the percentages of premature flaws, excluding surface voids, found within a specified temperature range