

University of Nebraska - Lincoln

DigitalCommons@University of Nebraska - Lincoln

Ralph Skomski Publications

Research Papers in Physics and Astronomy

2012

Magnetism of Less Common Cobalt-Rich Alloys

Bhaskar Das

University of Nebraska-Lincoln, bhaskar.das@huskers.unl.edu

Balamurugan Balamurugan

University of Nebraska-Lincoln, balamurugan@unl.edu

Wenyong Zhang

University of Nebraska-Lincoln, wenyong.zhang@unl.edu

Ralph Skomski

University of Nebraska-Lincoln, rskomski2@unl.edu

E. Krage

University of Nebraska-Lincoln

See next page for additional authors

Follow this and additional works at: <https://digitalcommons.unl.edu/physicsskomski>


Das, Bhaskar; Balamurugan, Balamurugan; Zhang, Wenyong; Skomski, Ralph; Krage, E.; Valloppilly, Shah R.; Shield, Jeffrey E.; and Sellmyer, David J., "Magnetism of Less Common Cobalt-Rich Alloys" (2012). *Ralph Skomski Publications*. 89.

<https://digitalcommons.unl.edu/physicsskomski/89>

This Article is brought to you for free and open access by the Research Papers in Physics and Astronomy at DigitalCommons@University of Nebraska - Lincoln. It has been accepted for inclusion in Ralph Skomski Publications by an authorized administrator of DigitalCommons@University of Nebraska - Lincoln.

Authors

Bhaskar Das, Balamurugan Balamurugan, Wenyong Zhang, Ralph Skomski, E. Krage, Shah R. Valloppilly, Jeffrey E. Shield, and David J. Sellmyer



Magnetism of Less Common Cobalt-Rich Alloys

B. DAS,^{1,2)} B. BALAMURUGAN,^{1,2)} W.Y. ZHANG,^{1,2)} R. SKOMSKI,^{1,2)} E.S. KRAGE,^{2,3)} S.R. VALLOPILLY,²⁾ J.E. SHIELD,^{1,4)}, and D.J. SELLMYER^{1,2)}

¹⁾ Nebraska Center for Materials and Nanoscience, University of Nebraska, Lincoln, NE-68588, USA

²⁾ Department of Physics and Astronomy, University of Nebraska, Lincoln, NE-68588, USA

³⁾ Department of Physics, South Dakota University, Brookings, SD-57007, USA

⁴⁾ Department of Mechanical and Materials Engineering, University of Nebraska, Lincoln, NE-68588, USA

Abstract—Alternative permanent-magnet materials with intermediate performance, such as $K_I \geq 1 \text{ MJ/m}^3$, are investigated experimentally. Our focus is on the structural and magnetic properties of bulk $\text{YCo}_{5-x}\text{Fe}_x$ and on rare-earth-free transition-metal alloys such as $\text{TM}_x\text{Co}_{100-x}$ (TM = Zr, Hf). $\text{YCo}_{5-x}\text{Fe}_x$ alloys ($x = 0$ to 0.75), which crystallize in the hexagonal CaCu_5 -type structure, exhibit an improved of anisotropy and magnetization as x increases from 0 to 0.75, but the anisotropy increase is much less pronounced than recent theoretical predictions. $\text{Zr}_x\text{Co}_{100-x}$ and $\text{Hf}_x\text{Co}_{100-x}$ exhibit reasonable room-temperature hard-magnetic properties, such as coercivities of 0.10 to 0.28 T and magnetizations of 0.60 to 0.94 T.

I. INTRODUCTION

Rare-earth cobalt alloys, especially SmCo_5 and $\text{Sm}_2\text{Co}_{17}$, are the first rare-earth permanent magnets and continue to be useful for high-temperature applications [1-2]. In particular, RCo_5 (R = Sm, Y), which crystallizes in the hexagonal CaCu_5 -type structure, exhibit high anisotropies at room temperature and above, and there are continuing theoretical [3-6] and experimental [7, 8] attempts to further improve their magnetic properties by doping with a third element, such as B and Fe. For example, recent density-functional calculations have shown that Fe in $\text{RCo}_{5-x}\text{Fe}_x$ increases both the magnetic anisotropy constant K_I and magnetic polarization J_s for small fractions of Fe ($x \leq 0.35$) [4]. However, it is unclear to what extent these predictions are consistent with experiment.

Beyond the hexagonal 1:5 and rhombohedral or hexagonal 2:17 structures, there are other noncubic Co-rich intermetallics, and atomic substitutions yield a rich variety of related pseudoternary compounds. For example, $\text{Zr}_2\text{Co}_{11}$ and HfCo_7 are part of the ongoing search for alternative permanent-magnet alloys due to their high Curie temperatures ($T_c > 600 \text{ K}$), and non-cubic structures, which can create high anisotropy in these materials [9-12]. The crystal structure of the last alloy is only partially known, but unrelated to the hexagonal SmCo_5 and SmCo_7 . Our current research focuses on the improvement of magnetic properties by further doping or alloying Y alloys with a

third element such as Fe and search for rare-earth-free alloys with high $K_I \geq 1 \text{ MJ/m}^3$.

II. EXPERIMENTAL METHODS

$\text{YCo}_{5-x}\text{Fe}_x$ alloys with different Fe concentrations ($x = 0, 0.25, 0.50, \text{ and } 0.75$) were prepared using a conventional arc-melting technique followed by high-temperature thermal annealing at $1100 \text{ }^\circ\text{C}$ for 48 hrs. The alloys were then ground into small particles for structural and magnetic investigation. To determine K_I , the as-produced $\text{YCo}_{5-x}\text{Fe}_x$ particles were embedded in an epoxy resin and the easy axes were subsequently aligned with a magnetic pulse field of 12 T.

The $\text{Zr}_x\text{Co}_{100-x}$ and $\text{Hf}_x\text{Co}_{100-x}$ alloys were produced by melt spinning. For this, high-purity elements with appropriate compositions were mixed homogeneously using conventional arc melting and subsequently melt spun to obtain ribbons. The rapid cooling during the melt spinning process is advantageous for controlling phase purity and microstructure, which is important to realize the permanent-magnet properties of the alloys.

X-ray diffraction (XRD: Rigaku D/Max-B diffractometer), transmission-electron microscopy (TEM: JEOL 2010 with an acceleration voltage of 200 kV), energy dispersive x-ray analysis (EDX, JEOL JSM 840A scanning electron microscope), and SQUID magnetometry were used for characterization.



III. STRUCTURAL AND MAGNETIC PROPERTIES OF YCo_{1-x}Fe_x BULK ALLOYS

The structural properties of as-produced YCo_{5-x}Fe_x alloys as a function of Fe concentration were investigated using x-ray diffraction. For example, Fig. 1(a) shows the XRD patterns for YCo_{5-x}Fe_x ($0 \leq x \leq 0.75$).

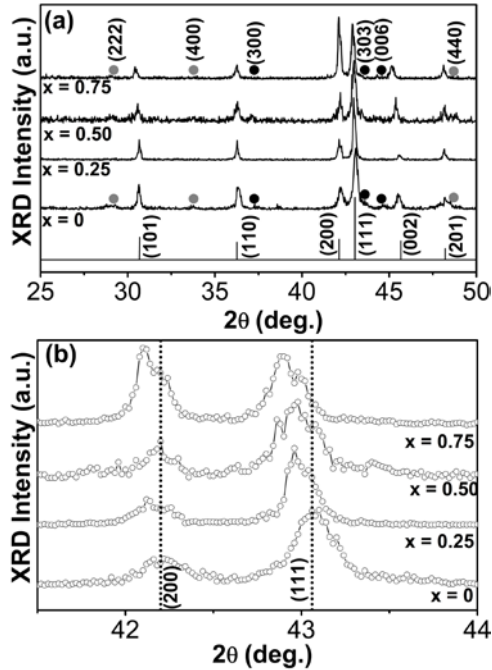


Fig. 1 X-ray diffraction patterns: (a) YCo_{5-x}Fe_x alloys of different Fe concentrations with the standard positions and relative intensities of the diffraction peaks corresponding to YCo₅ (vertical lines), Y₂Co₁₇ (black dots) and Y₂O₃ (gray dots), and (b) the expanded x-ray diffraction patterns at $2\theta = 41.5^\circ$ to 44.0° , showing the composition-dependent shift in the peak positions as guided by the dotted lines.

The standard peak positions and relative intensities of the diffraction peaks corresponding to the hexagonal CaCu₅-type structure of YCo₅ are shown as black solid vertical lines [13]. The XRD peaks are sharp and intense, revealing well-developed polycrystallites, and also in good agreement with the hexagonal CaCu₅-type structure. A minor presence of Y₂O₃ and Y₂Co₁₇ is, however, evident from the weak diffraction peaks corresponding to these phases, as indicated by the respective gray and black dots in Fig. 1(a) [14, 15].

The weak diffraction peaks corresponding to Y₂O₃ phase, such as (222) and (440) in Fig. 1(a), are also broad due to the well-known crystallite size of Y₂O₃. In addition, the standard-maximum intensity (330) peak of Y₂Co₁₇ phase also appears as a weak hump near to most intense

(111) peak of the YCo₅ phase. Note that conventional preparation techniques (such as arc melting followed by high-temperature thermal annealing for bulk RCo₅ alloys) are generally expected to produce a small fraction of 2:17 phase during the cooling process [16, 17].

We also have carried out Rietveld analysis to quantify these phases [18], but an accurate refinement was limited by the broadness of Y₂O₃ peaks and a shift in the peak positions of YCo₅ phase along with an increased intensity of the (200) peak on substituting Fe for Co in YCo_{5-x}Fe_x. Nevertheless, as an example, Rietveld analysis for YCo_{4.75}Fe_{0.25} typically yields 95.1 wt. % of YCo_{4.75}Fe_{0.25}, 0.6 wt. % of Y₂O₃ and 4.3 wt. % of Y₂Co₁₇.

To trace the changes in the YCo₅ lattice upon Fe substitution, we have expanded the XRD patterns of the as-produced YCo_{5-x}Fe_x alloys in the 2θ range from 41.5° to 44.0° , as shown in Fig. 1(b). We see a systematic shift in the angular positions of the Bragg reflections from YCo₅ phase towards lower angles as x increases from 0 to 0.5. This corresponds to a lattice expansion upon the substitution of Fe for Co. For example, the lattice constants increased from $a = 4.940 \text{ \AA}$ and $c = 3.981 \text{ \AA}$ to $a = 4.950 \text{ \AA}$ and $c = 4.009 \text{ \AA}$ on varying x from 0 to 0.75. In addition, the intensity of (200) peak also increases as compared to that of (111) peak as x increases from 0 to 0.75. This indicates the stabilization of the hexagonal CaCu₅-type structure in YCo_{5-x}Fe_x alloys for x up to 0.75.

In order to determine the anisotropy constant K_1 , we have measured the parallel and perpendicular M - H curves at 300 K for magnetically aligned YCo_{5-x}Fe_x alloys, as shown for YCo₅, Fig. 2(a), and YCo_{4.5}Fe_{0.5}, Fig. 2(b).


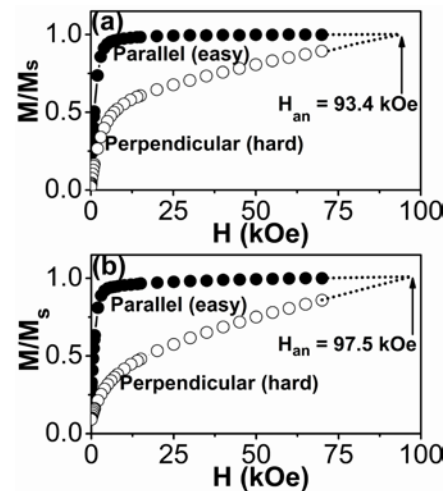


Fig. 2 Parallel and perpendicular M - H curves measured at 300 K : (a) aligned YCo₅ and (b) aligned YCo_{4.5}Fe_{0.5}.



The straight approach of the perpendicular curves to the saturation indicates that the effect of K_2 is very small. In addition, a striking feature of these curves is that the perpendicular $M-H$ intersects the magnetization axis at $M > 0$. This feature can be presumably due to the collective effects of the grain-misalignment and weak presence of secondary phases..

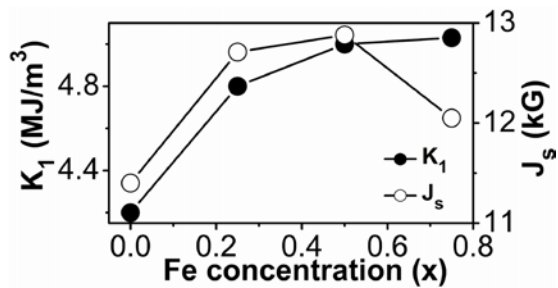


Fig. 3 Room-temperature magnetic anisotropy constant K_1 and saturation magnetic polarization J_s of $\text{YCo}_{5-x}\text{Fe}_x$ as a function of Fe concentration (x).

The K_1 of the hard YCo_5 phase can be, however, obtained from the magnetic anisotropy field H_{an} . As indicated in Fig. 2, H_a is given by the intercept between the parallel and linear portion of the perpendicular curves, and this method has an error of typically less than 10% [1, 19, 20]. Figure 3 shows the corresponding values of K_1 and J_s of $\text{YCo}_{5-x}\text{Fe}_x$ as a function of Fe concentration.

As x varies from 0 to 0.75, the room-temperature anisotropy of $\text{YCo}_{5-x}\text{Fe}_x$ improves from 4.2 to 5.0 MJ/m^3 , and the magnetization also increases. This is consistent with previous findings, including theoretical calculations [4-7]. Furthermore, the moderate improvements due to Fe substitutions in rare-earth cobalt magnets have long been explored and exploited in industry. Even in cases where Fe leaves the magnetic properties of a rare-earth cobalt alloy unchanged, Fe substitution is preferred, because Fe is much cheaper than Co.

Interestingly, density-functional calculations tend to overestimate the anisotropy difference between YCo_5 and $\text{YCo}_{5-x}\text{Fe}_x$. For example, they predict that K_1 increases from 2.7 MJ/m^3 in YCo_5 to 4.7 MJ/m^3 in $\text{YCo}_{4.65}\text{Fe}_{0.35}$ [4]. Similarly, the calculated band-filling dependence of the magnetic anisotropies also reveals an increase in K_1 from about 8.3 MJ/m^3 (YCo_5) to a maximum of 26.5 MJ/m^3 for YCo_4Fe [7]. These theoretical calculations were performed at zero temperature, but the temperature dependence of the

anisotropy of YCo_5 is notoriously weak [2] and cannot account for the high anisotropy values predicted by some of the calculations.

IV. RARE-EARTH-FREE $\text{Zr}_x\text{Co}_{100-x}$ and $\text{Hf}_x\text{Co}_{100-x}$ BULK ALLOYS

The XRD patterns and TEM images of $\text{Zr}_x\text{Co}_{100-x}$ ($16 \leq x \leq 21$) show the presence of predominant $\text{Zr}_2\text{Co}_{11}$ phase having a rhombohedral structure, along with comparatively weak hcp Co and cubic $\text{Zr}_6\text{Co}_{23}$ phases [21, 22]. The soft magnetic Co and $\text{Zr}_6\text{Co}_{23}$ phases are expected to form exchange coupling to the hard magnetic $\text{Zr}_2\text{Co}_{11}$ phase.


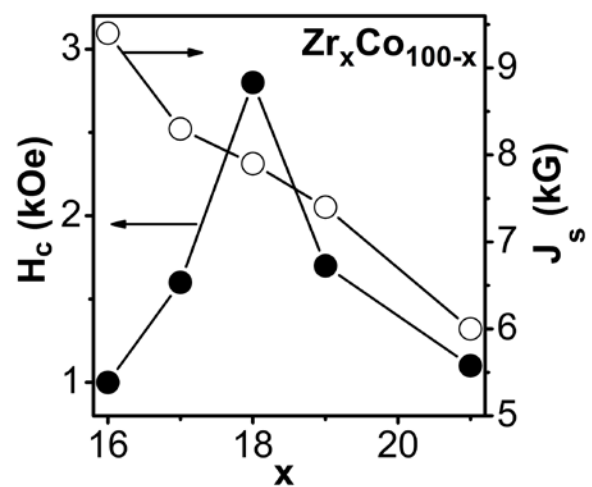


Fig. 4 Coercivity H_c and saturation polarization J_s measured at 300 K for $\text{Zr}_x\text{Co}_{100-x}$ alloys as a function of Zr concentration x .

Figure 4 shows that $\text{Zr}_x\text{Co}_{100-x}$ is hard-magnetic, with coercivities larger than 1 kOe and appreciable magnetizations between 0.60 and 0.95 T at room temperature. The coercivity changes in Fig. 4 mainly depend on the amount of hard magnetic $\text{Zr}_2\text{Co}_{11}$ phase in these samples [22].

Similarly, H_c increases from 0.05 to 1.8 kOe at 300 K on increasing x from 0 to 12.5 in $\text{Hf}_x\text{Co}_{100-x}$ [23]. For $x = 12.5$, $\text{Hf}_x\text{Co}_{100-x}$ forms a HfCo_7 phase having orthorhombic structure. Available literature data on the unit cells are contradictory and however, a careful analysis of the question goes far beyond the present paper and will be discussed elsewhere.

It is worthwhile mentioning that $M-H$ curves of both Zr-Co and Hf-Co do not saturate even in fields of 7 T. While the approach to saturation is relatively slow for isotropic magnets, this nevertheless confirms the high



magnetic anisotropy of the materials. More explicitly, K_I was evaluated from the high-field magnetization curves of these alloys ($H \geq 30$ kOe) using the law of approach to saturation method [24]. The corresponding room-temperature anisotropy values are 1.1 and 1.6 MJ/m³ for Zr₁₈Co₈₂ and Hf_{12.5}Co_{87.5}, respectively.

V. CONCLUSIONS

The structural and magnetic properties of YCo_{5-x}Fe_x and rare-earth-free transition metal alloys such as Zr_xCo_{100-x} and Zr_xCo_{100-x} were investigated. The magnetic anisotropy constant K_I improves from 4.2 to 5.0 MJ/m³ at 300 K along with an improvement of J_s on varying x from 0 to 0.75 in YCo_{5-x}Fe_x. This general trend is consistent with recently reported theoretical investigations based on density-functional and band-filling calculations. However, it seems that density-functional calculations significantly overestimate the anisotropy enhancement due to Fe, and further research will be necessary to explain the discrepancies.

Zr-Co and Hf-Co alloys also exhibit a fairly high anisotropy of $K_I \geq 1.0$ MJ/m³. Concerning price and performance, these rare-earth-free permanent-magnet materials are generally intermediate between Ba ferrite and rare-earth permanent magnets, and future research will show whether any of these materials can be developed into industrial magnets.

ACKNOWLEDGMENT

This work is supported by US DOE (DE-FG02-04ER46152, DJS), ARPA-E (DE-AR 0000046, B.B. and B.D.), NSF-MRSEC (Grant No. DMR-0820521, R.S. and J.E.S.), BREM (WYZ), and NCMN.

REFERENCES

- [1] K. Strnat, G. Hoffer, J. Olson, W. Ostertag, and J.J. Becker, *J. Appl. Phys.* 38, 1001 (1967).
- [2] R. Skomski and J.M.D. Coey, *Permanent Magnetism*, Institute of Physics, Bristol 1999.
- [3] P. Larson, I. I. Mazin, and D. A. Papaconstantopoulos, *Phys. Rev. B* 69, 134408 (2004).
- [4] I. Opahle, M. Richter, M.D. Kuz'min, U. Nitzsche, K. Koepernik, L. Schramm, *J. Magn. Magn. Mater.* 290-291, 374 (2005).
- [5] G.H.O. Daalderop, P.J. Kelly, and M.F.H. Schuurmans, *Phys. Rev. B* 53, 14415 (1996).
- [6] L. Steinbeck, M. Richter, and H. Eschrig, *Phys. Rev. B* 63, 184431 (2001).
- [7] H. Ido, K. Konno, H. Ogata, K. Sugiyama, H. Hachino, M. Date, and K. Maki, *J. Appl. Phys.* 70, 6128 (1991).
- [8] J.J.M. Franze, N.P. Thuy, and N.M. Hong, *J. Magn. Magn. Mater.* 72, 361 (1988).
- [9] A.M. Ghemawat, M. Foldeaki, R.A. Dunlap, and R.C. O'Handley, *IEEE Trans. Mag.* 25, 3312 (1989).
- [10] G.V. Ivanova, N.N. Schegoleva, and A.M. Gabay, *J. Alloys. Comp.* 423, 135 (2007).
- [11] K.H.J. Buschow, J.H. Wernick. And G.Y. Chin, *Journal of the Less Common Metals.* 59, 61 (1978)..
- [12] K.H.J. Buschow, *J. Appl. Phys.* 53, 7713 (1982).
- [13] ICDD-International Centre for Diffraction Data, Card No. 01-071-7515.
- [14] ICDD-International Centre for Diffraction Data, Card No. 04-043-1036.
- [15] ICDD-International Centre for Diffraction Data, Card No. 04-005-4950.
- [16] J.T.E. Galindo, J.A. Matutes-Aquino, M. Costes, and J.M. Broto, *J. Appl. Phys.* 105, 07A725 (2009).
- [17] J.T.E. Galindo, F.J. Rivera Gomez, and J.A. Matutes-Aquino, *J. Appl. Phys.* 99, 08B512 (2006).
- [18] H.M. Rietveld, *J. Appl. Cryst.* 2, 65 (1969).
- [19] Y.Q. Guo, W. Li, J. Luo, W.C. Feng, and J.K. Liang, *J. Magn. Magn. Mater.* 303, e367 (2006).
- [20] Y. Guo, W. Feng, W. Li, J. Luo, and J. Liang, *J. Appl. Phys.* 101, 023919 (2007).
- [21] W.Y. Zhang, S. Valloppilly, X.Z. Li, R. Skomski, J.E. Shield, and D.J. Sellmyer, *IEEE Trans. Mag.* (in press).
- [22] W.Y. Zhang, X.Z. Li, S. Valloppilly, R. Skomski, J.E. Shield, and D.J. Sellmyer (in preparation).
- [23] B. Das, B. Balamurugan, V.R. Shah, R. Skomski, and D.J. Sellmyer (in preparation).
- [24] G.C. Hadjipanayis, D.J. Sellmyer, and B. Brandt, *Phys. Rev. B* 23, 3349, 1978.